

ASX Announcement

EXCEPTIONAL RESULTS FROM MAIDEN RC DRILLING PROGRAM AT HATCHES CREEK

Highlights

- RC drilling at four prospects confirms polymetallic mineralisation.
- Several prospects intersected wide zones of mineralisation in areas where narrow high grades were expected.
- Intersections include:
 - HCRC013, 44m at 0.21% WO₃ and 0.12% Cu, from 55m
 - HCRC014, 53m at 0.26% WO₃ and 0.13% Cu, from 63m
 - HCRC016, 7m @ 0.73% WO₃, and 0.01% Cu, from 81m
 - HCRC010, 2m @ 3.05% WO₃ and 0.02% Cu, from 3m
 - HCRC004, 1m @ 2.85% WO₃, 1.76g/t Au and 0.29% Cu, from 43m
 - HCRC004, 1m @ 1.96% WO₃, 1.58g/t Au and 0.28% Cu, from 80m
- Follow up drilling planned along strike as well as at next set of targets.
- Metallurgical test work undertaken as part of the original dumps project in 2015 produced a concentrate of 66% WO₃. In addition, a sulphide pre-float produced a concentrate assaying 16.4% Cu and 7.9g/t Au, demonstrating the ability to recover both tungsten and other valuable by-products.
- Recent test work undertaken on dump samples from Pioneer showed that 97% of the WO₃ could be recovered, with 34% mass reduction by simply crushing. At Hit or Miss, a combination of screening and X-ray ore sorting test work has resulted in a 98% WO₃ yield and a mass rejection of 24%.

GWR Group Limited (ASX: GWR) ("GWR" or "the Company") is pleased to announce that Reverse Circulation (RC) drilling at the Hatches Creek Project in the Northern Territory has successfully intersected tungsten mineralisation (WO₃) as well as copper (Cu) and gold (Au) at some of the prospects.

GWR tested four prospects in this initial drilling campaign, with targets assessed based on previous dump sampling, mapping and accessibility.

At **Treasure**, broad zones of tungsten and copper mineralisation were intersected. Where the initial target was narrow high grade zones, the drilling returned 53m at 0.26% WO₃ and 0.13% Cu, from 63m in HCRC014 and 44m at 0.21% WO₃ and 0.12% Cu, from 55m in HCRC013.

Intersections at **Hit or Miss** included wide zones such as 36m at 0.18% WO₃ and 0.24% Cu in HCRC011 from 52m and narrow high grade intersections including 2m at 3.05% WO₃ from 3m in HCRC010.

At **Pioneer**, the Company intersected multiple stacked zones of mineralisation that correspond with historical mining zones. Several of the holes intersected at least three stacked mineralised zones. Better results included 2m at 1.60% WO₃, 0.96g/t Au and 0.36% Cu from 43m in HCRC004, also in HCRC004, 1m @ 1.96% WO₃, 1.58g/t Au and 0.28% Cu, from 80m and 3m at 0.63% WO₃ from 81m in HCRC002. Eight of the mineralised tungsten zones also had coincident gold grades of greater than 0.8g/t Au.

At **Copper Show**, tungsten and copper mineralisation were of a similar tenor in the intersected holes. Results included 1m at 0.58% WO₃ and 0.54% Cu from 3m and 1m at 0.49% WO₃ and 0.12% Cu, both in HCRC006.

GWR's Chief Executive Officer, Craig Ferrier, said "These are excellent results from what was the first modern drilling program ever completed at Hatches Creek.

"While further drilling is required before we can confidently say that we have made a new polymetallic discovery, the success rate that we have had in this first program coupled with the grades and widths encountered, offers significant upside potential for shareholders."

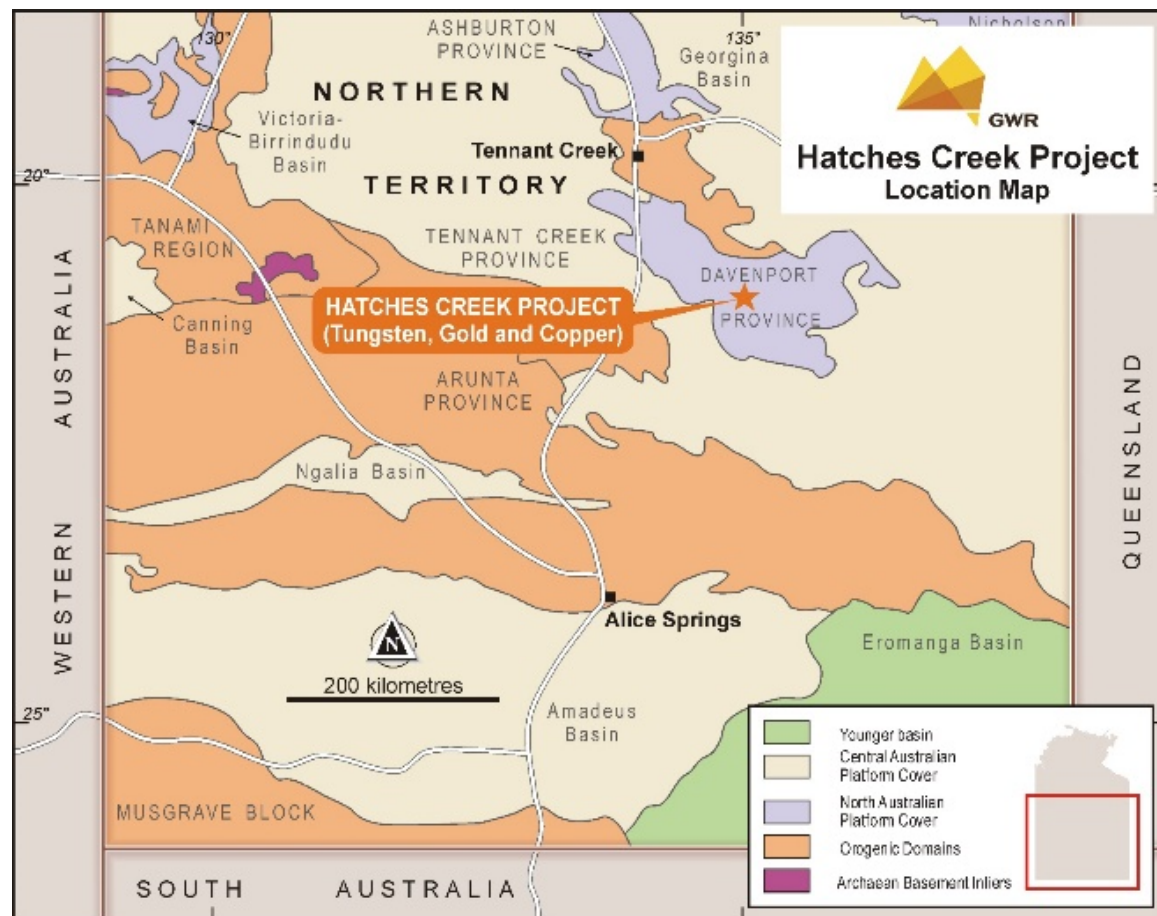


Figure 1: Hatches Creek Location Plan

Hatches Creek Drilling Program

GWR has completed an 18 hole, 1,739m maiden RC drilling program at its 100% owned Hatches Creek project located in the Northern Territory (Figure 1). Four prospect areas were targeted; Pioneer, Hit or Miss, Treasure and Copper Show (Table 1), while an additional 11 prospects remain to be drilled.

The drilling has intersected significant tungsten and copper mineralisation in all four areas targeted and at Treasure and Hit or Miss over much larger widths than expected. At Pioneer, the tungsten and copper mineralisation is also accompanied by gold mineralisation confirming the polymetallic nature of the mineralised structures.

Table 1
Drill Hole Collar Summary

Prospect	Tenement	Hole #	Depth (M)	East (MGA)	North (MGA)	RL	Azimuth / Dip
Pioneer	EL23463	HCRC001	29	518740	7692154	403	360/-60
Pioneer	EL23463	HCRC002	96	518744	7692114	401	360/-60
Pioneer	EL23463	HCRC003	130	518750	7692074	399	360/-60
Pioneer	EL23463	HCRC004	100	518630	7692080	400	360/-60
Pioneer	EL23463	HCRC005	84	518626	7692117	402	360/-60
Copper Show	EL22912	HCRC006	40	516950	7685380	450	180 /-60
Copper Show	EL22912	HCRC007	50	516950	7685400	450	180 /-60
Copper Show	EL22912	HCRC008	100	516950	7685425	450	180 /-60
Hit or Miss	EL22912	HCRC009	100	519590	7685740	431	090/-60
Hit or Miss	EL22912	HCRC010	100	519550	7685740	430	090/-60
Hit or Miss	EL22912	HCRC011	100	519510	7685740	430	090/-60
Hit or Miss	EL22912	HCRC012	100	519470	7685750	432	090/-60
Treasure	EL22912	HCRC013	120	519840	7686860	425	090/-60
Treasure	EL22912	HCRC014	120	519925	7686850	432	270/-60
Treasure	EL22912	HCRC015	120	519845	7687050	443	090/-60
Treasure	EL22912	HCRC016	150	519800	7687070	438	090/-60
Hit or Miss	EL22912	HCRC017	100	519460	7685750	432	090/-60
Hit or Miss	EL22912	HCRC018	100	519620	7685745	435	090/-60

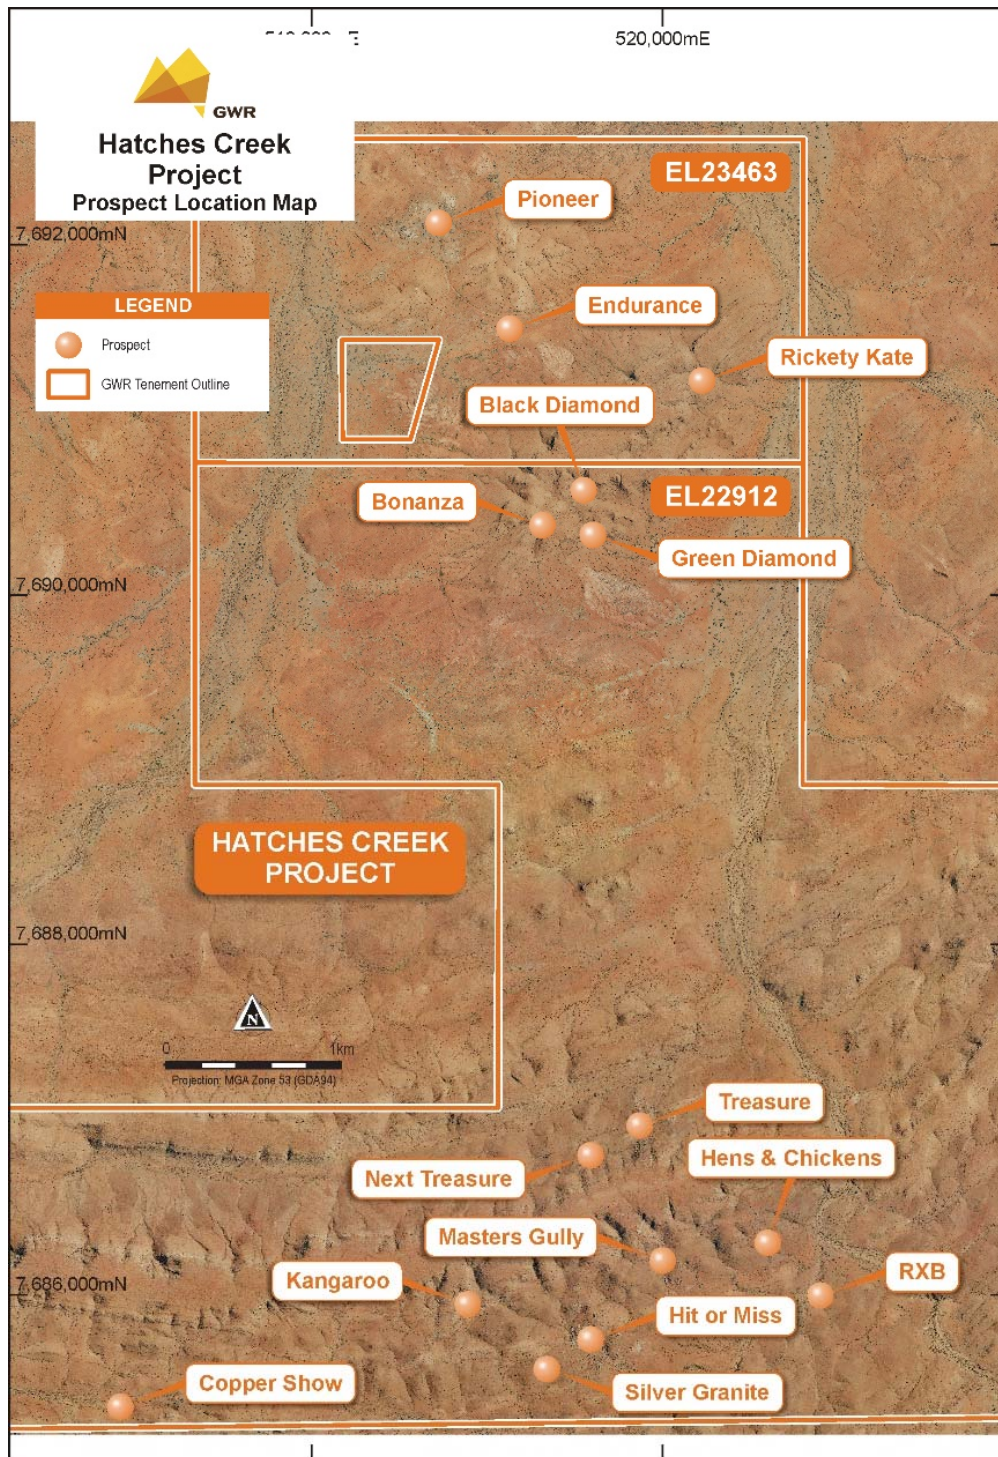


Figure 2: Hatches Creek Prospect Locations

Pioneer

The Pioneer mine is the largest historical mine in the Hatches Creek region. Records show that the mine was developed to a vertical depth of 63m (206') and consisted of up to 5 parallel lodes. The dumps and historical tailings contain a total Inferred Resource of 85,600 tonnes @ 0.66% WO₃ (upper cut of 1.5% WO₃ applied), refer to Arunta Resources Limited ASX release 23rd September 2014. Recent dump sampling by GWR also showed that the historical dumps contained anomalous to significant Au and Cu mineralisation (ASX release dated 27th October 2016).



Figure 3: Pioneer Mine

A total of 5 RC holes (HCRC001 to HCRC005) were drilled on two east-west orientated lines (Figure 4), with historical mine plans used to assist with targeting the previously recognised lodes.

HCRC001 to HCRC003 (Figure 5) were drilled on a line adjacent to the Macarthur Shaft (headframe in Figure 2) and HCRC004 and HCRC005 (Figure 6) were drilled adjacent to Cambells shaft.

Significant results are listed in Table 2 and all results are provided in Appendix 1. Intercepts include:

- **HCRC002, 1m @ 1.31% WO₃, 0.26g/t Au and 0.04% Cu, from 81m**
- **HCRC003, 1m @ 1.20% WO₃, 0.81g/t Au and 0.93% Cu, from 121m**
- **HCRC004, 1m @ 2.85% WO₃, 1.76g/t Au and 0.29% Cu, from 44m**

The drilling results confirm the polymetallic nature of the mineralisation with significant and at times co-incident WO₃, Au and Cu intercepts having been achieved.

As Figure 5 shows (518745E Cross Section), the drilling intersected four mineralised structures, which correspond to the previously recognised, #1, #2 and #12 lodes, plus an additional unnamed possibly unknown structure. Interestingly, the significant / anomalous Au and Cu mineralisation appears to be confined to the Pedlar Gabbro and absent in the quartzite. Importantly, all the targeted lodes contained significant WO₃ mineralisation.

Cross Section 518630E (Figure 6), shows that five mineralised structures were intersected, which appear to correspond with the previously recognised; #1 Lode, #5 Lode, Della Lode, #12 Lode and possibly Pink Lode. All significant WO₃ intercepts also contained anomalous or significant Au mineralisation. On this section, all of the targeted lodes contained significant WO₃ mineralisation.

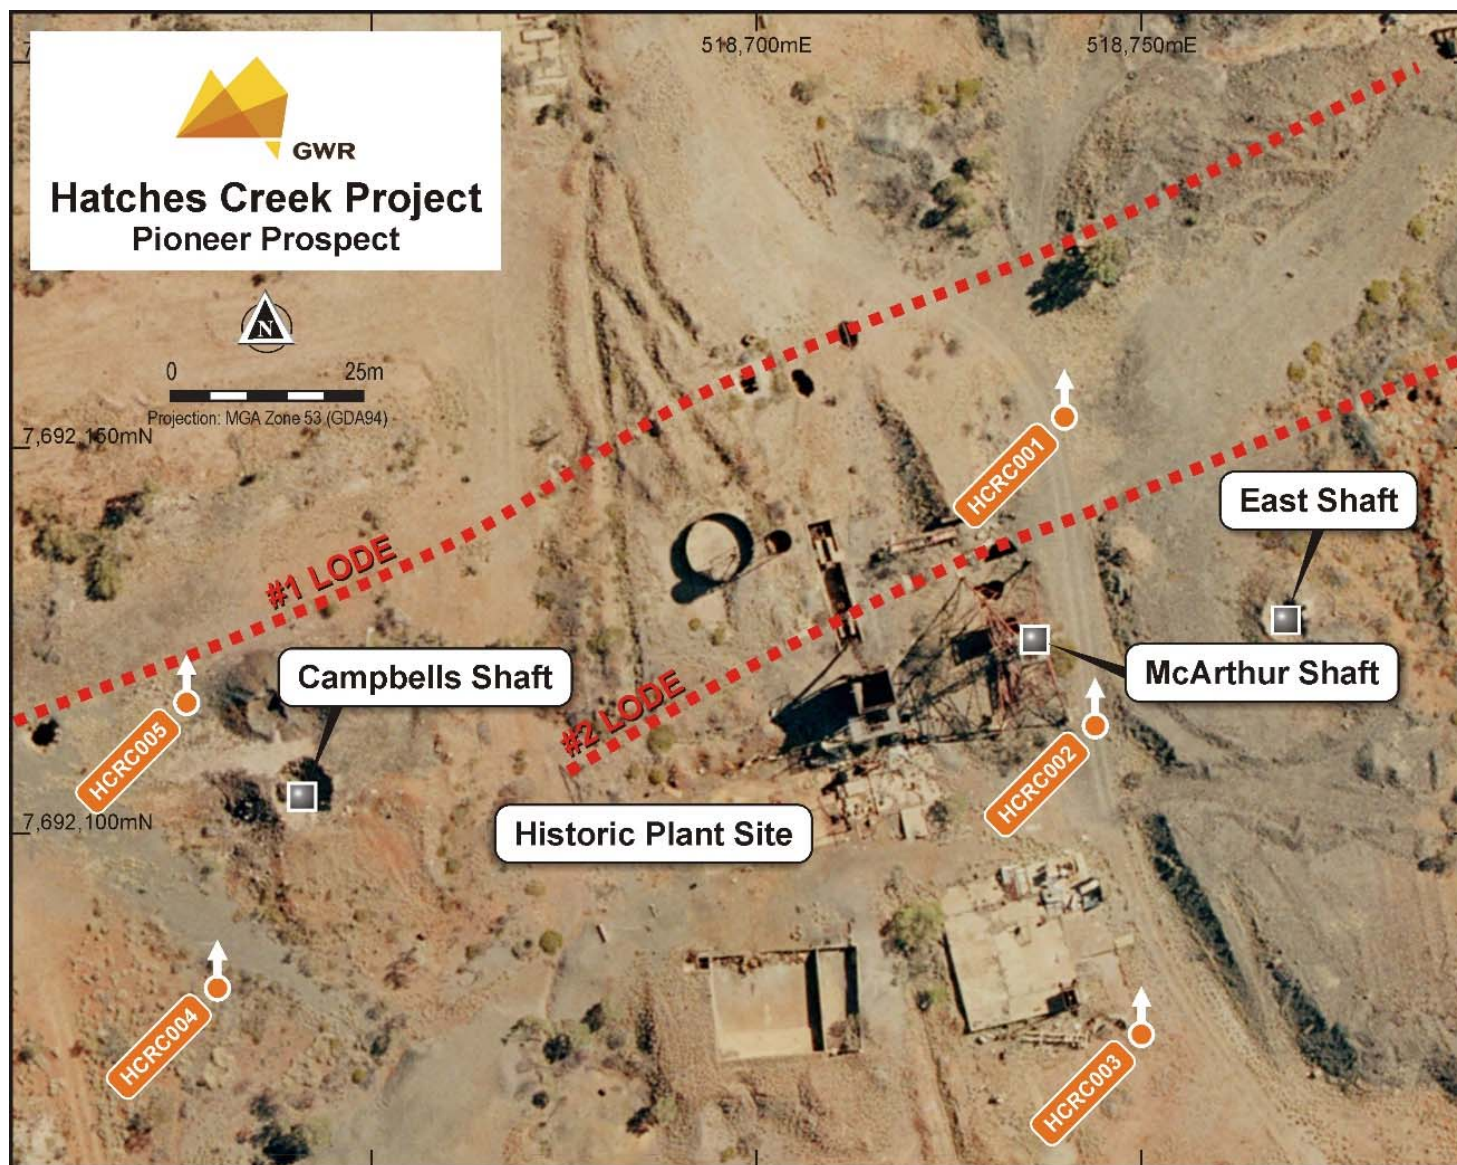


Figure 4: Pioneer Mine Drill Hole Collars

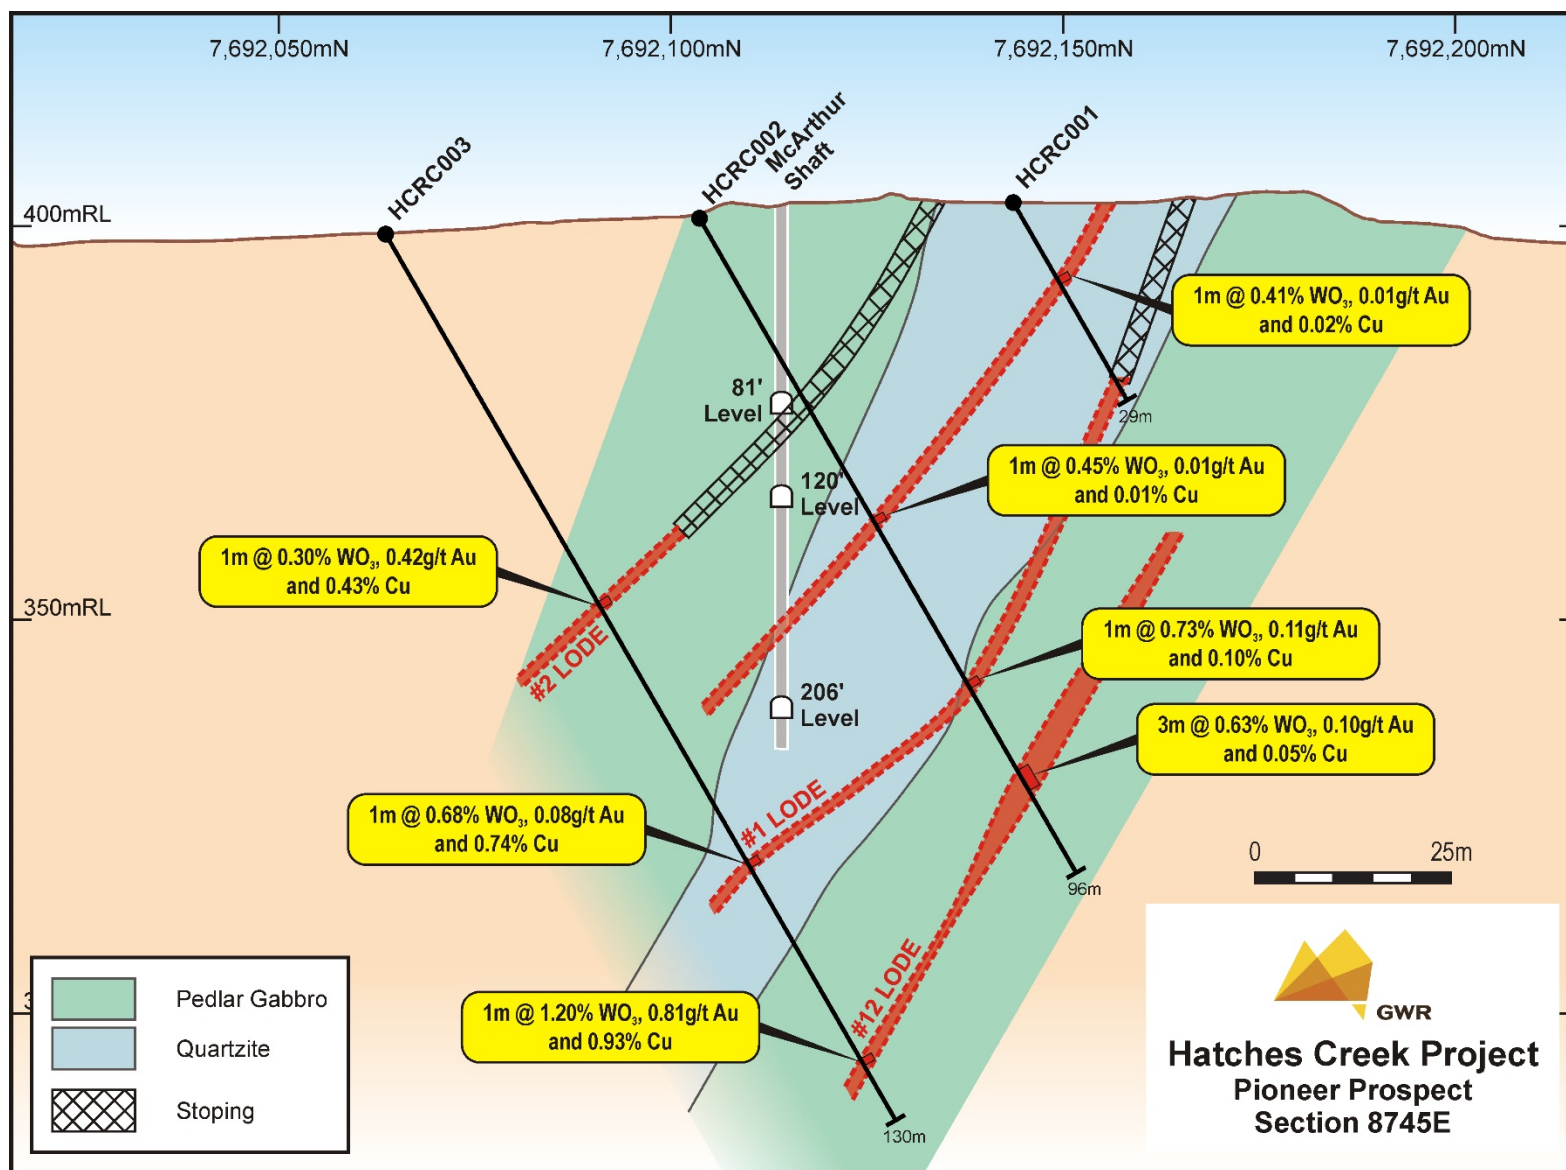


Figure 5: Pioneer Cross Section 518745E

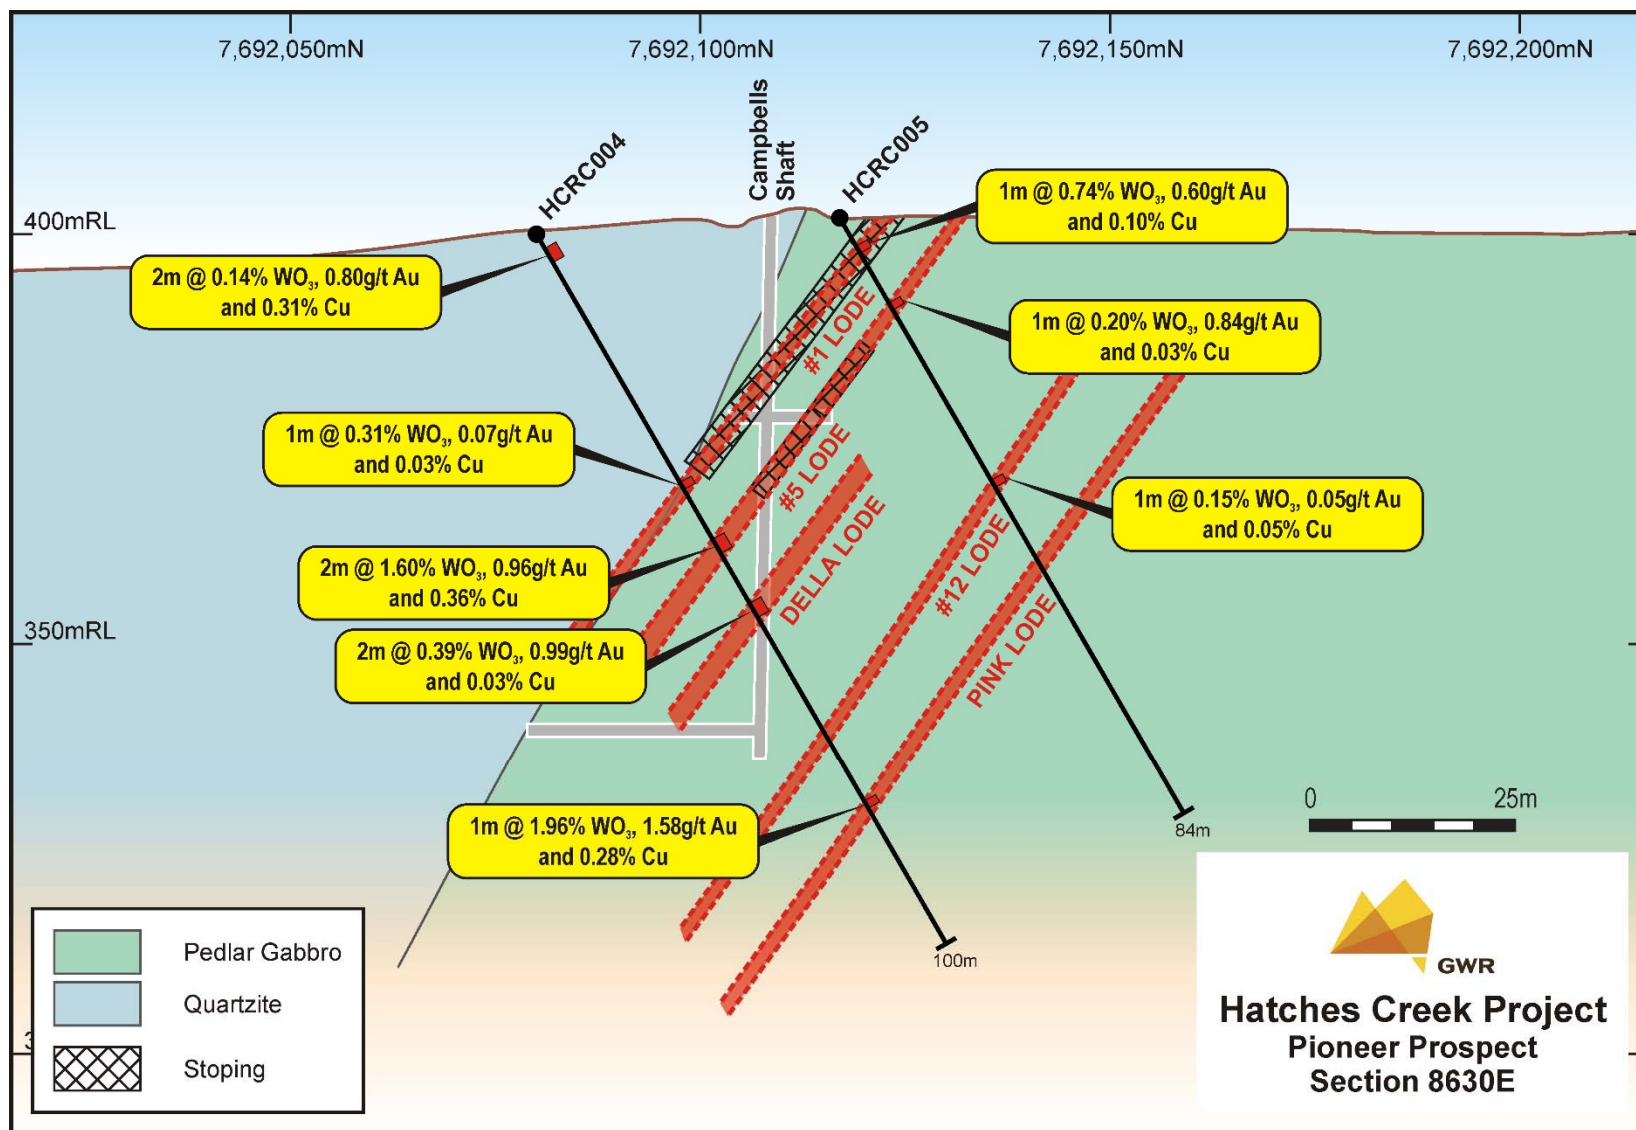


Figure 6: Pioneer Cross Section 518630E

Hit or Miss

The Hit or Miss Group historically contains the largest and most complex concentration of tungsten bearing veins at Hatches Creek. Historical mining activities have exposed multiple mineralised structures of varying orientations but dominantly north striking over an area of approximately 10 hectares (Figure 7). More than 30 individual mineralised structures have been identified by previous mining activities, which dominantly strike in a north to north-north east direction. However, there several east trending mineralised structures, suggesting significant potential for a quartz stockwork or sheeted vein style of mineralisation.

A total of 6 RC holes were completed on a single east-west orientated line with holes generally spaced at 40m intervals. The area drilled was selected because of topography and the presence of an existing track and not because of the density of potential mineralisation. The drilling was highly successful and identified 14 individual mineralised structures containing significant WO₃ mineralisation. Anomalous and significant Cu mineralisation was also identified and interestingly, this was sometimes independent of the WO₃ mineralisation. Lithology in this area strikes in an easterly direction and is subparallel to the drill traverse and all holes were dominantly within quartzites and some with minor shale. Historical accounts suggest that mineralisation is stronger within the felsic volcanics and these are the preferred host.

Significant results are listed in Table 2 and all results are provided in Appendix 1. Intercepts include:

- **HCRC010, 1m @ 8.68% WO₃, and 0.04% Cu, from 4m**
- **HCRC011, 36m @ 0.18% WO₃, and 0.24% Cu, from 52m**
- **HCRC012, 4m @ 0.06% WO₃ and 1.65% Cu, from 43m**
- **HCRC012, 5m @ 0.17% WO₃ and 0.76% Cu, from 71m**

As Figure 8 shows (Cross Section 70685740N), the RC drilling intersected 14 mineralised structures containing greater than 1m @ 0.1% WO₃. Importantly, five of these were nestled between the previously recognised # 1 Lode and # 2 Lode over an estimated true width of 20m. As shown in Figure 7, there is evidence to the north of the drill traverse that this mineralised zone between #1 and 2 Lodes persists along strike. The significant and anomalous Cu mineralisation intersected in most holes, sometimes independent of the WO₃, was unexpected and suggests that a powerful mineralising event has occurred. As Figure 7 also shows, the drilling to date has only tested approximately 50% of the potential width of the mineralised area.

The RC drilling program has demonstrated significant potential for a substantial WO₃ / Cu deposit and further drilling is planned to evaluate the 10 hectare area of potential mineralisation, especially within the felsic volcanic rocks that are considered even more prospective.

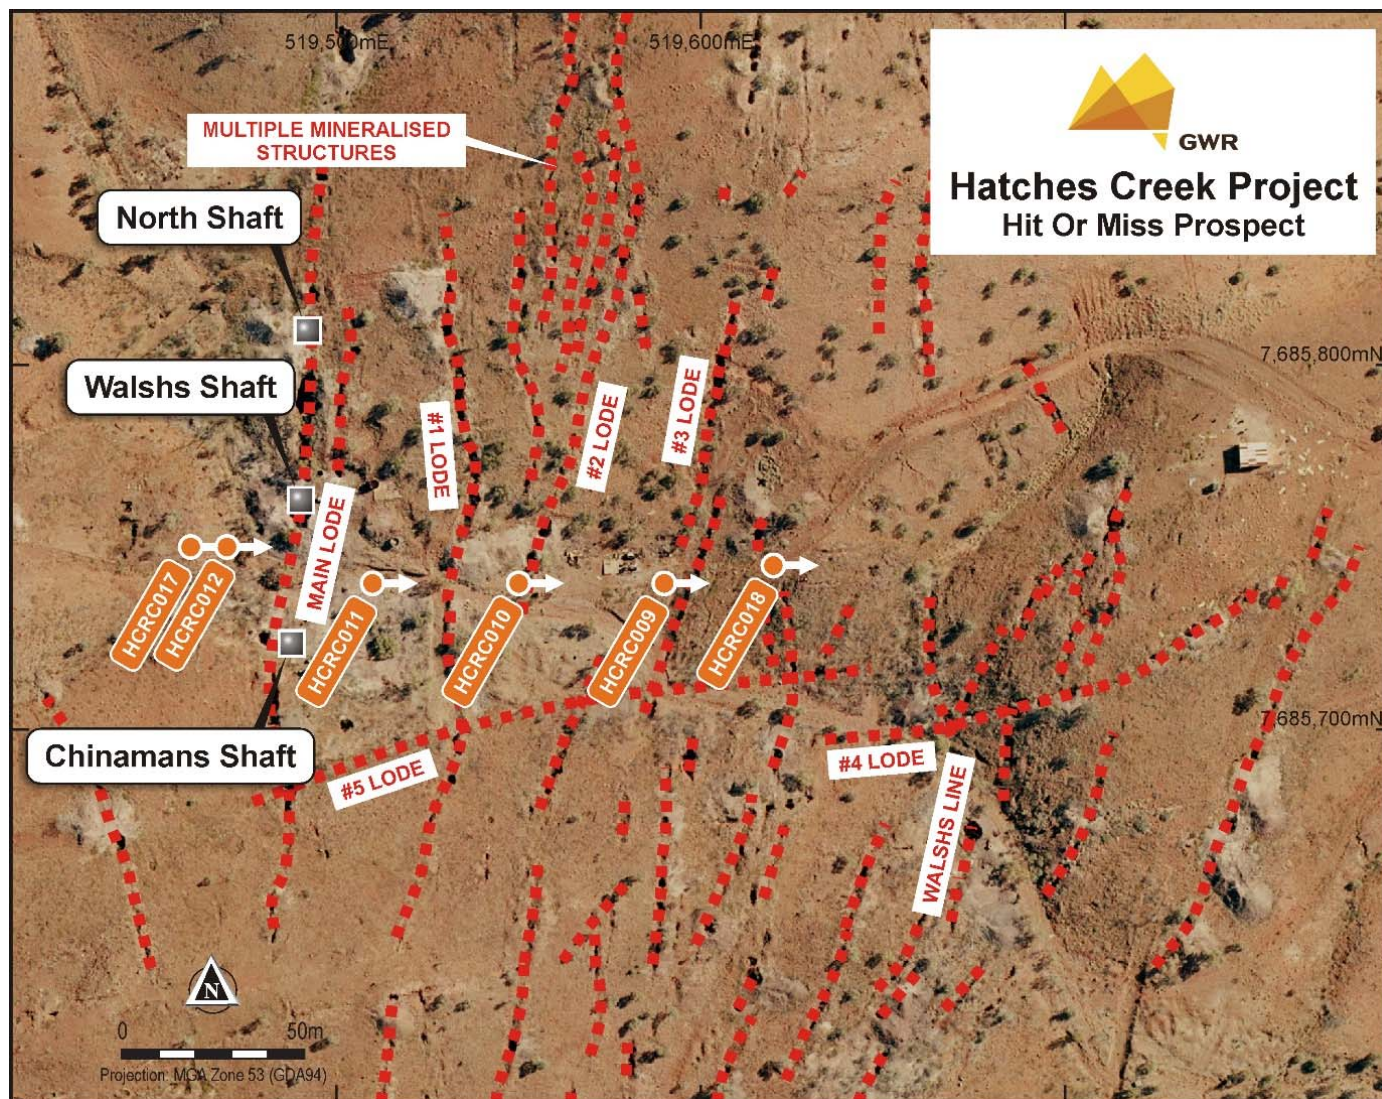


Figure 7; Hit or Miss Drill Hole Collars

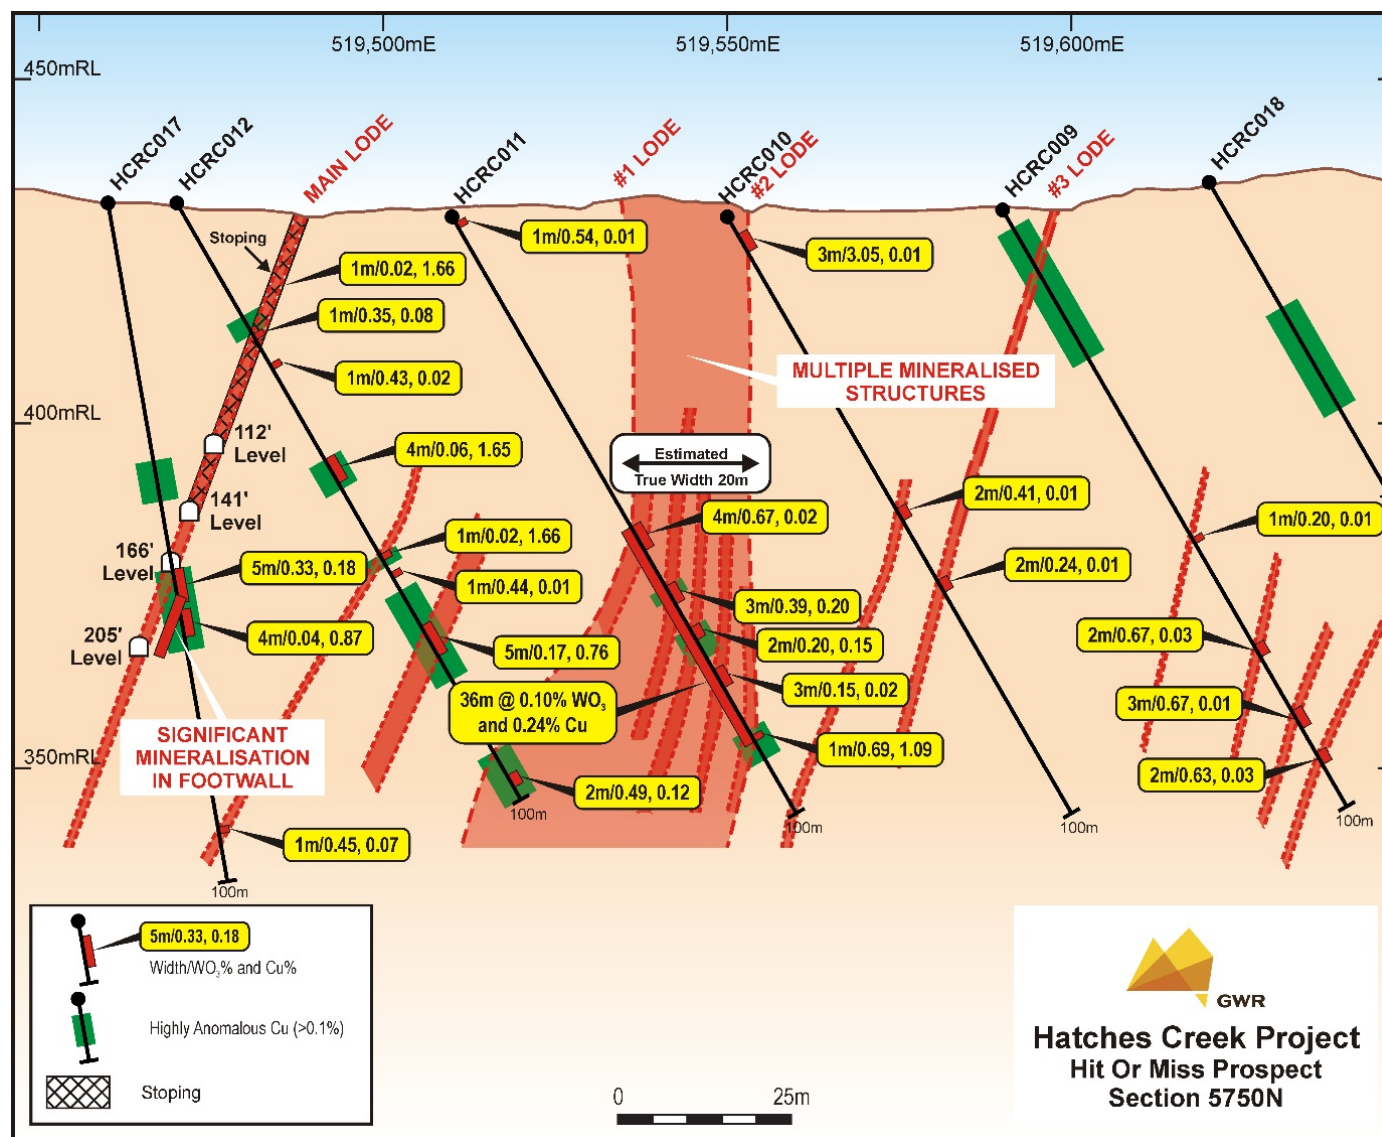


Figure 8; Hit or Miss Cross Section 7,685,750N

Treasure

The Treasure area contains substantial underground workings that rival the Pioneer in their length but not in depth. Treasure was the 3rd largest producer at Hatches Creek behind Pioneer and Hit or Miss (Figure 9).

A total of four RC holes were completed on two east–west orientated lines (768650N and 7687060N) as shown in Figure 9. As with Hit or Miss, the drill sites were selected partly because of accessibility and not necessarily prospectivity. The drilling was however highly successful and intersected broad zones of significant WO₃ mineralisation, which was often accompanied by significant to anomalous Cu mineralisation. All holes were within felsic volcanics and the mineralisation, based upon historical data, suggests that this is the preferred host in this location

Significant results are listed in Table 2 and all results are provided in Appendix 1. Intercepts include:

- **HCRC013, 44m @ 0.21% WO₃, and 0.12% Cu, from 55m**
- **HCRC013, 2m @ 1.27% WO₃, and 0.58% Cu, from 114m**
- **HCRC014, 53m @ 0.26% WO₃, and 0.13% Cu, from 63m**
- **HCRC014, 2m @ 1.72% WO₃, and 0.07% Cu, from 112m**
- **HCRC015, 11m @ 0.30% WO₃, and 0.02% Cu, from 21m**
- **HCRC016, 7m @ 0.73% WO₃, and 0.01% Cu, from 81m**
- **HCRC016, 3m @ 1.22% WO₃, and 0.05% Cu, from 126m**

On Cross Section 7686850N (Figure 10), multiple mineralised structures were intersected in HCRC013 and HCRC014, between the previously identified #2 and #3 lodes, containing unexpected significant and anomalous Cu mineralisation. The estimated true width of the mineralised zone is 25m, which is markedly different to the expected narrow high grade mineralisation. Outside of the above zone, two other mineralised structures were identified, meaning a total of six structures were intersected containing significant WO₃ mineralisation with grades of up to 2.87% WO₃ and up to 0.90% Cu.

On Cross Section 7687060N, HCRC015 and HCRC 016 intersected the targeted Main and #2 Lodes, with a combined estimated true width of 5 to 7m and grades of up to 3.54% WO₃, plus an additional three mineralised structures. Interestingly, the mineralisation contained no anomalous Cu.

The RC drilling at Treasure, especially on line 7686850, has intersected broad widths of significant mineralisation over estimated true widths of up to 25m. Based upon historical records and mine workings, the potential strike length is 400 to 500m. As such, the potential for this area to host a significant WO₃ / Cu deposit is considered to be high.

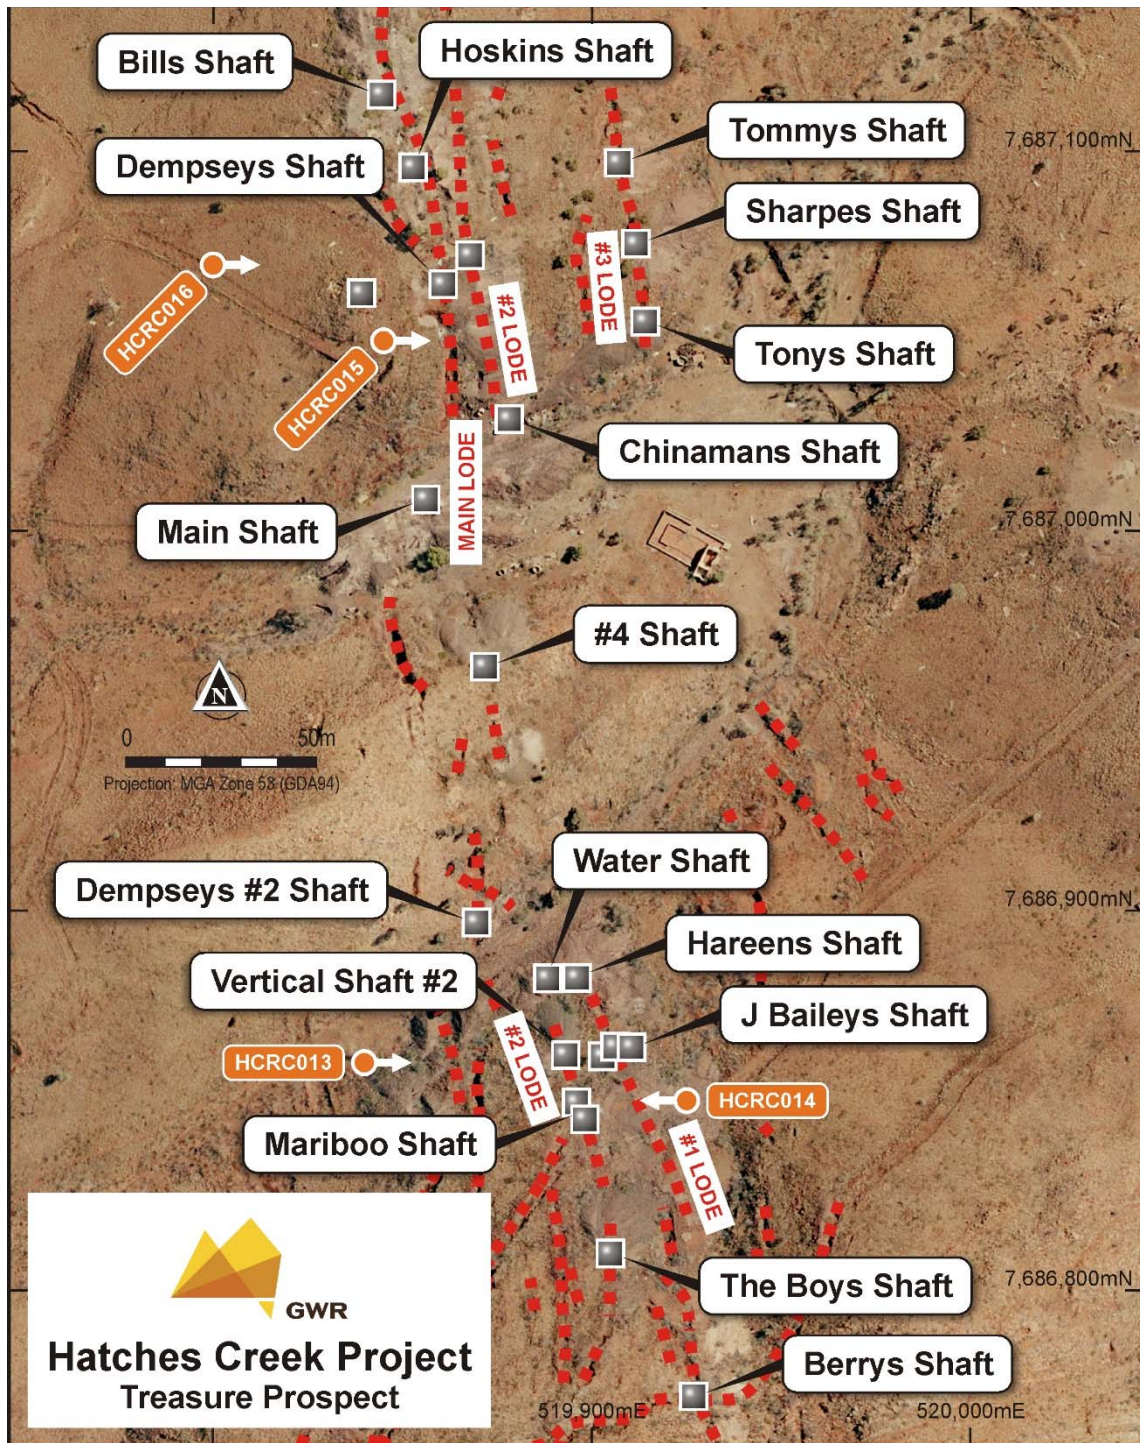


Figure 9; Treasure Drill Hole Collars

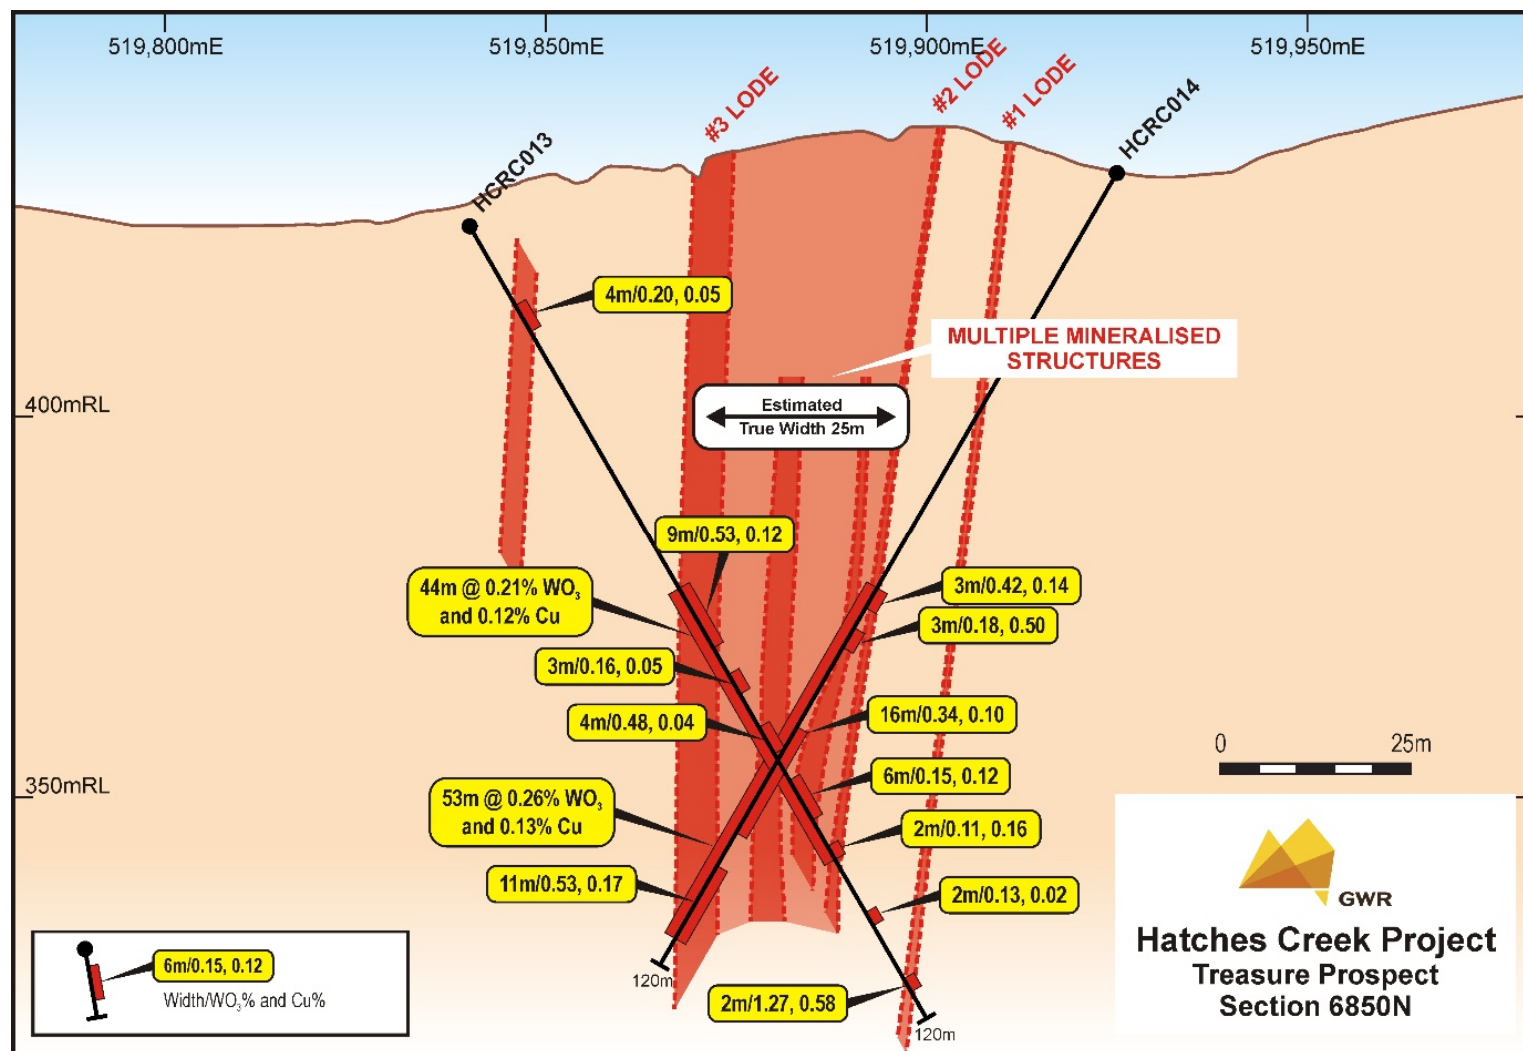


Figure 10; Treasure Cross Section 7,686,850N

Copper Show

Copper Show is located in the south west corner of the project area approximately 2.6km west south west of Hit or Miss (Figure 2). Historical mine workings exist over a strike length of approximately 120m and strike in an east-north east direction. According to historical records, the ore in this location is complex and contains wolframite, scheelite, and as the name suggests, substantial copper. Recent dump sampling by GWR (ASX release 27th October 2016) confirms WO₃ grades of between 1% and 3.5% with Cu ranging from 1 to 3.7%.

A total of three RC holes (HCRC006 to 8) were drilled on a single north–south orientated line on 516950E. The results compared to the other areas were disappointing, with only 4 significant intercepts achieved, the best being HCRC006, 1m at 0.58% WO₃ and 0.54% Cu. Based upon the substantial mineralisation evident from the historical mine workings and dumps, it is possible that the recent drilling has missed the target. Further work is planned to investigate this.

Metallurgical Test work and Recent Crushing and Ore Sorting Test work

Substantial metallurgical test work as part of the dumps project has already been undertaken over the project area with positive results (refer to announcement 19th January 2015, March 2015 Quarterly Report and June 2015 Quarterly Report).

Crushing and ore sorting testwork was recently undertaken on bulk samples previously collected from Pioneer and Hit or Miss. A 203kg sample of Hit or Miss (0.3% WO₃) and 213kg sample of Pioneer (0.4% WO₃) were chosen, crushed to p100 -40mm and screened at 20mm. The -40mm+20mm material was bagged and shipped to Tomra Ore Sorting Technology in NSW and the -20mm material remained at Nagrom.

For the Pioneer waste dump composite, 52% of the mass deported to the +20mm portion and for the Hit or Miss dump composite, 44% of the mass deported to the +20mm portion. In both samples, there is a significant %WO₃ grade differential between the +20 and -20mm fraction, in particular for the Pioneer dump where the +20mm size fraction assayed 0.04% WO₃ vs the -20mm size fraction that assayed 0.60% WO₃.

For the Pioneer sample, 97% of the contained WO₃ and 66% of the feed mass deports to the -20mm size fraction. The grade of the -20mm fraction has increased from 0.41 to 0.60% WO₃. Although only 3% of the contained WO₃ deported to the ore sorter feed, the ore sorter was effective in increasing the grade from 0.04% in the feed to 0.11% WO₃ in the “accepts” portion whilst recovering 95% of the WO₃. Overall WO₃ recovery in the circuit was 99.9% with 22% of the mass removed as waste.

For the Hit or Miss sample, 81% of the contained WO₃ and 69% of the feed mass deports to the -20mm size fraction and 19% of the contained WO₃ has deported to the ore sorter feed. The ore sorter has been effective in increasing the WO₃ grade from 0.17% in the feed to 0.68% in the “accepts” portion whilst recovering 89% of the WO₃. Overall WO₃ recovery in the circuit was 98% with 24% of the mass removed as waste.

Planned Work Future Program

The recent RC program tested four target areas and a further 11 targets remain. GWR has an approved Environmental Management and Monitoring Plan (EMMP) from both the NT Mines Department and Work Program from Central Land Council (CLC) to also drill at the Black Diamond, Copper Show, Bonanza, Hens and Chicken, Masters Gully and Kangaroo Group target areas. Based upon the highly

successful results to date, testing these targets is more than justified and GWR plans to undertake this as soon as practicably possible.

It is planned to also submit an EMMP to the NT Mines Department and CLC to test possible strike extensions to the mineralisation already identified and to also test additional target areas.

For further information:

Craig Ferrier
Chief Executive Officer
Ph: +61 8 9322 6666
E: craigf@gwrgroup.com.au

For Broker and Media Enquiries:

Andrew Rowell
Cannings Purple
Ph: +61 400 466 226
E: arowell@canningspurple.com.au

Competent Persons Statement

The information in this report which relates to Exploration Targets, Exploration Results and Mineral Resources or Ore Reserves is based on information compiled by Mr Allen Maynard, who is a Member of the Australian Institute of Geosciences ("AIG"), a Corporate Member of the Australasian Institute of Mining & Metallurgy ("AusIMM") and independent consultant to the Company. Mr Maynard is the Director and principal geologist of Al Maynard & Associates Pty Ltd and has over 35 continuous years of exploration and mining experience in a variety of mineral deposit styles. Mr Maynard has sufficient experience which is relevant to the style of mineralisation and type of deposit under consideration and to the activity which he is undertaking to qualify as a Competent Person as defined in the 2012 Edition of the "Australasian Code for reporting of Exploration Results, Exploration Targets, Mineral Resources and Ore Reserves".(JORC Code). Mr Maynard consents to inclusion in the report of the matters based on this information in the form and context in which it appears.

Details concerning the JORC-2012 Resource Estimate for the Hatches Creek Tungsten Project (including table 1 report) and referred to in this announcement are set out in the ASX announcement of Arunta Resources Ltd dated 23 September 2014

Table 2
Significant RC Drill Hole Intercepts

Prospect	Hole#	East (MGA 94)	North (MGA 94)	Dip/Azi	From (m)	To (m)	Interval (m)	WO3 (%)	Au (g/t)	Cu (%)
Pioneer	HCRC001	518740	7692154	-60 / 360	8	9	1	0.1	0.06	0.01
					12	13	1	0.41	0.01	0.08
Pioneer	HCRC002	518744	7692114	-60 / 360	44	45	1	0.45	0.01	0.01
					68	69	1	0.73	0.11	0.10
					76	77	1	0.16	0.50	0.26
					81	84	3	0.63	0.10	0.05
			INCL		81	82	1	1.31	0.26	0.04
			EOH		95	96	1	0.25	0.02	0.04
Pioneer	HCRC003	518750	7692074	-60 / 360	38	39	1	0.11	0.05	0.21
					54	55	1	0.30	0.42	0.43
					92	93	1	0.68	0.08	0.74
					97	98	1	0.00	2.26	0.01
					107	108	1	0.19	0.02	0.08
					118	119	1	0.16	0.01	0.01
					121	122	1	1.20	0.81	0.93
					128	129	1	0.11	0.03	0.25
Pioneer	HCRC004	518630	7692080	-60 / 360	0	1	1	0.14	0.10	0.06
					2	4	2	0.14	0.80	0.31
			INCL		3	4	1	0.14	1.33	0.29
					35	36	1	0.31	0.07	0.03
					43	45	2	1.60	0.96	0.36
			INCL		44	45	1	2.85	1.76	0.29
					48	49	1	0.44	0.19	0.02
					52	54	2	0.39	0.99	0.03
			INCL		53	54	1	0.42	1.96	0.04
					70	71	1	0.23	0.06	0.28
					72	74	2	0.16	0.01	0.31
					80	81	1	1.96	1.58	0.28
					93	94	1	0.12	0.01	0.01
					95	96	1	0.12	0.01	0.03
Pioneer	HCRC005	518626	7692117	-60 / 360	4	5	1	0.74	0.60	0.10
					12	13	1	0.20	0.84	0.03
					37	38	1	0.15	0.05	0.05
Copper Show	HCRC006	516950	7685380	-60 / 180	0	1	1	0.49		0.12
					3	4	1	0.58		0.54
Copper Show	HCRC007	516950	7685400	-60 / 180	20	21	1	0.17		0.07
					26	27	1	0.17		0.13
Hit or Miss	HCRC009	519590	7685740	-60 / 090	55	56	1	0.20		0.01
					73	75	2	0.66		0.03
			INCL		73	74	1	1.19		0.00
		0.05% LOWER CUT OFF			84	93	9	0.39		0.02

Prospect	Hole#	East (MGA 94)	North (MGA 94)	Dip/Azi	From (m)	To (m)	Interval (m)	WO3 (%)	Au (g/t)	Cu (%)
					84	87	3	0.67		0.01
			INCL		84	85	1	1.71		0.01
					91	93	2	0.63		0.03
					97	98	1	0.26		0.00
Hit or Miss	HCRC010	518550	7685740	-60 / 090	0	1	1	0.12		0.01
					3	5	2	3.05		0.02
			INCL		4	5	1	8.68		0.04
					16	17	1	0.11		0.04
					41	42	1	0.15		0.04
					49	51	2	0.41		0.01
					61	63	2	0.24		0.01
Hit or Miss	HCRC011	519510	7685740	-60 / 090	1	2	1	0.54		0.01
					37	38	1	0.11		0.03
					43	44	1	0.19		0.01
			MINERALISED ZONE		52	88	36	0.18		0.24
					52	56	4	0.67		0.02
			INCL		55	56	1	1.39		0.02
					62	65	3	0.39		0.20
					67	68	1	0.12		0.08
					69	71	2	0.20		0.15
					71	72	1	0.09		0.73
					73	74	1	0.07		3.30
					76	77	1	0.24		0.03
					78	79	1	0.20		0.02
					86	87	1	0.04		1.62
					87	88	1	0.69		1.09
					99	100	1	0.04		0.53
Hit or Miss	HCRC012	519470	7685750	-60 / 090	22	23	1	0.35		0.08
					27	28	1	0.43		0.02
					41	42	1	0.11		0.09
					43	47	4	0.06		1.65
					59	60	1	0.02		1.66
					62	63	1	0.44		0.01
					71	76	5	0.17		0.76
					72	73	1	0.22		0.92
					74	76	2	0.29		0.54
					96	98	2	0.49		0.12
Treasure	HCRC013	519840	7686860	-60 / 090	8	9	1	0.12		0.03
					12	16	4	0.20		0.05
			MINERALISED ZONE		55	99	44	0.21		0.12
					55	64	9	0.22		0.03
			INCL		58	59	1	2.87		0.08
					68	71	3	0.16		0.05
					76	80	4	0.48		0.04
					84	90	6	0.15		0.12

Prospect	Hole#	East (MGA 94)	North (MGA 94)	Dip/Azi	From (m)	To (m)	Interval (m)	WO3 (%)	Au (g/t)	Cu (%)
					94	96	2	0.11		0.16
					98	99	1	0.24		0.27
					104	106	2	0.13		0.01
					111	112	1	0.15		0.01
					114	116	2	1.27		0.58
			INCL		114	115	1	1.98		0.38
Treasure	HCRC014	519925	7686850	-60 / 270	1	4	3	0.13		0.03
					29	30	1	0.13		0.05
					36	37	1	0.50		0.11
					41	42	1	0.14		0.01
			MINERALISED ZONE		63	116	53	0.26		0.13
					63	66	3	0.42		0.14
					69	74	5	0.14		0.37
			INCL		69	70	1	0.15		0.90
			INCL		92	93	1	1.51		0.08
					105	116	11	0.53		0.17
			INCL		112	114	2	1.72		0.07
Treasure	HCRC015	519845	7687050	-60 / 090	21	27	6	0.14		0.02
					29	32	3	0.81		0.01
				INCL	30	31	1	1.35		0.01
					21	32	11	0.30		0.02
Treasure	HCRC016	519800	7687070	-60 / 090	70	71	1	0.31		0.01
					81	88	7	0.73		0.01
				INCL	82	83	1	1.26		0.01
				INCL	86	87	1	3.54		0.01
					126	129	3	1.22		0.05
				INCL	127	128	1	3.15		0.05
					131	132	1	0.22		0.01
					139	140	1	0.35		0.08
					143	144	1	0.39		0.00
Hit or Miss	HCRC017	519460	7685750	-80 / 090	6	7	1	0.74		0.25
					54	59	5	0.33		0.18
					60	64	4	0.04		0.87
					61	62	1	0.04		1.41
					73	74	1	0.14		0.05
					86	87	1	0.14		0.01
					92	93	1	0.45		0.07
Hit or Miss	HCRC018	519620	7685745	-60 / 090	65	67	2	0.57		0.08
					76	77	1	0.11		0.01
					78	79	1	0.12		0.05

APPENDIX 1
JORC 2012 TABLE 1

JORC 2012 TABLE 1

SECTION 1: SAMPLING TECHNIQUES AND DATA

Criteria	JORC Code explanation	Commentary
Sampling techniques	<i>Nature and quality of sampling (e.g. cut channels, random chips, or specific specialised industry standard measurement tools appropriate to the minerals under investigation, such as down hole gamma sondes, or handheld XRF instruments, etc.). These examples should not be taken as limiting the broad meaning of sampling.</i>	The Pioneer, Copper Show, Hit or Miss and Treasure prospect areas at the Hatches Creek project were sampled using Reverse Circulation ("RC") drilling. A total of 18 holes for an aggregate of 1739m was completed.
	<i>Include reference to measures taken to ensure sample representivity and the appropriate calibration of any measurement tools or systems used</i>	<p>The drill holes were located to intersect the mineralisation at representative points to help with the overall understanding of the geology and distribution of the mineralisation.</p> <p>All the sample recoveries were visually estimated and logged as they were collected and all the samples were consistently logged as approximately 100%.</p> <p>All the drill samples as well as QAQC samples including duplicates and Certified Standards were submitted to an independent, ISO certified laboratory for chemical analysis.</p> <p>No measurement tools or systems were used that required calibration.</p>
	<i>Aspects of the determination of mineralisation that are Material to the Public Report. In cases where 'industry standard' work has been done this would be relatively simple (e.g. 'reverse circulation drilling was used to obtain 1 m samples from which 3 kg was pulverised to produce a 30 g charge for fire assay'). In other cases more explanation may be required, such as where there is coarse gold that has inherent sampling problems. Unusual commodities or mineralisation types (e.g. submarine nodules) may warrant disclosure of detailed information</i>	<p>Samples were collected at 1m intervals using cyclone and passed through a cone splitter. Duplicate (A and B sample) sub samples were collected of approximately 2 to 4kg in pre-numbered and barcoded calico sample bags and the residue stored in a plastic bag. The A calico bag sample was submitted to Nagrom Laboratories in Perth where the following was carried out;</p> <ul style="list-style-type: none"> • Dried and pulverized • WO3, Sn, Fe2O3, MnO, SiO2, Al2O3, TiO2, CaO, MgO, As, P, S, Mo, Cu, Bi and Sb were all analysed using the Nagrom XRF008 technique with a lower detection limit of 0.001% • At the Pioneer prospect Au was also analysed by fire assay with a lower detection limit of 0.01 ppm
Drilling techniques	<i>Drill type (e.g. core, reverse circulation, open-hole hammer, rotary air blast, auger, Bangka, sonic, etc) and details (e.g. core diameter, triple or standard tube, depth of diamond tails, face-sampling bit or other type, whether core is oriented and if so, by what method, etc).</i>	A total of 18 RC holes for an aggregate of 1739m was completed at depths ranging from 29 to 150m, averaging 97m. All of the drilling was undertaken using a 146mm face sampling RC hammer
Drill sample recovery	<i>Method of recording and assessing core and chip sample recoveries and results assessed</i>	The sample recovery was visually assessed and recorded on drill logs and is considered to be acceptable.

Criteria	JORC Code explanation	Commentary
	<i>Measures taken to maximise sample recovery and ensure representative nature of the samples</i>	The samples were visually checked for recovery, moisture and contamination. A cyclone and cone splitter were utilised to provide a representative sample and were regularly cleaned. The drilling contractor blew out the hole at the beginning of each rod to remove any water.
	<i>Whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.</i>	The ground conditions were good and the drilling returned consistent sized dry samples and the possibility of sample bias through selective recoveries is considered negligible.
Logging	<i>Whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, mining studies and metallurgical studies.</i>	All samples were geologically logged with lithology and mineralisation recorded. This logging was of sufficient detail to support the findings of this report and, after further drilling is completed, included in later Mineral Resource estimation.
	<i>Whether logging is qualitative or quantitative in nature. Core (or costean, channel, etc) photography.</i>	The drill sample logging was qualitative.
	<i>The total length and percentage of the relevant intersections logged</i>	All the drill samples were logged.
Sub-sampling techniques and sample preparation	<i>If core, whether cut or sawn and whether quarter, half or all core taken.</i>	This section is not applicable as there were no core samples collected.
	<i>If non-core, whether riffled, tube sampled, rotary split, etc and whether sampled wet or dry.</i>	The RC drilling chip samples were collected using a cyclone and then duplicate sub samples of 2kg to 4kg in size collected using a cone splitter attached to the cyclone. All samples were dry.
	<i>For all sample types, the nature, quality and appropriateness of the sample preparation technique.</i>	<p>Samples were submitted to Nagrom Laboratories in Perth where the following sample preparation procedures were carried out;</p> <ul style="list-style-type: none"> • The sample was dried and crushed to -6.3mm using a jaw crusher • Samples in excess of 2kg are riffle split • The crushed sample is pulverized to 95% passing 75 micron <p>These sample preparation procedures followed by the laboratory meet industry standards and are appropriate for the sample type and mineralisation being analysed.</p>
	<i>Quality control procedures adopted for all sub-sampling stages to maximise representivity of samples.</i>	Certified Standards and duplicate samples were routinely inserted into the sample sequences submitted for chemical analysis according to GWR Group Limited ("GWR") QAQC procedures. Results from the QAQC were found to be acceptable. Nagrom Laboratories also carried out internal QAQC as per their operating procedures
	<i>Measures taken to ensure that the sampling is representative of the in situ material collected, including for instance results for field duplicate/second-half sampling.</i>	Field duplicates of the drilling samples were routinely collected and these were all found to agree within acceptable limits with the original samples.
	<i>Whether sample sizes are appropriate to the grain size of the material being sampled.</i>	The sample size is considered appropriate to the grain size of the material being sampled.

Criteria	JORC Code explanation	Commentary
Quality of assay data and laboratory tests	<i>The nature, quality and appropriateness of the assaying and laboratory procedures used and whether the technique is considered partial or total.</i>	<p>XRF has proven to be a very accurate analytical technique for a wide range of base metals, trace elements and major constituents found in rocks and mineral materials. Glass fusion XRF is utilised for assaying, since it provides good accuracy and precision; it is suitable for analysis from very low levels up to very high levels.</p> <p>ICP and Fire Assay techniques are also considered appropriate and industry standard for the elements analysed using this technique and the detection limits as stated.</p> <p>The assaying techniques used are total analyses.</p>
	<i>For geophysical tools, spectrometers, handheld XRF instruments, etc, the parameters used in determining the analysis including instrument make and model, reading times, calibrations factors applied and their derivation, etc.</i>	Since this equipment was not used, this section is not applicable.
	<i>Nature of quality control procedures adopted (e.g. standards, blanks, duplicates, external laboratory checks) and whether acceptable levels of accuracy (i.e. lack of bias) and precision have been established.</i>	<p>Certified Standards and duplicate samples were routinely inserted into the sample sequences submitted for chemical analysis according to GWR Group Limited ("GWR") QAQC procedures. Results from the QAQC indicate that the assays met acceptable levels of accuracy without significant bias. Nagrom Laboratories also carried out internal QAQC as per their operating procedures.</p> <p>No blanks were used for QAQC checking. The risk of contamination during sample preparation was considered minimal because of the mineralogy of the samples being tested.</p> <p>At this early stage of the exploration program no external laboratory checks have been undertaken.</p>
Verification of sampling and assaying	<i>The verification of significant intersections by either independent or alternative company personnel.</i>	Brian Varndell of Al Maynard and Associates, who are consultants to GWR, has checked and verified the data pertaining to the significant intercepts against original field logs, laboratory certificates and by checking cross sections.
	<i>The use of twinned holes.</i>	At this early stage of the exploration program no twin holes have been drilled.
	<i>Documentation of primary data, data entry procedures, data verification, data storage (physical and electronic) protocols.</i>	All field data is recorded on log sheets as per GWR operating procedures. Drill data is entered into a digital database and is also stored in hard copy in Perth office. The digital data was checked against the field logs by the geologist after the data entry was completed and also checked visually on cross sections.
	<i>Discuss any adjustment to assay data.</i>	No adjustments to the assay data were made.
Location of data points	<i>Accuracy and quality of surveys used to locate drillholes (collar and down-hole surveys), trenches, mine workings and other locations used in Mineral Resource estimation.</i>	<p>The RC drill hole collar northings and eastings were surveyed using a hand held GPS while the RLs were determined from contours generated by high quality photogrammetry.</p> <p>A down hole survey measurement was taken at the bottom of each hole.</p>
	<i>Specification of the grid system used.</i>	The grid system is MGA GDA94 Zone 53.

Criteria	JORC Code explanation	Commentary
	<i>Quality and adequacy of topographic control.</i>	High resolution aerial photogrammetry was collected using an unmanned aerial vehicle (UAV) survey undertaken in August 2015 with an accuracy of +/-40mm in all 3 dimensions.
Data spacing and distribution	<i>Data spacing for reporting of Exploration Results.</i>	The drilling is of a first pass nature to test the overall geology and indicative style and extent of the mineralisation only.
	<i>Whether the data spacing and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the Mineral Resource and Ore Reserve estimation procedure(s) and classifications applied.</i>	No resource estimation was undertaken using the drilling data so this section is not applicable
	<i>Whether sample compositing has been applied.</i>	Only 1m RC drill samples were collected and no sample compositing was undertaken.
Orientation of data in relation to geological structure	<i>Whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the deposit type.</i>	The drilling was designed to intersect mineralisation approximately perpendicular to the mineralisation and not biased towards any special grade areas. However since the orientation of the mineralisation has not been determined accurately at this early stage, the intersection widths may be appreciably longer than the true width of the mineralisation intersected and some mineralised structures intersected at sub-optimal angles.
	<i>If the relationship between the drilling orientation and the orientation of key mineralised structures is considered to have introduced a sampling bias, this should be assessed and reported if material.</i>	Since the drilling to date has been exploratory and not at a sufficient density to properly determine the orientation and grade of the mineralisation, it cannot be determined at this early stage if the orientation of the drilling has introduced a sampling bias. But the knowledge of the mineralisation gained so far from surface mapping and drilling indicates that the drilling has been properly oriented to test the mineralisation without undue bias.
Sample security	<i>The measures taken to ensure sample security.</i>	Samples were collected in calico sample bags, then placed in a polyweave bag and the bag sealed with a cable tie. The individual bags were then placed in a Bulka Bag and this bag was sealed with rope. The bulka bags were transported by trucking contractors to Nagrom Laboratories in Perth.
Audits or reviews	<i>The results of any audits or reviews of sampling techniques and data.</i>	<p>Since the exploration program is only at an early stage there have been no audits or reviews of the sampling techniques. It is believed by GWR that the sampling procedures and techniques followed meet current international standards of quality.</p> <p>Independent geological consultants, Al Maynard & Associates, have audited all the drilling data collected to date.</p>

\$

SECTION 2: REPORTING OF EXPLORATION RESULTS

Criteria	JORC Code explanation	Commentary
Mineral tenement and land tenure status	<p>Type, reference name/number, location and ownership including agreements or material issues with third parties such as joint ventures, partnerships, overriding royalties, native title interests, historical sites, wilderness or national park and environmental settings.</p>	<p>The Hatches Creek project is located in the Northern Territory of Australia upon EL22912 and EL23463 covering a total area of approximately 31.8 km²</p> <p>The registered holder of the tenements is NT Tungsten Pty Ltd, which is a 100% owned subsidiary of GWR Group Limited.</p> <p>The tenements are located upon Aboriginal Freehold Land, which is owned by the Anurrete Aboriginal Trust and administered by the Central Land Council (CLC), with whom a Deed of Exploration has been executed</p> <p>NT Tungsten holds a 100% interest in the tenements and a 1.5% net smelter royalty is payable to Davenport Resources Limited.</p>
	<p>The security of the tenure held at the time of reporting along with any known impediments to obtaining a licence to operate in the area.</p>	<p>The tenements are in good standing.</p>
Exploration done by other parties	<p>Acknowledgment and appraisal of exploration by other parties.</p>	<p>Previous mining activities up to 1960 are well documented and are summarised in Bulletin No 6 “The Geology and Mineral Resources of the Hatches Creek Wolfram Field, Northern Territory”, G. R Ryan 1961.</p> <p>Between 2008 and 2015 the ground was held by numerous companies associated with Davenport Resources Limited and Arunta Resources Limited. Their activities focused on sampling and mapping of the historical mine workings.</p>
Geology	<p>Deposit type, geological setting and style of mineralisation.</p>	<p>Tungsten mineralisation at Hatches Creek is associated with quartz veins in shear zones within a variety of Proterozoic host rocks forming part of the Davenport Province. Wolframite and Scheelite are the dominant tungsten minerals present</p>
Drill hole Information	<p>A summary of all information material to the understanding of the exploration results including a tabulation of the following information for all Material drill holes:</p> <ul style="list-style-type: none"> • easting and northing of the drill hole collar • elevation or RL (Reduced Level – elevation above sea level in metres) of the drill hole collar • dip and azimuth of the hole • down hole length and interception depth • hole length. 	<p>All relevant data for GWR’s RC drilling is summarised in Tables 1 and 2 in the body of the report and all assay data in Appendix 2</p>

Criteria	JORC Code explanation	Commentary
Data aggregation methods		<p>Significant Intercept Significant WO3 intersections are reported for all intervals greater than 1m at 0.1% WO3 or greater than 2m at 0.1% WO3 and up to 2m of internal waste.</p> <p>Significant Cu intersections are reported for all intervals greater than 1m at 0.5% Cu.</p> <p>Significant Au intercepts are reported for all intervals greater than 1m at 0.5g/t Au.</p> <p>All composited intercept assays were weighted by sample length. No upper cut-off grades were applied.</p> <p>Mineralised Zone At the Hit or Miss and Treasure prospects mineralised zones have been reported which encompass the significant intercepts within defined structures that do contain multiple mineralised structures and these with the internal waste intervals are shown on the accompanying Figures 8 and 10</p>
	In reporting Exploration Results, weighting averaging techniques, maximum and/or minimum grade truncations (e.g. cutting of high grades) and cut-off grades are usually Material and should be stated.	
	Where aggregate intercepts incorporate short lengths of high grade results and longer lengths of low grade results, the procedure used for such aggregation should be stated and some typical examples of such aggregations should be shown in detail.	All the drill samples are collected over -consistent 1 m intervals and composited assays weighted by sample lengths.
	The assumptions used for any reporting of metal equivalent values should be clearly stated.	Metal equivalent values have not been reported
Relationship between mineralisation widths and intercept lengths	<p>These relationships are particularly important in the reporting of Exploration Results.</p> <p>If the geometry of the mineralisation with respect to the drill hole angle is known, its nature should be reported.</p> <p>If it is not known and only the down hole lengths are reported, there should be a clear statement to this effect (e.g. 'down hole length, true width not known').</p>	Based upon historical mine reports and surface observations; the geometry of the mineralisation is reasonably well understood. In most cases the drilling is close to perpendicular to the strike and as the mineralisation is steeply dipping, true widths of the mineralisation are considered to be greater than 60% of the intercept width. Plans and cross sections are provided in the body of the report that show the relationship between the drill holes and the mineralisation.
Diagrams	Appropriate maps and sections (with scales) and tabulations of intercepts should be included for any significant discovery being reported. These should include, but not be limited to a plan view of drill hole collar locations and appropriate sectional views.	Refer to diagrams provided in the body of the report
Balanced reporting	Where comprehensive reporting of all Exploration Results is not practicable, representative reporting of both low and high grades and/or widths should be practiced to avoid misleading reporting of Exploration Results.	All drilling results are provided in Appendix 2 of the report.

Criteria	JORC Code explanation	Commentary
Other substantive exploration data	Other exploration data, if meaningful and material, should be reported including (but not limited to): geological observations; geophysical survey results; geochemical survey results; bulk samples – size and method of treatment; metallurgical test results; bulk density, groundwater, geotechnical and rock characteristics; potential deleterious or contaminating substances.	<p>The area was the subject of detailed study by the Bureau of Mineral Resources and this was published in Bulletin No 6 (1961). The geology of all the areas drilled are described in detail in this report.</p> <p>GWR has undertaken significant metallurgical test work on representative mineralised samples with the results of these tests reported in previous ASX announcements.</p>
Further work	The nature and scale of planned further work (e.g. tests for lateral extensions or depth extensions or large-scale step-out drilling). Diagrams clearly highlighting the areas of possible extensions, including the main geological interpretations and future drilling areas, provided this information is not commercially sensitive	Further RC drilling and possibly diamond drilling is planned to follow up on the results described in this report and also to evaluate the remaining prospect areas not tested in the current program.

APPENDIX 2

DRILL HOLE ASSAY RESULTS

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC001	0	1	0.035	0.116	0.078	0.003	0.014	0.004	<0.001	0.336
HCRC001	1	2	0.029	0.073	0.010	0.001	0.021	0.003	0.002	0.004
HCRC001	2	3	0.007	0.014	0.020	<0.001	<0.001	<0.001	<0.001	0.006
HCRC001	3	4	0.008	0.025	0.021	<0.001	0.008	<0.001	<0.001	0.002
HCRC001	4	5	0.002	0.003	0.004	<0.001	<0.001	<0.001	0.004	0.001
HCRC001	5	6	0.005	0.005	0.006	<0.001	0.002	<0.001	<0.001	0.002
HCRC001	6	7	0.019	0.024	0.047	<0.001	0.002	<0.001	<0.001	<0.001
HCRC001	7	8	0.004	0.004	0.025	<0.001	0.002	<0.001	0.007	0.002
HCRC001	8	9	0.102	0.056	0.140	<0.001	0.020	0.003	<0.001	0.005
HCRC001	9	10	0.071	0.046	0.324	<0.001	0.003	<0.001	0.007	0.009
HCRC001	10	11	0.013	0.021	0.147	<0.001	0.002	0.002	0.008	0.002
HCRC001	11	12	0.013	0.004	0.043	<0.001	<0.001	0.007	0.007	0.004
HCRC001	12	13	0.411	0.013	0.075	<0.001	0.003	<0.001	0.004	0.002
HCRC001	13	14	0.019	0.016	0.098	<0.001	<0.001	<0.001	0.005	0.003
HCRC001	14	15	0.007	0.008	0.028	<0.001	0.007	0.008	<0.001	<0.001
HCRC001	15	16	0.006	0.010	0.030	<0.001	0.010	<0.001	<0.001	<0.001
HCRC001	16	17	0.004	0.006	0.035	<0.001	0.004	<0.001	0.002	0.003
HCRC001	17	18	0.004	0.005	0.020	<0.001	0.003	0.006	0.003	0.001
HCRC001	18	19	0.005	0.007	0.028	<0.001	<0.001	0.003	0.003	0.002
HCRC001	19	20	0.004	0.004	0.012	<0.001	<0.001	0.010	0.002	0.003
HCRC001	20	21	0.005	0.016	0.009	<0.001	0.015	<0.001	<0.001	0.002
HCRC001	21	22	0.008	0.015	0.028	<0.001	0.007	<0.001	0.003	0.002
HCRC001	22	23	0.052	0.011	0.022	<0.001	0.010	0.005	0.002	0.002
HCRC001	23	24	0.005	0.001	0.004	<0.001	0.003	0.004	0.004	0.002
HCRC001	24	25	0.030	0.015	0.048	<0.001	0.016	0.003	0.004	0.004
HCRC001	25	26	0.020	0.017	0.034	<0.001	0.022	0.003	0.005	0.002
HCRC001	26	27	0.047	0.103	0.250	<0.001	0.008	0.002	0.002	0.008
HCRC001	27	28	0.025	0.030	0.218	<0.001	0.004	0.005	0.004	0.004
HCRC001	28	29	0.006	0.012	0.016	<0.001	0.009	0.004	0.005	0.003
HCRC002	0	1	No sample							
HCRC002	1	2	0.036	0.045	0.052	<0.001	0.022	<0.001	0.004	0.016
HCRC002	2	3	0.002	0.009	0.004	<0.001	<0.001	<0.001	0.002	0.006
HCRC002	3	4	<0.001	0.005	0.002	<0.001	<0.001	<0.001	<0.001	0.001
HCRC002	4	5	0.008	0.004	0.044	<0.001	0.010	<0.001	<0.001	0.003
HCRC002	5	6	0.003	0.002	0.069	<0.001	<0.001	<0.001	0.002	0.002
HCRC002	6	7	0.004	0.001	0.058	<0.001	0.002	0.004	0.002	0.015
HCRC002	7	8	0.002	<0.001	0.018	<0.001	0.003	<0.001	<0.001	0.006
HCRC002	8	9	0.003	<0.001	0.010	<0.001	0.003	<0.001	0.002	0.002
HCRC002	9	10	0.004	0.002	0.017	<0.001	0.005	0.002	<0.001	0.001
HCRC002	10	11	0.002	0.001	0.011	<0.001	<0.001	0.005	0.002	0.002
HCRC002	11	12	0.002	<0.001	0.007	<0.001	0.002	0.001	<0.001	<0.001
HCRC002	12	13	0.003	0.001	0.014	<0.001	0.002	0.001	0.002	0.001
HCRC002	13	14	0.021	0.005	0.034	<0.001	0.007	0.002	<0.001	<0.001
HCRC002	14	15	0.005	0.005	0.007	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC002	15	16	0.016	0.004	0.031	<0.001	<0.001	0.002	0.002	0.004
HCRC002	16	17	0.021	0.004	0.045	<0.001	<0.001	<0.001	0.006	0.003
HCRC002	17	18	0.006	0.002	0.024	<0.001	0.004	<0.001	0.005	<0.001
HCRC002	18	19	0.004	0.001	0.013	<0.001	<0.001	0.010	<0.001	0.002
HCRC002	19	20	0.009	0.001	0.029	<0.001	<0.001	<0.001	0.006	0.002
HCRC002	20	21	0.007	0.003	0.030	<0.001	<0.001	<0.001	0.008	0.003
HCRC002	21	22	0.010	0.010	0.091	<0.001	<0.001	0.002	0.013	0.003
HCRC002	22	23	0.026	0.013	0.090	<0.001	<0.001	0.006	0.005	0.015
HCRC002	23	24	0.008	0.038	0.037	<0.001	<0.001	<0.001	0.008	0.008

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC002	24	25	0.031	0.073	0.062	<0.001	0.003	<0.001	0.002	0.022
HCRC002	25	26	0.006	0.005	0.038	<0.001	<0.001	<0.001	0.002	0.003
HCRC002	26	27	No sample							
HCRC002	27	28	0.086	0.080	0.297	0.001	0.017	<0.001	0.005	0.016
HCRC002	28	29	0.031	0.026	0.152	<0.001	0.004	<0.001	0.004	0.121
HCRC002	29	30	0.074	0.028	0.123	0.003	0.006	<0.001	0.002	0.261
HCRC002	30	31	0.027	0.031	0.225	0.001	0.003	<0.001	0.002	0.143
HCRC002	31	32	0.010	0.016	0.146	<0.001	0.005	<0.001	0.003	0.250
HCRC002	32	33	0.005	<0.001	0.032	<0.001	0.002	<0.001	<0.001	0.158
HCRC002	33	34	0.006	0.004	0.043	<0.001	0.002	0.002	<0.001	0.078
HCRC002	34	35	0.006	0.006	0.049	0.005	0.002	0.004	0.002	0.579
HCRC002	35	36	0.013	0.006	0.028	0.004	0.004	0.001	0.005	0.481
HCRC002	36	37	0.012	0.009	0.069	0.011	0.006	0.004	0.003	1.407
HCRC002	37	38	0.004	0.003	0.032	0.003	0.002	<0.001	0.003	0.285
HCRC002	38	39	0.006	0.005	0.022	0.002	0.004	<0.001	0.004	0.273
HCRC002	39	40	0.014	0.004	0.025	0.001	0.002	<0.001	0.002	0.129
HCRC002	40	41	0.039	0.063	0.225	0.002	0.005	0.001	0.006	0.428
HCRC002	41	42	0.014	0.017	0.154	0.003	0.014	<0.001	<0.001	0.240
HCRC002	42	43	0.005	0.005	0.007	<0.001	<0.001	0.003	<0.001	0.011
HCRC002	43	44	0.003	<0.001	0.004	0.001	0.003	<0.001	0.002	0.005
HCRC002	44	45	0.454	0.013	0.005	0.012	0.009	<0.001	0.003	0.015
HCRC002	45	46	0.007	0.044	0.012	<0.001	0.007	0.004	<0.001	0.011
HCRC002	46	47	0.022	0.025	0.058	0.003	0.063	<0.001	<0.001	0.109
HCRC002	47	48	0.003	<0.001	0.009	<0.001	0.003	<0.001	0.002	0.009
HCRC002	48	49	0.004	<0.001	0.008	<0.001	0.002	<0.001	<0.001	0.002
HCRC002	49	50	0.003	0.013	0.014	<0.001	0.009	<0.001	0.002	0.061
HCRC002	50	51	0.008	0.013	0.043	0.004	0.010	0.002	<0.001	0.295
HCRC002	51	52	0.010	0.007	0.026	<0.001	0.005	<0.001	0.002	0.028
HCRC002	52	53	0.003	<0.001	0.002	<0.001	0.003	0.004	<0.001	0.006
HCRC002	53	54	0.003	0.040	0.145	0.001	0.020	0.001	0.002	0.258
HCRC002	54	55	0.004	0.020	0.045	0.001	0.009	<0.001	<0.001	0.207
HCRC002	55	56	0.002	0.020	0.043	0.003	0.011	0.003	0.002	0.184
HCRC002	56	57	0.001	0.004	0.002	<0.001	0.002	<0.001	0.002	0.030
HCRC002	57	58	0.002	0.007	0.034	<0.001	0.003	0.002	0.002	0.045
HCRC002	58	59	0.002	0.011	<0.001	<0.001	0.002	0.003	<0.001	0.005
HCRC002	59	60	0.007	0.056	0.080	0.007	0.055	0.003	<0.001	0.729
HCRC002	60	61	0.002	0.006	0.022	0.001	0.006	0.004	<0.001	0.064
HCRC002	61	62	0.092	0.020	0.010	0.008	0.043	<0.001	<0.001	0.053
HCRC002	62	63	0.002	0.002	0.002	<0.001	<0.001	<0.001	<0.001	0.051
HCRC002	63	64	0.003	0.006	<0.001	<0.001	0.006	<0.001	0.002	0.015
HCRC002	64	65	0.002	0.002	<0.001	<0.001	0.002	<0.001	0.002	0.007
HCRC002	65	66	0.001	0.001	<0.001	<0.001	0.002	<0.001	0.002	0.013
HCRC002	66	67	<0.001	<0.001	0.009	<0.001	<0.001	0.002	0.002	0.018
HCRC002	67	68	0.002	0.009	0.032	0.001	0.008	<0.001	<0.001	0.060
HCRC002	68	69	0.727	0.107	0.100	0.004	0.076	0.003	0.002	0.223
HCRC002	69	70	0.014	0.087	0.043	0.003	0.050	<0.001	0.002	0.102
HCRC002	70	71	0.006	0.101	0.016	0.002	0.024	0.003	<0.001	0.200
HCRC002	71	72	0.004	0.012	0.005	0.001	0.007	<0.001	<0.001	0.079
HCRC002	72	73	0.003	0.018	0.009	0.001	0.004	0.006	<0.001	0.224
HCRC002	73	74	0.004	0.002	0.005	<0.001	0.003	<0.001	<0.001	0.145
HCRC002	74	75	0.002	0.002	0.008	<0.001	0.002	0.005	<0.001	0.126
HCRC002	75	76	0.014	0.005	0.020	0.002	0.002	<0.001	0.002	0.258
HCRC002	76	77	0.158	0.498	0.258	0.009	0.149	0.004	0.002	0.559

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC002	77	78	0.062	0.031	0.010	<0.001	0.013	<0.001	<0.001	0.124
HCRC002	78	79	0.008	0.003	0.002	<0.001	0.003	<0.001	0.002	0.012
HCRC002	79	80	0.010	0.005	0.021	<0.001	0.003	<0.001	0.002	0.141
HCRC002	80	81	0.014	0.003	0.011	<0.001	0.004	0.003	<0.001	0.139
HCRC002	81	82	1.313	0.263	0.039	0.003	0.137	<0.001	0.002	0.192
HCRC002	82	83	0.242	0.021	0.039	0.003	0.021	<0.001	0.007	0.432
HCRC002	83	84	0.329	0.015	0.062	0.004	0.014	<0.001	0.002	0.287
HCRC002	84	85	0.026	0.012	0.040	0.005	0.015	<0.001	<0.001	0.202
HCRC002	85	86	0.026	0.031	0.064	0.004	0.010	<0.001	0.005	0.530
HCRC002	86	87	0.005	0.057	0.065	0.008	0.020	<0.001	<0.001	0.525
HCRC002	87	88	0.018	0.032	0.093	0.005	0.013	0.002	0.002	0.590
HCRC002	88	89	0.009	0.037	0.083	0.007	0.019	0.002	0.002	0.831
HCRC002	89	90	0.047	0.055	0.047	0.006	0.025	<0.001	0.002	0.539
HCRC002	90	91	0.019	0.010	0.020	0.003	0.009	<0.001	<0.001	0.246
HCRC002	91	92	0.003	0.010	0.037	0.004	0.004	<0.001	<0.001	0.529
HCRC002	92	93	0.002	0.011	0.046	0.009	<0.001	<0.001	0.004	1.393
HCRC002	93	94	0.004	0.012	0.066	0.012	0.003	<0.001	0.005	1.905
HCRC002	94	95	0.003	0.024	0.091	0.011	0.019	<0.001	0.003	1.204
HCRC002	95	96	0.246	0.022	0.039	0.011	0.023	<0.001	0.004	0.749
HCRC003	0	1	No sample							
HCRC003	1	2	0.036	0.100	0.026	0.001	0.015	0.007	0.002	0.053
HCRC003	2	3	0.002	0.006	0.010	<0.001	<0.001	<0.001	<0.001	0.010
HCRC003	3	4	0.003	0.003	0.008	<0.001	<0.001	0.003	0.002	0.005
HCRC003	4	5	0.006	0.014	0.086	<0.001	0.004	<0.001	0.002	0.004
HCRC003	5	6	<0.001	0.002	0.011	<0.001	<0.001	0.004	<0.001	0.002
HCRC003	6	7	0.005	0.010	0.026	<0.001	<0.001	<0.001	0.002	0.005
HCRC003	7	8	0.003	0.004	0.015	<0.001	<0.001	0.004	0.002	0.002
HCRC003	8	9	0.005	0.002	0.019	<0.001	0.001	0.007	<0.001	0.003
HCRC003	9	10	0.001	0.003	0.016	<0.001	<0.001	<0.001	<0.001	0.003
HCRC003	10	11	0.003	0.001	0.016	<0.001	0.005	0.001	<0.001	0.003
HCRC003	11	12	0.008	0.013	0.097	<0.001	0.003	0.010	<0.001	0.003
HCRC003	12	13	0.006	0.003	0.019	<0.001	0.001	<0.001	<0.001	0.007
HCRC003	13	14	0.003	0.006	0.022	<0.001	0.002	0.003	0.002	0.003
HCRC003	14	15	0.005	0.004	0.022	<0.001	0.002	<0.001	0.002	0.002
HCRC003	15	16	0.011	0.006	0.019	<0.001	0.003	0.004	0.002	0.002
HCRC003	16	17	0.016	0.023	0.025	<0.001	0.004	<0.001	0.003	0.003
HCRC003	17	18	0.017	0.009	0.050	<0.001	0.004	<0.001	0.006	0.006
HCRC003	18	19	0.008	0.006	0.026	<0.001	0.002	0.006	0.003	0.005
HCRC003	19	20	0.006	0.006	0.026	<0.001	0.003	<0.001	0.004	0.002
HCRC003	20	21	0.012	0.007	0.051	<0.001	0.006	0.008	<0.001	0.002
HCRC003	21	22	0.004	0.005	0.039	<0.001	0.016	0.006	<0.001	0.007
HCRC003	22	23	0.004	0.009	0.016	<0.001	0.001	<0.001	<0.001	0.002
HCRC003	23	24	0.013	0.006	0.118	<0.001	0.016	<0.001	<0.001	0.008
HCRC003	24	25	0.004	0.001	0.036	<0.001	0.002	<0.001	0.002	0.003
HCRC003	25	26	0.010	0.010	0.115	<0.001	0.012	0.004	<0.001	0.004
HCRC003	26	27	0.007	0.033	0.096	<0.001	0.017	0.002	<0.001	0.003
HCRC003	27	28	0.007	0.007	0.065	<0.001	0.005	<0.001	<0.001	0.003
HCRC003	28	29	0.017	0.027	0.085	<0.001	0.005	<0.001	<0.001	0.009
HCRC003	29	30	0.002	<0.001	0.009	0.001	0.002	<0.001	<0.001	0.111
HCRC003	30	31	0.002	0.001	0.004	<0.001	0.002	0.006	<0.001	0.098
HCRC003	31	32	0.002	0.017	0.005	<0.001	0.002	<0.001	<0.001	0.067
HCRC003	32	33	0.004	0.001	0.011	0.001	0.002	<0.001	0.002	0.212
HCRC003	33	34	0.003	0.002	0.016	<0.001	0.006	0.005	<0.001	0.190

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC003	34	35	0.003	0.003	0.036	0.001	0.002	<0.001	0.005	0.376
HCRC003	35	36	0.007	0.015	0.071	0.003	0.004	0.004	0.005	0.651
HCRC003	36	37	0.005	0.016	0.106	0.003	0.002	<0.001	0.002	0.435
HCRC003	37	38	0.008	0.006	0.052	0.005	0.003	0.006	0.006	0.650
HCRC003	38	39	0.112	0.051	0.205	0.041	0.023	0.009	0.006	6.403
HCRC003	39	40	0.008	0.003	0.021	0.002	0.004	<0.001	0.003	0.266
HCRC003	40	41	0.004	0.001	0.020	<0.001	0.003	<0.001	<0.001	0.190
HCRC003	41	42	0.020	0.031	0.063	0.002	0.004	0.004	0.002	0.559
HCRC003	42	43	0.003	0.002	0.009	0.001	0.002	0.007	<0.001	0.195
HCRC003	43	44	0.002	0.057	0.010	<0.001	0.003	<0.001	<0.001	0.163
HCRC003	44	45	0.006	0.005	0.033	0.003	0.006	0.001	<0.001	0.603
HCRC003	45	46	0.004	0.013	0.097	0.011	0.006	<0.001	0.002	1.420
HCRC003	46	47	0.002	0.005	0.010	0.002	0.001	0.003	<0.001	0.395
HCRC003	47	48	0.001	0.003	0.006	0.002	0.001	<0.001	<0.001	0.276
HCRC003	48	49	0.002	0.004	0.011	0.001	0.005	0.005	<0.001	0.232
HCRC003	49	50	0.003	0.002	0.019	0.001	0.003	0.003	<0.001	0.525
HCRC003	50	51	0.003	0.005	0.018	0.001	0.002	<0.001	<0.001	0.246
HCRC003	51	52	0.008	0.027	0.049	0.002	0.005	<0.001	0.003	0.422
HCRC003	52	53	0.090	0.022	0.104	0.005	0.004	0.004	0.002	0.722
HCRC003	53	54	0.018	0.151	0.269	0.006	0.002	<0.001	0.006	1.045
HCRC003	54	55	0.295	0.420	0.426	0.010	0.048	<0.001	0.005	0.884
HCRC003	55	56	0.090	0.165	0.489	0.015	0.031	0.004	0.002	2.314
HCRC003	56	57	0.055	0.062	0.351	0.018	0.019	<0.001	0.006	2.557
HCRC003	57	58	0.067	0.037	0.134	0.003	0.007	<0.001	0.004	0.608
HCRC003	58	59	0.029	0.066	0.240	0.003	0.009	0.002	0.002	0.592
HCRC003	59	60	0.017	0.026	0.125	0.003	0.007	<0.001	<0.001	0.447
HCRC003	60	61	0.009	0.049	0.212	0.005	0.004	<0.001	<0.001	0.775
HCRC003	61	62	0.006	0.051	0.064	0.002	0.004	0.005	0.002	0.621
HCRC003	62	63	0.023	0.008	0.057	0.006	0.004	<0.001	0.005	1.235
HCRC003	63	64	0.010	0.025	0.081	0.007	0.004	0.003	0.004	1.224
HCRC003	64	65	0.016	0.022	0.124	0.008	0.003	<0.001	0.005	1.475
HCRC003	65	66	0.008	0.013	0.093	0.004	0.003	<0.001	0.009	0.854
HCRC003	66	67	0.062	0.031	0.161	0.007	0.008	<0.001	<0.001	1.062
HCRC003	67	68	0.014	0.017	0.085	0.003	0.006	0.003	<0.001	0.678
HCRC003	68	69	0.006	0.004	0.036	0.003	0.004	<0.001	0.003	0.356
HCRC003	69	70	0.004	0.005	0.023	0.002	0.004	0.004	<0.001	0.429
HCRC003	70	71	0.005	0.008	0.026	0.003	0.004	0.008	<0.001	0.469
HCRC003	71	72	0.008	0.005	0.024	0.001	0.002	0.008	<0.001	0.227
HCRC003	72	73	0.006	0.024	0.042	0.003	0.026	0.004	<0.001	0.314
HCRC003	73	74	0.063	0.026	0.058	<0.001	0.024	0.003	<0.001	0.373
HCRC003	74	75	0.025	0.020	0.029	0.001	0.010	<0.001	0.002	0.154
HCRC003	75	76	0.006	0.008	0.044	<0.001	0.004	0.004	<0.001	0.219
HCRC003	76	77	0.006	0.006	0.027	<0.001	0.004	0.002	<0.001	0.159
HCRC003	77	78	0.013	0.009	0.098	0.002	0.005	<0.001	0.002	0.222
HCRC003	78	79	0.058	0.022	0.108	<0.001	0.009	<0.001	0.006	0.309
HCRC003	79	80	0.056	0.026	0.212	0.014	0.002	0.001	0.006	2.189
HCRC003	80	81	0.014	0.026	0.183	0.009	0.006	<0.001	0.005	0.567
HCRC003	81	82	0.012	0.011	0.052	0.003	0.001	0.003	0.006	0.395
HCRC003	82	83	0.009	0.006	0.050	0.009	0.002	<0.001	0.002	1.238
HCRC003	83	84	0.012	0.010	0.031	0.003	0.002	<0.001	0.011	0.363
HCRC003	84	85	0.047	0.081	0.151	0.002	0.013	0.004	0.002	0.464
HCRC003	85	86	0.009	0.094	0.054	0.005	0.003	<0.001	0.010	0.478
HCRC003	86	87	0.012	0.006	0.035	0.002	0.003	<0.001	0.006	0.199

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC003	87	88	0.012	0.012	0.077	0.002	0.004	<0.001	0.002	0.323
HCRC003	88	89	0.019	0.022	0.029	<0.001	0.015	0.006	0.002	0.151
HCRC003	89	90	0.019	0.074	0.173	0.009	0.035	0.006	<0.001	1.020
HCRC003	90	91	0.017	0.034	0.076	0.002	0.011	0.005	<0.001	0.232
HCRC003	91	92	0.003	0.035	0.027	<0.001	0.004	<0.001	0.002	0.078
HCRC003	92	93	0.678	0.081	0.742	0.011	0.018	0.006	<0.001	1.163
HCRC003	93	94	0.010	0.005	0.012	<0.001	<0.001	<0.001	0.002	0.047
HCRC003	94	95	0.004	0.019	0.009	0.005	0.020	0.004	<0.001	0.346
HCRC003	95	96	0.003	0.005	0.003	<0.001	0.003	0.002	<0.001	0.043
HCRC003	96	97	0.003	0.061	0.057	0.002	0.020	<0.001	<0.001	0.199
HCRC003	97	98	0.003	2.258	0.008	0.003	0.178	<0.001	<0.001	0.069
HCRC003	98	99	0.002	0.024	0.006	<0.001	0.003	<0.001	<0.001	0.028
HCRC003	99	100	0.001	0.005	0.001	<0.001	0.001	<0.001	<0.001	0.009
HCRC003	100	101	0.001	0.005	0.002	<0.001	<0.001	0.005	<0.001	0.019
HCRC003	101	102	0.001	0.001	0.001	<0.001	<0.001	0.001	0.002	0.019
HCRC003	102	103	0.037	0.038	0.030	0.004	0.009	0.001	<0.001	0.151
HCRC003	103	104	0.004	0.015	0.026	<0.001	0.007	0.008	0.002	0.100
HCRC003	104	105	0.003	0.535	0.030	0.004	0.082	<0.001	<0.001	0.152
HCRC003	105	106	0.005	0.027	0.040	0.004	0.010	<0.001	<0.001	0.552
HCRC003	106	107	0.078	0.004	0.021	<0.001	0.003	0.006	0.006	0.104
HCRC003	107	108	0.185	0.021	0.077	0.001	0.016	<0.001	0.004	0.217
HCRC003	108	109	0.013	0.043	0.068	<0.001	0.021	0.002	0.003	0.480
HCRC003	109	110	0.005	0.006	0.034	<0.001	0.007	0.004	0.005	0.424
HCRC003	110	111	0.031	0.004	0.019	<0.001	0.007	<0.001	<0.001	0.257
HCRC003	111	112	0.025	0.080	0.065	<0.001	0.007	<0.001	<0.001	0.357
HCRC003	112	113	0.053	0.107	0.196	<0.001	0.101	<0.001	0.003	0.426
HCRC003	113	114	0.006	0.007	0.029	<0.001	0.005	0.009	0.004	0.298
HCRC003	114	115	0.013	0.020	0.016	<0.001	0.014	0.003	<0.001	0.229
HCRC003	115	116	0.002	0.005	0.009	<0.001	0.001	0.009	<0.001	0.143
HCRC003	116	117	0.004	0.004	0.029	<0.001	0.002	<0.001	0.002	0.446
HCRC003	117	118	0.006	0.004	0.014	0.001	0.003	0.010	<0.001	0.253
HCRC003	118	119	0.159	0.011	0.014	0.003	0.007	<0.001	<0.001	0.149
HCRC003	119	120	0.037	0.122	0.897	<0.001	0.031	0.002	0.002	1.373
HCRC003	120	121	0.014	0.009	0.031	<0.001	0.004	0.004	<0.001	0.210
HCRC003	121	122	1.197	0.814	0.932	<0.001	0.191	0.003	<0.001	2.077
HCRC003	122	123	0.052	0.044	0.048	<0.001	0.030	0.007	<0.001	0.215
HCRC003	123	124	0.010	0.007	0.019	0.002	0.004	0.008	<0.001	0.443
HCRC003	124	125	0.008	0.008	0.019	0.003	0.005	0.002	0.002	0.597
HCRC003	125	126	0.028	0.012	0.042	<0.001	0.007	0.001	0.004	1.147
HCRC003	126	127	0.017	0.012	0.043	<0.001	0.002	<0.001	0.005	0.668
HCRC003	127	128	0.003	0.007	0.042	<0.001	0.002	0.002	<0.001	0.986
HCRC003	128	129	0.110	0.033	0.252	<0.001	0.019	<0.001	<0.001	1.193
HCRC003	129	130	0.040	0.015	0.162	<0.001	0.088	0.006	<0.001	0.802
HCRC004	0	1	0.139	0.104	0.056	0.002	0.021	<0.001	0.003	0.064
HCRC004	1	2	0.010	0.019	0.124	<0.001	0.003	<0.001	<0.001	0.023
HCRC004	2	3	0.152	0.276	0.324	0.002	0.055	<0.001	0.003	0.044
HCRC004	3	4	0.136	1.333	0.291	0.002	0.082	0.003	0.006	0.039
HCRC004	4	5	0.005	0.062	0.130	<0.001	0.003	0.003	0.002	0.018
HCRC004	5	6	0.007	0.037	0.017	<0.001	0.010	0.009	<0.001	0.007
HCRC004	6	7	0.019	0.058	0.055	<0.001	0.014	<0.001	<0.001	0.017
HCRC004	7	8	0.005	0.010	0.024	<0.001	0.003	0.003	0.002	0.008
HCRC004	8	9	0.006	0.038	0.058	<0.001	0.002	0.002	<0.001	0.004
HCRC004	9	10	0.006	0.005	0.009	<0.001	0.004	0.002	0.002	0.029

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC004	10	11	0.002	0.003	0.006	<0.001	0.001	0.001	<0.001	0.005
HCRC004	11	12	<0.001	0.003	0.003	<0.001	<0.001	0.005	<0.001	0.003
HCRC004	12	13	0.002	0.002	<0.001	<0.001	<0.001	0.003	<0.001	0.005
HCRC004	13	14	0.002	0.003	0.121	<0.001	0.001	<0.001	0.002	0.003
HCRC004	14	15	0.002	0.036	0.351	0.001	0.019	0.003	0.002	0.004
HCRC004	15	16	0.003	0.003	0.018	<0.001	0.007	0.002	<0.001	0.003
HCRC004	16	17	0.002	0.007	0.006	<0.001	<0.001	<0.001	0.003	0.002
HCRC004	17	18	0.003	0.016	0.023	<0.001	0.003	0.007	0.002	0.007
HCRC004	18	19	0.003	0.005	0.062	<0.001	0.002	0.005	0.002	0.002
HCRC004	19	20	0.017	0.005	0.098	<0.001	0.002	0.007	<0.001	0.036
HCRC004	20	21	0.005	0.030	0.084	<0.001	0.011	<0.001	<0.001	0.075
HCRC004	21	22	0.004	0.001	0.017	<0.001	0.002	0.006	<0.001	0.007
HCRC004	22	23	0.004	<0.001	0.008	<0.001	0.002	<0.001	<0.001	0.002
HCRC004	23	24	0.003	0.008	0.011	<0.001	0.003	0.006	<0.001	0.003
HCRC004	24	25	0.001	0.009	0.027	<0.001	<0.001	<0.001	<0.001	0.002
HCRC004	25	26	0.002	0.025	0.045	0.003	0.003	0.003	0.002	0.046
HCRC004	26	27	0.005	0.030	0.024	0.001	0.002	<0.001	0.002	0.015
HCRC004	27	28	0.007	0.010	0.057	<0.001	0.002	<0.001	0.003	0.006
HCRC004	28	29	0.003	0.175	0.017	<0.001	0.070	<0.001	<0.001	0.011
HCRC004	29	30	0.003	0.009	0.026	<0.001	0.005	<0.001	0.002	0.036
HCRC004	30	31	0.060	0.024	0.298	<0.001	0.005	0.003	0.005	0.014
HCRC004	31	32	0.093	0.022	0.106	<0.001	0.003	0.008	0.004	0.350
HCRC004	32	33	0.008	0.004	0.027	<0.001	0.002	<0.001	0.003	0.062
HCRC004	33	34	0.005	0.004	0.013	<0.001	0.002	<0.001	<0.001	0.059
HCRC004	34	35	0.017	0.001	0.010	<0.001	0.003	<0.001	0.005	0.026
HCRC004	35	36	0.313	0.070	0.030	0.041	0.108	0.003	0.003	0.310
HCRC004	36	37	0.016	0.002	0.005	<0.001	0.008	0.004	0.002	0.019
HCRC004	37	38	0.004	0.004	0.004	<0.001	0.002	0.003	<0.001	0.011
HCRC004	38	39	0.010	0.011	0.011	0.004	0.005	0.003	0.003	0.077
HCRC004	39	40	0.006	0.047	0.004	0.023	0.008	0.006	0.003	0.038
HCRC004	40	41	0.005	<0.001	<0.001	<0.001	0.004	0.002	<0.001	0.009
HCRC004	41	42	0.003	0.002	0.014	<0.001	<0.001	0.006	0.004	0.028
HCRC004	42	43	0.006	0.004	0.010	<0.001	0.002	0.004	0.002	0.029
HCRC004	43	44	0.341	0.155	0.436	<0.001	0.033	0.002	0.003	3.609
HCRC004	44	45	2.854	1.758	0.285	0.004	0.270	<0.001	0.004	0.842
HCRC004	45	46	0.068	0.026	0.016	<0.001	0.007	<0.001	<0.001	0.203
HCRC004	46	47	0.049	0.034	0.073	<0.001	0.009	0.003	<0.001	0.432
HCRC004	47	48	0.021	0.015	0.012	<0.001	0.004	0.003	<0.001	0.208
HCRC004	48	49	0.437	0.188	0.018	<0.001	0.034	<0.001	0.002	0.283
HCRC004	49	50	0.018	0.016	0.013	<0.001	0.007	0.005	0.002	0.222
HCRC004	50	51	0.008	0.016	0.014	<0.001	0.004	<0.001	<0.001	0.272
HCRC004	51	52	0.006	0.005	0.014	<0.001	0.003	<0.001	0.002	0.391
HCRC004	52	53	0.355	0.019	0.027	<0.001	0.005	<0.001	<0.001	0.556
HCRC004	53	54	0.418	1.962	0.039	<0.001	0.243	<0.001	0.003	0.920
HCRC004	54	55	0.016	0.041	0.016	<0.001	0.008	<0.001	<0.001	0.425
HCRC004	55	56	0.007	0.020	0.049	<0.001	0.005	<0.001	0.006	0.654
HCRC004	56	57	0.012	0.013	0.030	<0.001	0.004	<0.001	0.003	0.875
HCRC004	57	58	0.013	0.034	0.013	<0.001	0.001	<0.001	<0.001	0.442
HCRC004	58	59	0.006	0.016	0.048	<0.001	0.003	<0.001	<0.001	1.223
HCRC004	59	60	0.008	0.076	0.041	<0.001	0.027	0.002	<0.001	0.723
HCRC004	60	61	0.011	0.004	0.030	<0.001	0.003	0.006	<0.001	0.341
HCRC004	61	62	0.007	0.003	0.009	<0.001	0.001	0.003	<0.001	0.066
HCRC004	62	63	0.009	0.004	0.004	<0.001	0.005	<0.001	0.002	0.025

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC004	63	64	0.008	0.091	<0.001	<0.001	0.006	0.002	0.002	0.008
HCRC004	64	65	0.006	0.006	<0.001	<0.001	0.002	0.001	0.002	0.005
HCRC004	65	66	0.006	0.002	0.002	<0.001	0.002	0.005	0.002	0.005
HCRC004	66	67	0.033	0.054	0.001	0.002	0.004	0.004	0.002	0.013
HCRC004	67	68	0.026	0.011	0.007	<0.001	0.007	0.006	0.003	0.020
HCRC004	68	69	0.013	0.034	0.007	<0.001	0.015	0.004	<0.001	0.029
HCRC004	69	70	0.004	0.004	0.011	<0.001	0.002	<0.001	<0.001	0.046
HCRC004	70	71	0.234	0.057	0.276	0.004	0.031	0.004	0.002	1.045
HCRC004	71	72	0.030	0.013	0.047	<0.001	0.006	<0.001	0.005	0.152
HCRC004	72	73	0.145	0.017	0.038	<0.001	0.005	<0.001	<0.001	0.393
HCRC004	73	74	0.167	0.007	0.031	0.005	0.003	<0.001	<0.001	0.343
HCRC004	74	75	0.046	0.039	0.045	<0.001	0.040	0.007	0.002	0.340
HCRC004	75	76	0.005	0.024	0.023	<0.001	0.003	<0.001	<0.001	0.347
HCRC004	76	77	0.016	0.004	0.028	<0.001	0.003	<0.001	<0.001	0.343
HCRC004	77	78	0.005	0.007	0.039	0.014	0.013	<0.001	0.002	0.678
HCRC004	78	79	0.031	0.011	0.099	<0.001	0.004	0.006	0.006	1.203
HCRC004	79	80	0.005	0.008	0.030	<0.001	0.002	<0.001	0.002	0.530
HCRC004	80	81	1.956	1.579	0.278	0.011	0.297	<0.001	<0.001	0.442
HCRC004	81	82	0.004	0.009	0.026	<0.001	0.003	<0.001	<0.001	0.242
HCRC004	82	83	0.051	0.026	0.058	0.009	0.016	<0.001	0.003	0.465
HCRC004	83	84	0.009	0.007	0.026	<0.001	0.003	<0.001	<0.001	0.339
HCRC004	84	85	0.004	0.002	0.015	<0.001	0.003	<0.001	<0.001	0.180
HCRC004	85	86	0.006	0.029	0.153	<0.001	0.035	0.004	<0.001	0.689
HCRC004	86	87	0.005	0.332	0.027	<0.001	0.142	0.004	<0.001	0.449
HCRC004	87	88	0.003	0.006	0.008	<0.001	0.005	<0.001	<0.001	0.159
HCRC004	88	89	0.005	0.006	0.008	<0.001	0.002	0.002	0.002	0.100
HCRC004	89	90	0.002	0.001	0.010	<0.001	0.003	0.003	0.002	0.104
HCRC004	90	91	0.009	0.006	0.021	<0.001	0.010	0.002	0.002	0.770
HCRC004	91	92	0.018	0.040	0.066	<0.001	0.092	0.003	<0.001	0.447
HCRC004	92	93	0.007	<0.001	0.011	<0.001	0.004	0.003	<0.001	0.074
HCRC004	93	94	0.119	0.005	0.010	<0.001	0.004	<0.001	0.005	0.098
HCRC004	94	95	0.005	<0.001	0.011	0.001	0.003	<0.001	<0.001	0.242
HCRC004	95	96	0.119	0.012	0.033	<0.001	0.021	<0.001	0.003	0.238
HCRC004	96	97	0.024	0.003	0.011	<0.001	0.010	0.001	<0.001	0.079
HCRC004	97	98	0.007	0.001	0.017	<0.001	0.003	<0.001	<0.001	0.326
HCRC004	98	99	0.005	0.004	0.009	<0.001	0.004	0.007	0.002	0.176
HCRC004	99	100	0.006	0.003	0.012	<0.001	0.002	0.001	0.003	0.157
HCRC005	0	1	0.078	0.123	0.030	0.001	0.030	<0.001	0.002	0.130
HCRC005	1	2	0.084	0.066	0.026	<0.001	0.015	<0.001	<0.001	0.029
HCRC005	2	3	0.007	0.012	0.010	<0.001	0.003	<0.001	<0.001	0.007
HCRC005	3	4	0.013	0.028	0.097	<0.001	0.006	0.004	0.002	0.008
HCRC005	4	5	0.739	0.601	0.095	0.003	0.188	0.010	0.002	0.005
HCRC005	5	6	0.008	0.009	0.016	<0.001	0.001	<0.001	<0.001	0.002
HCRC005	6	7	0.037	0.033	0.130	<0.001	0.002	0.002	0.002	0.002
HCRC005	7	8	0.028	0.017	0.063	<0.001	<0.001	<0.001	0.004	0.003
HCRC005	8	9	0.005	0.005	0.005	<0.001	<0.001	0.002	0.002	<0.001
HCRC005	9	10	0.011	0.004	0.010	<0.001	0.001	0.007	0.003	<0.001
HCRC005	10	11	0.014	0.014	0.037	<0.001	0.002	0.002	0.002	0.003
HCRC005	11	12	0.013	0.009	0.049	<0.001	0.016	<0.001	<0.001	0.004
HCRC005	12	13	0.199	0.840	0.027	<0.001	0.121	0.003	<0.001	0.003
HCRC005	13	14	0.027	0.078	0.012	<0.001	0.010	0.009	<0.001	0.002
HCRC005	14	15	0.009	0.014	0.013	<0.001	0.004	0.004	<0.001	0.002
HCRC005	15	16	0.007	0.010	0.007	<0.001	0.003	0.005	0.002	0.003

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC005	16	17	0.017	0.004	0.010	<0.001	0.001	<0.001	0.002	0.002
HCRC005	17	18	0.011	0.019	0.009	0.002	0.004	<0.001	0.002	0.005
HCRC005	18	19	0.007	0.004	0.012	<0.001	0.001	<0.001	<0.001	0.001
HCRC005	19	20	0.018	0.010	0.044	<0.001	0.011	0.005	<0.001	0.005
HCRC005	20	21	0.006	0.003	0.010	<0.001	0.002	<0.001	0.005	0.002
HCRC005	21	22	0.005	0.009	0.010	<0.001	0.001	<0.001	0.005	0.002
HCRC005	22	23	0.029	0.022	0.018	<0.001	0.006	<0.001	0.002	0.005
HCRC005	23	24	0.024	0.007	0.087	<0.001	0.008	<0.001	<0.001	0.040
HCRC005	24	25	0.035	0.114	0.372	0.001	0.042	0.006	0.003	0.022
HCRC005	25	26	0.017	0.008	0.079	<0.001	0.002	0.004	<0.001	0.025
HCRC005	26	27	0.006	0.003	0.012	<0.001	0.003	0.002	0.002	0.003
HCRC005	27	28	0.006	0.003	0.010	<0.001	0.002	<0.001	<0.001	0.002
HCRC005	28	29	0.015	0.003	0.010	<0.001	0.002	0.004	<0.001	0.003
HCRC005	29	30	0.011	0.008	0.032	<0.001	0.007	0.008	<0.001	0.006
HCRC005	30	31	0.007	0.003	0.009	<0.001	0.003	0.002	0.002	0.005
HCRC005	31	32	0.006	0.006	0.009	<0.001	0.003	<0.001	0.002	0.004
HCRC005	32	33	0.009	0.071	0.020	<0.001	0.091	0.002	0.002	0.005
HCRC005	33	34	0.005	0.006	0.013	<0.001	0.004	<0.001	<0.001	0.065
HCRC005	34	35	0.015	0.038	0.032	0.001	0.002	0.003	0.005	0.215
HCRC005	35	36	0.005	0.014	0.016	<0.001	0.002	<0.001	0.002	0.161
HCRC005	36	37	0.005	0.055	0.009	0.003	0.004	0.006	<0.001	0.218
HCRC005	37	38	0.145	0.048	0.046	0.003	0.042	<0.001	0.002	0.379
HCRC005	38	39	0.008	0.016	0.046	0.002	0.004	<0.001	<0.001	0.271
HCRC005	39	40	0.015	0.030	0.150	0.014	0.073	0.002	0.005	1.335
HCRC005	40	41	0.011	0.015	0.024	0.001	0.023	<0.001	0.002	0.284
HCRC005	41	42	0.004	0.001	0.016	<0.001	0.007	<0.001	0.003	0.194
HCRC005	42	43	0.006	0.353	0.055	0.008	0.139	<0.001	0.002	0.563
HCRC005	43	44	0.012	0.012	0.020	<0.001	0.005	<0.001	<0.001	0.240
HCRC005	44	45	0.010	0.012	0.038	0.003	0.013	0.003	<0.001	0.417
HCRC005	45	46	0.005	0.009	0.113	0.004	0.011	0.006	0.002	0.725
HCRC005	46	47	0.003	0.006	0.031	0.002	0.031	<0.001	<0.001	0.414
HCRC005	47	48	0.040	0.033	0.134	0.004	0.013	0.005	0.003	0.400
HCRC005	48	49	0.060	0.040	0.036	0.002	0.028	<0.001	<0.001	0.255
HCRC005	49	50	0.013	0.037	0.186	0.003	0.059	<0.001	0.002	0.467
HCRC005	50	51	0.008	0.007	0.046	<0.001	0.009	<0.001	0.002	0.207
HCRC005	51	52	0.030	0.005	0.025	<0.001	0.003	<0.001	0.002	0.189
HCRC005	52	53	0.045	0.012	0.349	0.007	0.012	<0.001	<0.001	1.006
HCRC005	53	54	0.022	0.006	0.043	<0.001	0.001	0.007	0.002	0.336
HCRC005	54	55	0.003	0.190	0.023	<0.001	0.004	0.004	0.002	0.350
HCRC005	55	56	0.002	0.005	0.010	<0.001	0.001	0.002	<0.001	0.037
HCRC005	56	57	0.065	0.011	0.028	0.003	0.011	<0.001	0.003	0.118
HCRC005	57	58	0.004	0.006	0.030	<0.001	0.003	<0.001	<0.001	0.142
HCRC005	58	59	0.008	0.001	0.008	0.001	0.002	<0.001	<0.001	0.177
HCRC005	59	60	0.003	0.003	0.016	<0.001	0.004	<0.001	<0.001	0.083
HCRC005	60	61	0.013	0.001	0.021	0.001	0.002	<0.001	0.002	0.236
HCRC005	61	62	0.004	0.040	0.027	<0.001	0.007	<0.001	<0.001	0.147
HCRC005	62	63	0.005	0.560	0.158	<0.001	0.019	<0.001	<0.001	0.237
HCRC005	63	64	0.025	0.010	0.034	<0.001	0.002	<0.001	<0.001	0.158
HCRC005	64	65	0.005	0.016	0.022	<0.001	0.002	<0.001	<0.001	0.051
HCRC005	65	66	0.002	0.001	0.009	<0.001	0.002	<0.001	<0.001	0.034
HCRC005	66	67	0.004	<0.001	0.008	<0.001	0.002	<0.001	0.003	0.048
HCRC005	67	68	0.014	0.005	0.018	0.002	0.004	<0.001	0.002	0.327
HCRC005	68	69	0.002	0.003	0.015	<0.001	0.001	0.001	0.002	0.062

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC005	69	70	0.001	<0.001	0.010	<0.001	0.001	0.004	0.002	0.114
HCRC005	70	71	0.011	<0.001	0.008	<0.001	0.002	<0.001	<0.001	0.111
HCRC005	71	72	0.013	0.009	0.044	0.001	0.002	<0.001	0.006	0.446
HCRC005	72	73	0.003	0.007	0.008	<0.001	0.003	0.003	<0.001	0.120
HCRC005	73	74	0.001	0.002	0.009	<0.001	0.001	<0.001	<0.001	0.158
HCRC005	74	75	0.003	<0.001	0.014	<0.001	0.001	<0.001	0.002	0.132
HCRC005	75	76	0.006	<0.001	0.014	<0.001	0.002	<0.001	<0.001	0.162
HCRC005	76	77	0.003	0.001	0.010	<0.001	0.002	<0.001	<0.001	0.152
HCRC005	77	78	0.008	0.004	0.012	<0.001	0.002	<0.001	<0.001	0.127
HCRC005	78	79	0.004	0.001	0.012	<0.001	0.001	<0.001	<0.001	0.082
HCRC005	79	80	0.003	<0.001	0.010	<0.001	0.002	<0.001	<0.001	0.076
HCRC005	80	81	0.004	0.001	0.028	<0.001	0.003	<0.001	0.002	0.063
HCRC005	81	82	0.008	0.004	0.058	<0.001	<0.001	<0.001	0.010	0.156
HCRC005	82	83	0.014	0.008	0.032	<0.001	0.002	0.002	0.013	0.117
HCRC005	83	84	0.016	0.014	0.027	<0.001	<0.001	<0.001	0.005	0.164
HCRC006	0	1	0.493		0.122	<0.001	<0.001	<0.001	<0.001	0.013
HCRC006	1	2	0.020		0.096	0.003	0.002	<0.001	0.005	0.006
HCRC006	2	3	0.007		0.074	<0.001	0.001	<0.001	0.007	<0.001
HCRC006	3	4	0.579		0.535	0.002	0.001	<0.001	0.008	0.006
HCRC006	4	5	0.091		0.301	<0.001	<0.001	0.006	0.014	0.001
HCRC006	5	6	0.028		0.286	<0.001	0.002	0.001	0.015	0.002
HCRC006	6	7	0.017		0.140	<0.001	<0.001	<0.001	0.012	0.002
HCRC006	7	8	0.010		0.096	<0.001	0.002	<0.001	0.015	<0.001
HCRC006	8	9	0.016		0.133	<0.001	0.002	<0.001	0.020	0.002
HCRC006	9	10	0.017		0.136	<0.001	<0.001	<0.001	0.021	0.001
HCRC006	10	11	0.022		0.088	<0.001	<0.001	<0.001	0.011	<0.001
HCRC006	11	12	0.029		0.106	<0.001	<0.001	0.002	0.008	<0.001
HCRC006	12	13	0.014		0.040	<0.001	0.001	<0.001	0.006	<0.001
HCRC006	13	14	0.019		0.054	<0.001	<0.001	0.004	0.007	<0.001
HCRC006	14	15	0.019		0.200	<0.001	<0.001	<0.001	0.008	<0.001
HCRC006	15	16	0.047		0.386	<0.001	0.003	0.003	0.014	0.012
HCRC006	16	17	0.048		0.160	0.003	0.001	0.005	0.006	0.003
HCRC006	17	18	0.013		0.136	<0.001	0.002	<0.001	0.009	<0.001
HCRC006	18	19	0.035		0.443	<0.001	<0.001	<0.001	0.011	<0.001
HCRC006	19	20	0.014		0.092	<0.001	0.001	<0.001	0.010	<0.001
HCRC006	20	21	0.016		0.020	<0.001	<0.001	<0.001	0.006	<0.001
HCRC006	21	22	0.012		0.009	<0.001	<0.001	<0.001	0.004	<0.001
HCRC006	22	23	0.016		0.016	<0.001	0.001	0.003	0.004	<0.001
HCRC006	23	24	0.021		0.008	<0.001	<0.001	<0.001	0.002	<0.001
HCRC006	24	25	0.023		0.004	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC006	25	26	0.006		0.002	<0.001	<0.001	0.004	0.002	<0.001
HCRC006	26	27	0.054		0.004	<0.001	<0.001	<0.001	0.004	<0.001
HCRC006	27	28	0.013		0.016	<0.001	<0.001	<0.001	0.003	0.010
HCRC006	28	29	0.020		0.040	<0.001	<0.001	<0.001	0.003	<0.001
HCRC006	29	30	0.014		0.039	<0.001	<0.001	0.004	<0.001	<0.001
HCRC006	30	31	0.006		0.026	<0.001	<0.001	<0.001	0.007	<0.001
HCRC006	31	32	0.006		0.022	<0.001	<0.001	<0.001	0.010	0.003
HCRC006	32	33	0.007		0.025	<0.001	<0.001	<0.001	0.011	<0.001
HCRC006	33	34	0.023		0.037	<0.001	<0.001	<0.001	0.008	<0.001
HCRC006	34	35	0.025		0.020	<0.001	<0.001	0.001	0.005	<0.001
HCRC006	35	36	0.017		0.014	<0.001	0.001	<0.001	0.008	0.015
HCRC006	36	37	0.014		0.010	<0.001	<0.001	0.002	0.007	0.017
HCRC006	37	38	0.034		0.232	<0.001	0.002	<0.001	0.011	0.065

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC006	38	39	0.030		0.288	<0.001	0.001	<0.001	0.013	0.021
HCRC006	39	40	0.040		0.099	<0.001	<0.001	<0.001	0.008	0.023
HCRC007	0	1	0.013		0.006	<0.001	<0.001	<0.001	0.002	0.004
HCRC007	1	2	0.003		0.009	<0.001	<0.001	<0.001	<0.001	0.015
HCRC007	2	3	0.006		0.005	<0.001	<0.001	<0.001	<0.001	0.030
HCRC007	3	4	0.004		0.003	<0.001	<0.001	<0.001	<0.001	0.006
HCRC007	4	5	0.002		0.005	<0.001	<0.001	<0.001	<0.001	0.001
HCRC007	5	6	0.005		0.029	<0.001	<0.001	<0.001	0.002	0.002
HCRC007	6	7	0.008		0.087	<0.001	<0.001	0.004	0.002	0.003
HCRC007	7	8	0.010		0.083	<0.001	0.002	<0.001	0.004	0.001
HCRC007	8	9	0.003		0.168	<0.001	<0.001	0.002	<0.001	0.002
HCRC007	9	10	0.042		0.113	<0.001	0.001	<0.001	<0.001	<0.001
HCRC007	10	11	0.010		0.200	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC007	11	12	0.004		0.107	<0.001	<0.001	0.002	<0.001	<0.001
HCRC007	12	13	0.003		0.019	<0.001	<0.001	<0.001	0.002	<0.001
HCRC007	13	14	0.004		0.005	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC007	14	15	0.004		0.002	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC007	15	16	0.006		0.001	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC007	16	17	0.002		0.003	<0.001	0.001	<0.001	<0.001	0.002
HCRC007	17	18	0.004		0.002	<0.001	0.001	<0.001	<0.001	0.013
HCRC007	18	19	0.004		0.002	<0.001	<0.001	<0.001	0.002	<0.001
HCRC007	19	20	0.010		0.001	<0.001	<0.001	0.002	<0.001	<0.001
HCRC007	20	21	0.170		0.065	<0.001	<0.001	<0.001	0.003	<0.001
HCRC007	21	22	0.014		0.045	<0.001	<0.001	<0.001	0.003	<0.001
HCRC007	22	23	0.009		0.041	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC007	23	24	0.014		0.062	<0.001	0.001	<0.001	0.005	<0.001
HCRC007	24	25	0.016		0.063	<0.001	<0.001	<0.001	0.004	<0.001
HCRC007	25	26	0.017		0.055	<0.001	<0.001	<0.001	0.006	<0.001
HCRC007	26	27	0.166		0.126	<0.001	0.003	<0.001	0.010	<0.001
HCRC007	27	28	0.029		0.021	<0.001	0.001	<0.001	0.008	0.002
HCRC007	28	29	0.033		0.002	<0.001	0.002	<0.001	<0.001	<0.001
HCRC007	29	30	0.012		0.001	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC007	30	31	0.008		0.001	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC007	31	32	0.007		<0.001	<0.001	<0.001	<0.001	0.002	0.002
HCRC007	32	33	0.003		0.001	<0.001	<0.001	0.005	<0.001	0.008
HCRC007	33	34	0.004		<0.001	<0.001	<0.001	<0.001	0.002	<0.001
HCRC007	34	35	0.005		0.001	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC007	35	36	0.003		0.002	<0.001	<0.001	<0.001	<0.001	0.052
HCRC007	36	37	0.007		0.008	<0.001	0.001	<0.001	<0.001	0.015
HCRC007	37	38	0.009		0.005	<0.001	<0.001	0.004	0.004	0.002
HCRC007	38	39	0.013		0.012	<0.001	<0.001	<0.001	0.010	<0.001
HCRC007	39	40	0.011		0.047	<0.001	<0.001	<0.001	0.002	<0.001
HCRC007	40	41	0.026		0.397	<0.001	0.001	<0.001	0.008	0.046
HCRC007	41	42	0.036		0.265	0.002	0.001	<0.001	0.013	0.019
HCRC007	42	43	0.018		0.177	<0.001	0.002	<0.001	0.020	0.030
HCRC007	43	44	0.016		0.113	<0.001	0.002	<0.001	0.016	0.008
HCRC007	44	45	0.005		0.052	<0.001	<0.001	0.003	0.013	0.002
HCRC007	45	46	0.012		0.081	<0.001	<0.001	0.003	0.004	<0.001
HCRC007	46	47	0.004		0.019	<0.001	<0.001	<0.001	<0.001	0.008
HCRC007	47	48	0.008		0.048	<0.001	0.002	0.003	0.005	0.009
HCRC007	48	49	0.014		0.060	<0.001	0.001	<0.001	0.003	0.009
HCRC007	49	50	0.016		0.037	<0.001	<0.001	<0.001	0.006	0.008
HCRC008	0	1	No Sample							

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC008	1	2	0.003		0.006	<0.001	<0.001	<0.001	<0.001	0.002
HCRC008	2	3	0.010		0.005	<0.001	<0.001	<0.001	0.002	0.052
HCRC008	3	4	0.021		0.005	<0.001	<0.001	0.013	<0.001	0.010
HCRC008	4	5	0.012		0.024	<0.001	<0.001	<0.001	<0.001	0.006
HCRC008	5	6	0.011		0.071	<0.001	<0.001	<0.001	<0.001	0.006
HCRC008	6	7	0.012		0.076	<0.001	<0.001	<0.001	0.005	0.003
HCRC008	7	8	0.015		0.079	<0.001	0.002	0.004	0.005	0.003
HCRC008	8	9	0.034		0.088	<0.001	0.001	0.003	0.006	0.007
HCRC008	9	10	0.014		0.078	<0.001	0.001	<0.001	0.004	0.006
HCRC008	10	11	0.010		0.060	<0.001	<0.001	0.007	0.002	0.003
HCRC008	11	12	0.008		0.053	<0.001	<0.001	<0.001	0.004	0.002
HCRC008	12	13	0.010		0.039	<0.001	0.001	<0.001	0.006	0.004
HCRC008	13	14	0.013		0.006	<0.001	<0.001	<0.001	0.006	0.002
HCRC008	14	15	0.014		0.006	<0.001	<0.001	<0.001	0.005	0.003
HCRC008	15	16	0.009		0.015	<0.001	<0.001	<0.001	0.005	0.002
HCRC008	16	17	0.007		0.004	<0.001	<0.001	<0.001	0.006	<0.001
HCRC008	17	18	0.006		0.005	<0.001	<0.001	0.002	0.006	<0.001
HCRC008	18	19	0.006		0.003	<0.001	<0.001	<0.001	0.004	<0.001
HCRC008	19	20	0.006		0.002	<0.001	<0.001	<0.001	0.005	<0.001
HCRC008	20	21	0.010		0.009	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC008	21	22	0.010		0.003	<0.001	0.001	<0.001	0.002	<0.001
HCRC008	22	23	0.011		0.004	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC008	23	24	0.010		0.010	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC008	24	25	0.005		0.011	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC008	25	26	0.012		0.056	<0.001	0.001	<0.001	0.005	<0.001
HCRC008	26	27	0.021		0.117	<0.001	<0.001	<0.001	0.008	<0.001
HCRC008	27	28	0.010		0.021	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC008	28	29	0.010		0.038	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC008	29	30	0.024		0.095	<0.001	<0.001	<0.001	0.003	<0.001
HCRC008	30	31	0.021		0.138	<0.001	<0.001	<0.001	0.007	0.003
HCRC008	31	32	0.011		0.500	0.001	<0.001	<0.001	0.003	0.269
HCRC008	32	33	0.006		0.173	<0.001	<0.001	<0.001	<0.001	0.072
HCRC008	33	34	0.004		0.038	<0.001	<0.001	0.002	<0.001	0.030
HCRC008	34	35	0.005		0.112	<0.001	<0.001	<0.001	<0.001	0.130
HCRC008	35	36	0.008		0.151	<0.001	<0.001	<0.001	0.002	0.090
HCRC008	36	37	0.002		0.019	<0.001	<0.001	<0.001	<0.001	0.003
HCRC008	37	38	0.004		0.021	<0.001	<0.001	<0.001	0.002	<0.001
HCRC008	38	39	0.004		0.011	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC008	39	40	0.007		0.267	<0.001	<0.001	<0.001	0.005	0.026
HCRC008	40	41	0.008		0.165	<0.001	0.001	<0.001	0.009	0.021
HCRC008	41	42	0.008		0.154	<0.001	0.002	<0.001	0.002	0.125
HCRC008	42	43	0.003		0.052	<0.001	<0.001	<0.001	<0.001	0.066
HCRC008	43	44	0.003		0.047	<0.001	<0.001	<0.001	<0.001	0.102
HCRC008	44	45	0.009		0.394	0.001	<0.001	<0.001	0.002	0.263
HCRC008	45	46	0.010		0.134	<0.001	<0.001	<0.001	0.003	0.153
HCRC008	46	47	0.007		0.017	<0.001	<0.001	0.003	<0.001	0.003
HCRC008	47	48	0.005		0.018	<0.001	<0.001	0.002	<0.001	0.001
HCRC008	48	49	0.005		0.022	<0.001	<0.001	<0.001	0.002	<0.001
HCRC008	49	50	0.001		0.013	<0.001	<0.001	<0.001	0.003	<0.001
HCRC008	50	51	0.002		0.008	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC008	51	52	0.007		0.011	<0.001	0.001	0.002	0.002	0.003
HCRC008	52	53	0.003		0.032	<0.001	<0.001	<0.001	0.003	0.006
HCRC008	53	54	0.006		0.501	<0.001	0.002	0.006	<0.001	0.191

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC008	54	55	0.003		0.081	<0.001	<0.001	0.002	<0.001	0.041
HCRC008	55	56	0.004		0.015	<0.001	0.002	<0.001	0.002	0.002
HCRC008	56	57	0.003		0.013	<0.001	0.001	<0.001	0.002	0.002
HCRC008	57	58	0.002		0.009	<0.001	<0.001	<0.001	0.002	0.001
HCRC008	58	59	0.001		0.041	<0.001	<0.001	<0.001	<0.001	0.015
HCRC008	59	60	0.004		0.067	<0.001	<0.001	<0.001	0.002	0.054
HCRC008	60	61	0.007		0.224	0.002	0.002	<0.001	0.005	0.229
HCRC008	61	62	0.008		0.329	0.006	0.003	0.010	0.003	0.176
HCRC008	62	63	0.009		0.394	0.002	0.003	<0.001	0.006	0.158
HCRC008	63	64	0.004		0.050	<0.001	<0.001	<0.001	0.005	0.020
HCRC008	64	65	0.007		0.016	<0.001	0.001	<0.001	0.002	0.003
HCRC008	65	66	0.004		0.016	<0.001	<0.001	<0.001	<0.001	0.002
HCRC008	66	67	0.004		0.010	<0.001	0.002	<0.001	<0.001	0.002
HCRC008	67	68	0.004		0.007	<0.001	0.001	<0.001	0.002	0.002
HCRC008	68	69	0.004		0.007	<0.001	0.001	<0.001	<0.001	0.010
HCRC008	69	70	0.002		0.028	0.003	<0.001	<0.001	<0.001	0.527
HCRC008	70	71	0.001		0.022	0.002	<0.001	<0.001	0.002	0.561
HCRC008	71	72	0.004		0.014	0.002	0.002	<0.001	<0.001	0.299
HCRC008	72	73	0.003		0.019	<0.001	0.001	<0.001	0.002	0.189
HCRC008	73	74	0.003		0.024	0.003	<0.001	0.002	<0.001	0.387
HCRC008	74	75	0.003		0.014	<0.001	0.002	<0.001	<0.001	0.238
HCRC008	75	76	0.003		0.003	<0.001	<0.001	0.003	0.003	0.007
HCRC008	76	77	0.004		0.005	<0.001	0.002	<0.001	0.003	0.006
HCRC008	77	78	0.005		0.035	<0.001	0.005	<0.001	<0.001	0.067
HCRC008	78	79	0.004		0.036	0.004	0.001	<0.001	0.002	0.465
HCRC008	79	80	0.002		0.037	0.003	<0.001	0.002	<0.001	0.518
HCRC008	80	81	0.003		0.010	<0.001	<0.001	<0.001	<0.001	0.227
HCRC008	81	82	0.003		0.010	<0.001	0.001	<0.001	0.002	0.190
HCRC008	82	83	0.006		0.076	0.002	0.002	<0.001	0.004	0.566
HCRC008	83	84	0.010		0.134	0.001	0.002	<0.001	0.002	0.200
HCRC008	84	85	0.004		0.023	0.002	<0.001	<0.001	<0.001	0.391
HCRC008	85	86	0.005		0.112	0.003	<0.001	<0.001	<0.001	0.467
HCRC008	86	87	0.003		0.030	<0.001	<0.001	<0.001	0.002	0.074
HCRC008	87	88	0.002		0.008	0.001	<0.001	0.006	<0.001	0.406
HCRC008	88	89	0.009		0.098	0.006	0.002	<0.001	0.002	0.718
HCRC008	89	90	0.009		0.056	0.004	<0.001	<0.001	<0.001	0.235
HCRC008	90	91	0.003		0.004	0.001	0.001	<0.001	<0.001	0.119
HCRC008	91	92	0.003		0.003	0.001	<0.001	<0.001	<0.001	0.255
HCRC008	92	93	0.002		0.005	0.004	<0.001	<0.001	<0.001	0.584
HCRC008	93	94	0.002		0.005	0.002	0.002	0.002	0.002	0.276
HCRC008	94	95	0.003		0.044	<0.001	0.002	<0.001	<0.001	0.062
HCRC008	95	96	0.002		0.042	0.001	0.002	0.003	<0.001	0.212
HCRC008	96	97	0.003		0.040	<0.001	0.002	0.001	0.002	0.300
HCRC008	97	98	0.007		0.060	0.003	0.001	<0.001	0.002	0.243
HCRC008	98	99	0.084		0.088	0.002	0.001	<0.001	<0.001	0.150
HCRC008	99	100	0.014		0.026	0.001	0.001	0.003	0.003	0.031
HCRC009	0	1	No Sample							
HCRC009	1	2	0.040		0.035	0.001	0.003	<0.001	0.013	0.008
HCRC009	2	3	0.024		0.058	0.001	0.003	0.002	0.008	0.011
HCRC009	3	4	0.013		0.134	<0.001	0.003	<0.001	<0.001	0.019
HCRC009	4	5	0.016		0.207	<0.001	0.002	<0.001	0.002	0.009
HCRC009	5	6	0.037		0.267	<0.001	0.004	<0.001	0.002	0.005
HCRC009	6	7	0.037		0.113	<0.001	0.004	<0.001	0.006	0.005

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC009	7	8	0.035		0.215	<0.001	0.004	<0.001	0.008	0.005
HCRC009	8	9	0.013		0.245	<0.001	0.003	<0.001	<0.001	0.008
HCRC009	9	10	0.023		0.220	<0.001	0.003	0.001	0.007	0.006
HCRC009	10	11	0.025		0.294	<0.001	0.002	<0.001	0.002	0.007
HCRC009	11	12	0.035		0.183	<0.001	0.003	0.003	0.003	0.006
HCRC009	12	13	0.074		0.255	0.002	0.018	0.002	0.010	0.006
HCRC009	13	14	0.083		0.123	0.002	0.010	<0.001	0.031	0.005
HCRC009	14	15	0.070		0.099	0.003	0.005	<0.001	0.008	0.003
HCRC009	15	16	0.052		0.165	0.002	0.004	<0.001	0.014	0.001
HCRC009	16	17	0.055		0.384	<0.001	<0.001	<0.001	0.005	0.004
HCRC009	17	18	0.028		0.373	<0.001	0.002	<0.001	0.010	0.003
HCRC009	18	19	0.048		0.328	0.001	0.002	<0.001	0.010	0.003
HCRC009	19	20	0.030		0.113	<0.001	<0.001	0.001	0.006	0.005
HCRC009	20	21	0.055		0.083	0.001	0.004	<0.001	0.005	0.007
HCRC009	21	22	0.049		0.129	0.001	0.006	<0.001	0.008	0.001
HCRC009	22	23	0.060		0.196	<0.001	0.005	<0.001	0.006	0.002
HCRC009	23	24	0.077		0.248	<0.001	0.003	<0.001	0.004	<0.001
HCRC009	24	25	0.063		0.152	<0.001	0.004	0.008	0.005	0.002
HCRC009	25	26	0.032		0.068	<0.001	0.003	0.003	0.004	0.002
HCRC009	26	27	0.012		0.022	<0.001	<0.001	0.003	<0.001	0.002
HCRC009	27	28	0.026		0.025	<0.001	0.002	<0.001	0.003	0.001
HCRC009	28	29	0.035		0.031	0.001	0.003	0.001	0.014	0.001
HCRC009	29	30	0.017		0.047	0.001	0.002	0.005	0.009	<0.001
HCRC009	30	31	0.013		0.051	<0.001	0.003	0.001	0.009	<0.001
HCRC009	31	32	0.012		0.028	<0.001	0.002	0.004	0.058	0.001
HCRC009	32	33	0.015		0.040	0.003	0.003	0.003	0.006	0.002
HCRC009	33	34	0.037		0.050	0.001	0.008	0.005	0.005	0.003
HCRC009	34	35	0.099		0.064	0.005	0.014	0.001	0.012	0.002
HCRC009	35	36	0.030		0.105	0.003	0.007	<0.001	0.004	0.002
HCRC009	36	37	0.049		0.072	0.003	0.003	0.002	0.008	<0.001
HCRC009	37	38	0.029		0.156	0.006	0.005	0.001	0.010	<0.001
HCRC009	38	39	0.034		0.068	0.003	0.004	0.011	0.008	<0.001
HCRC009	39	40	0.023		0.056	0.003	0.004	0.002	0.006	<0.001
HCRC009	40	41	0.021		0.046	0.002	0.003	0.004	0.006	0.001
HCRC009	41	42	0.015		0.020	<0.001	0.002	0.004	0.006	<0.001
HCRC009	42	43	0.009		0.010	<0.001	0.002	<0.001	0.006	0.003
HCRC009	43	44	0.006		0.006	<0.001	0.003	<0.001	<0.001	0.006
HCRC009	44	45	0.003		0.005	<0.001	0.001	0.002	<0.001	0.007
HCRC009	45	46	0.009		0.017	0.001	0.002	0.004	0.002	0.006
HCRC009	46	47	0.026		0.049	0.001	0.003	0.002	0.006	0.004
HCRC009	47	48	0.009		0.020	<0.001	0.002	0.001	0.002	0.003
HCRC009	48	49	0.012		0.013	<0.001	0.001	0.004	0.002	0.002
HCRC009	49	50	0.030		0.007	<0.001	0.002	<0.001	0.005	0.005
HCRC009	50	51	0.006		0.015	<0.001	0.001	<0.001	0.004	0.003
HCRC009	51	52	0.005		0.011	0.002	0.002	<0.001	0.003	0.002
HCRC009	52	53	0.010		0.011	<0.001	0.002	0.002	0.009	0.004
HCRC009	53	54	0.007		0.011	<0.001	0.003	0.006	0.002	0.003
HCRC009	54	55	0.007		0.006	0.001	0.003	<0.001	0.003	0.003
HCRC009	55	56	0.201		0.005	0.005	0.001	0.003	0.006	0.002
HCRC009	56	57	0.009		0.006	<0.001	0.003	0.002	0.005	0.003
HCRC009	57	58	0.010		0.045	0.003	0.001	<0.001	0.005	0.007
HCRC009	58	59	0.017		0.055	0.003	0.003	0.002	0.006	0.020
HCRC009	59	60	0.013		0.012	0.001	0.002	<0.001	0.004	0.010

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC009	60	61	0.019		0.011	0.001	<0.001	0.004	<0.001	0.011
HCRC009	61	62	0.007		0.006	<0.001	<0.001	0.009	0.004	0.005
HCRC009	62	63	0.002		0.015	<0.001	<0.001	<0.001	0.002	0.004
HCRC009	63	64	0.004		0.018	<0.001	<0.001	<0.001	0.006	0.008
HCRC009	64	65	0.004		0.009	<0.001	<0.001	0.005	0.005	0.003
HCRC009	65	66	0.004		0.006	<0.001	<0.001	<0.001	0.006	0.003
HCRC009	66	67	0.009		0.013	<0.001	0.008	0.004	0.005	0.007
HCRC009	67	68	0.003		0.007	<0.001	<0.001	<0.001	0.005	0.003
HCRC009	68	69	0.003		0.003	<0.001	<0.001	0.004	0.004	0.002
HCRC009	69	70	0.006		0.006	<0.001	0.003	0.004	0.002	0.004
HCRC009	70	71	0.013		0.039	<0.001	0.003	0.002	0.003	0.010
HCRC009	71	72	0.020		0.007	0.007	<0.001	0.004	0.004	0.017
HCRC009	72	73	0.016		0.003	0.004	<0.001	<0.001	0.007	0.015
HCRC009	73	74	1.186		0.002	0.005	0.002	0.008	0.005	0.009
HCRC009	74	75	0.143		0.003	0.003	0.001	0.001	0.002	0.008
HCRC009	75	76	0.028		0.124	0.003	0.004	0.004	0.008	0.073
HCRC009	76	77	0.015		0.018	0.004	0.002	<0.001	0.004	0.009
HCRC009	77	78	0.005		0.066	0.007	<0.001	0.004	<0.001	0.022
HCRC009	78	79	0.011		0.026	0.003	0.002	0.003	<0.001	0.011
HCRC009	79	80	0.023		0.012	0.006	0.002	0.003	0.004	0.013
HCRC009	80	81	0.094		0.002	0.006	<0.001	0.006	0.002	0.006
HCRC009	81	82	0.040		0.002	0.006	<0.001	0.003	0.003	0.008
HCRC009	82	83	0.036		0.011	0.002	<0.001	0.002	0.002	0.005
HCRC009	83	84	0.023		0.005	0.006	0.002	0.007	0.003	0.007
HCRC009	84	85	1.708		0.005	0.048	0.002	0.005	0.002	0.036
HCRC009	85	86	0.099		0.001	0.008	0.003	0.005	0.008	0.013
HCRC009	86	87	0.208		0.019	0.009	0.003	0.004	0.006	0.019
HCRC009	87	88	0.022		0.040	0.004	0.003	0.005	0.002	0.015
HCRC009	88	89	0.065		0.075	0.020	0.008	0.002	0.006	0.043
HCRC009	89	90	0.067		0.004	0.004	0.001	0.004	0.007	0.002
HCRC009	90	91	0.054		0.002	0.009	0.002	0.004	0.004	0.004
HCRC009	91	92	1.162		0.003	0.143	0.003	<0.001	0.004	0.025
HCRC009	92	93	0.105		0.002	0.015	<0.001	0.003	0.005	0.004
HCRC009	93	94	0.036		<0.001	0.007	0.001	<0.001	0.006	0.006
HCRC009	94	95	0.096		0.001	0.003	<0.001	<0.001	0.002	0.005
HCRC009	95	96	0.025		0.004	0.003	0.001	<0.001	0.003	0.009
HCRC009	96	97	0.009		0.003	0.004	0.003	<0.001	0.004	0.011
HCRC009	97	98	0.263		0.002	0.004	0.002	0.003	0.005	0.011
HCRC009	98	99	0.043		0.001	0.003	0.002	<0.001	0.002	0.007
HCRC009	99	100	0.009		0.003	<0.001	0.002	0.001	0.005	<0.001
HCRC010	0	1	0.115		0.012	0.003	0.009	<0.001	0.006	0.006
HCRC010	1	2	0.040		0.008	0.001	0.004	<0.001	0.007	0.005
HCRC010	2	3	0.041		0.011	<0.001	0.010	<0.001	0.006	0.004
HCRC010	3	4	0.325		0.014	0.005	0.007	<0.001	0.007	0.023
HCRC010	4	5	8.679		0.043	0.019	0.030	0.003	0.013	0.030
HCRC010	5	6	0.132		0.008	0.006	0.003	<0.001	0.004	0.019
HCRC010	6	7	0.092		0.007	<0.001	0.008	<0.001	0.003	0.010
HCRC010	7	8	0.068		0.009	<0.001	0.005	0.003	0.010	0.007
HCRC010	8	9	0.087		0.014	<0.001	0.004	0.005	0.013	0.007
HCRC010	9	10	0.070		0.008	<0.001	0.003	0.004	0.012	0.019
HCRC010	10	11	0.060		0.012	0.001	0.003	<0.001	0.006	0.019
HCRC010	11	12	0.045		0.010	<0.001	0.004	0.004	0.006	0.015
HCRC010	12	13	0.046		0.012	<0.001	0.004	0.003	0.003	0.021

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC010	13	14	0.035		0.017	0.002	0.005	<0.001	<0.001	0.016
HCRC010	14	15	0.030		0.009	0.001	0.003	<0.001	0.006	0.018
HCRC010	15	16	0.036		0.008	0.001	0.002	<0.001	0.003	0.010
HCRC010	16	17	0.107		0.037	0.004	0.010	<0.001	0.008	0.007
HCRC010	17	18	0.034		0.039	<0.001	0.002	0.005	0.005	<0.001
HCRC010	18	19	0.045		0.033	<0.001	0.003	0.002	0.004	<0.001
HCRC010	19	20	0.058		0.029	<0.001	0.003	<0.001	0.006	<0.001
HCRC010	20	21	0.044		0.025	<0.001	0.004	<0.001	0.007	<0.001
HCRC010	21	22	0.033		0.022	<0.001	0.003	<0.001	0.007	<0.001
HCRC010	22	23	0.043		0.024	0.001	0.005	<0.001	0.004	<0.001
HCRC010	23	24	0.033		0.023	<0.001	0.007	<0.001	0.006	<0.001
HCRC010	24	25	0.033		0.020	<0.001	0.007	<0.001	0.009	<0.001
HCRC010	25	26	0.029		0.028	<0.001	0.011	0.002	0.002	<0.001
HCRC010	26	27	0.031		0.033	<0.001	0.006	<0.001	0.005	<0.001
HCRC010	27	28	0.044		0.048	<0.001	0.008	<0.001	0.005	<0.001
HCRC010	28	29	0.038		0.074	<0.001	0.004	0.002	0.006	<0.001
HCRC010	29	30	0.037		0.052	<0.001	0.004	<0.001	0.006	<0.001
HCRC010	30	31	0.023		0.035	<0.001	0.002	<0.001	0.004	<0.001
HCRC010	31	32	0.024		0.038	<0.001	0.020	0.010	0.006	<0.001
HCRC010	32	33	0.021		0.049	<0.001	0.016	<0.001	0.005	<0.001
HCRC010	33	34	0.022		0.048	0.001	0.002	0.004	0.004	<0.001
HCRC010	34	35	0.024		0.077	<0.001	0.029	0.003	0.010	<0.001
HCRC010	35	36	0.028		0.062	<0.001	0.011	<0.001	0.010	<0.001
HCRC010	36	37	0.020		0.026	<0.001	0.016	<0.001	0.006	<0.001
HCRC010	37	38	0.016		0.022	<0.001	0.009	<0.001	0.004	<0.001
HCRC010	38	39	0.023		0.023	<0.001	0.007	<0.001	0.006	<0.001
HCRC010	39	40	0.033		0.044	<0.001	0.013	<0.001	0.005	<0.001
HCRC010	40	41	0.035		0.048	0.001	0.004	0.005	0.005	<0.001
HCRC010	41	42	0.148		0.035	0.003	0.008	<0.001	0.013	0.003
HCRC010	42	43	0.034		0.009	0.001	0.007	<0.001	0.024	0.009
HCRC010	43	44	0.020		0.006	<0.001	0.003	<0.001	0.005	0.009
HCRC010	44	45	0.023		0.010	<0.001	0.003	<0.001	0.006	0.006
HCRC010	45	46	0.036		0.007	0.002	0.005	<0.001	0.009	<0.001
HCRC010	46	47	0.024		0.017	0.001	0.004	<0.001	0.006	<0.001
HCRC010	47	48	0.015		0.014	<0.001	0.003	<0.001	0.002	<0.001
HCRC010	48	49	0.014		0.011	0.001	0.001	<0.001	<0.001	0.002
HCRC010	49	50	0.551		0.013	0.022	0.007	<0.001	0.005	0.002
HCRC010	50	51	0.261		0.004	0.009	0.004	<0.001	0.006	<0.001
HCRC010	51	52	0.033		0.003	<0.001	0.001	<0.001	0.002	<0.001
HCRC010	52	53	0.027		0.006	<0.001	<0.001	0.002	0.003	<0.001
HCRC010	53	54	0.022		0.011	0.001	0.004	<0.001	0.004	0.002
HCRC010	54	55	0.011		0.002	0.001	<0.001	<0.001	0.002	<0.001
HCRC010	55	56	0.012		0.003	0.004	0.001	<0.001	0.002	0.005
HCRC010	56	57	0.012		0.004	0.003	0.001	<0.001	<0.001	0.005
HCRC010	57	58	0.013		0.003	0.003	0.003	<0.001	0.002	0.012
HCRC010	58	59	0.015		0.002	0.001	0.002	<0.001	0.006	0.011
HCRC010	59	60	0.060		0.011	0.011	0.017	<0.001	0.017	0.022
HCRC010	60	61	0.064		0.016	0.017	0.006	0.003	0.022	0.018
HCRC010	61	62	0.316		0.008	0.006	0.002	<0.001	0.006	0.002
HCRC010	62	63	0.166		0.019	0.005	0.004	<0.001	0.009	0.006
HCRC010	63	64	0.076		0.011	0.006	0.003	<0.001	0.008	0.012
HCRC010	64	65	0.010		0.017	0.001	0.002	<0.001	0.003	0.004
HCRC010	65	66	0.033		0.012	0.001	0.003	<0.001	0.010	0.005

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC010	66	67	0.045		0.005	0.001	0.002	0.003	0.008	<0.001
HCRC010	67	68	0.013		0.004	0.003	0.003	0.001	0.006	0.003
HCRC010	68	69	0.014		0.005	0.003	0.002	0.001	<0.001	0.004
HCRC010	69	70	0.016		0.005	0.002	0.002	<0.001	0.007	0.009
HCRC010	70	71	0.045		0.009	0.006	0.005	0.002	0.015	0.039
HCRC010	71	72	0.022		0.006	0.004	0.003	<0.001	0.005	0.019
HCRC010	72	73	0.022		0.003	0.004	0.004	0.001	0.002	0.018
HCRC010	73	74	0.015		0.003	0.003	0.004	<0.001	0.005	0.016
HCRC010	74	75	0.011		0.003	0.003	<0.001	<0.001	0.002	0.018
HCRC010	75	76	0.020		0.008	0.005	0.004	<0.001	0.005	0.030
HCRC010	76	77	0.019		0.005	0.006	0.004	<0.001	0.008	0.017
HCRC010	77	78	0.039		0.022	0.003	0.004	0.003	0.006	0.032
HCRC010	78	79	0.051		0.006	0.003	0.002	<0.001	0.006	0.011
HCRC010	79	80	0.021		0.003	0.003	0.003	0.004	0.005	0.018
HCRC010	80	81	0.014		0.004	0.003	0.002	0.001	0.007	0.021
HCRC010	81	82	0.014		0.003	0.003	0.003	0.002	0.010	0.021
HCRC010	82	83	0.018		0.004	0.005	0.002	0.001	0.006	0.022
HCRC010	83	84	0.008		0.002	0.005	<0.001	<0.001	0.002	0.009
HCRC010	84	85	0.007		0.002	0.003	0.001	<0.001	0.002	0.010
HCRC010	85	86	0.011		0.002	0.005	<0.001	<0.001	0.004	0.007
HCRC010	86	87	0.010		0.008	0.002	0.002	<0.001	0.007	0.009
HCRC010	87	88	0.015		0.005	0.005	0.003	<0.001	0.006	0.009
HCRC010	88	89	0.009		0.008	0.001	0.003	<0.001	0.006	0.006
HCRC010	89	90	0.009		0.010	<0.001	0.003	<0.001	<0.001	0.007
HCRC010	90	91	0.012		0.007	0.001	0.002	0.006	0.006	0.004
HCRC010	91	92	0.006		0.006	0.002	0.002	<0.001	0.005	0.004
HCRC010	92	93	0.004		0.002	0.001	0.001	<0.001	0.004	0.003
HCRC010	93	94	0.005		0.002	0.001	0.001	0.001	0.004	0.002
HCRC010	94	95	0.005		0.004	<0.001	<0.001	<0.001	0.002	<0.001
HCRC010	95	96	0.007		0.006	<0.001	<0.001	<0.001	0.007	<0.001
HCRC010	96	97	0.008		0.007	<0.001	0.002	0.001	0.007	0.002
HCRC010	97	98	0.016		0.005	<0.001	<0.001	<0.001	0.002	<0.001
HCRC010	98	99	0.012		0.012	0.001	<0.001	<0.001	0.006	0.004
HCRC010	99	100	0.011		0.018	0.001	0.002	0.002	0.005	0.005
HCRC011	0	1	No Sample							
HCRC011	1	2	0.537		0.010	0.006	0.010	<0.001	0.010	0.008
HCRC011	2	3	0.087		0.006	0.001	0.004	<0.001	0.003	0.007
HCRC011	3	4	0.018		0.006	<0.001	0.001	0.002	0.004	<0.001
HCRC011	4	5	0.020		0.008	<0.001	0.003	<0.001	0.002	<0.001
HCRC011	5	6	0.016		0.009	<0.001	<0.001	<0.001	0.002	<0.001
HCRC011	6	7	0.026		0.009	<0.001	0.006	<0.001	0.002	<0.001
HCRC011	7	8	0.015		0.007	<0.001	<0.001	<0.001	0.004	<0.001
HCRC011	8	9	0.011		0.004	<0.001	0.001	<0.001	0.004	<0.001
HCRC011	9	10	0.020		0.006	<0.001	<0.001	<0.001	0.003	0.005
HCRC011	10	11	0.022		0.005	<0.001	0.001	0.003	0.004	0.005
HCRC011	11	12	0.025		0.004	<0.001	0.001	<0.001	<0.001	0.002
HCRC011	12	13	0.026		0.004	<0.001	0.003	<0.001	0.002	0.006
HCRC011	13	14	0.022		0.004	<0.001	<0.001	<0.001	0.002	0.001
HCRC011	14	15	0.072		0.005	<0.001	0.002	<0.001	0.002	<0.001
HCRC011	15	16	0.016		0.005	<0.001	0.001	<0.001	0.002	<0.001
HCRC011	16	17	0.051		0.021	0.003	0.002	<0.001	0.011	<0.001
HCRC011	17	18	0.016		0.013	<0.001	<0.001	0.004	0.003	<0.001
HCRC011	18	19	0.015		0.014	<0.001	0.001	<0.001	0.002	<0.001

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC011	19	20	0.021		0.011	<0.001	0.001	0.008	0.004	<0.001
HCRC011	20	21	0.020		0.017	<0.001	<0.001	<0.001	0.002	<0.001
HCRC011	21	22	0.022		0.007	<0.001	0.002	<0.001	0.007	<0.001
HCRC011	22	23	0.052		0.021	0.002	0.003	<0.001	0.006	<0.001
HCRC011	23	24	0.033		0.019	0.001	0.002	<0.001	<0.001	<0.001
HCRC011	24	25	0.038		0.035	0.001	0.004	0.002	0.006	<0.001
HCRC011	25	26	0.022		0.043	<0.001	0.002	<0.001	0.005	<0.001
HCRC011	26	27	0.015		0.022	<0.001	0.002	0.003	0.005	<0.001
HCRC011	27	28	0.016		0.016	<0.001	<0.001	<0.001	0.007	<0.001
HCRC011	28	29	0.008		0.008	<0.001	<0.001	<0.001	0.003	<0.001
HCRC011	29	30	0.007		0.006	<0.001	<0.001	<0.001	0.003	<0.001
HCRC011	30	31	0.050		0.007	<0.001	<0.001	<0.001	0.005	<0.001
HCRC011	31	32	0.043		0.011	0.001	0.002	0.002	0.004	<0.001
HCRC011	32	33	0.061		0.029	0.003	0.003	<0.001	0.008	<0.001
HCRC011	33	34	0.034		0.021	0.003	0.002	0.002	0.006	<0.001
HCRC011	34	35	0.032		0.018	<0.001	0.003	<0.001	0.008	<0.001
HCRC011	35	36	0.042		0.028	0.003	0.006	<0.001	0.005	<0.001
HCRC011	36	37	0.024		0.012	0.001	0.012	0.002	0.006	<0.001
HCRC011	37	38	0.112		0.030	0.002	0.018	<0.001	0.014	<0.001
HCRC011	38	39	0.086		0.013	0.003	0.006	<0.001	0.009	<0.001
HCRC011	39	40	0.020		0.004	0.001	0.003	<0.001	0.006	<0.001
HCRC011	40	41	0.021		0.004	0.001	0.004	0.004	0.006	<0.001
HCRC011	41	42	0.014		0.004	0.002	0.003	<0.001	0.005	0.001
HCRC011	42	43	0.017		0.005	0.002	0.003	<0.001	0.005	<0.001
HCRC011	43	44	0.190		0.011	0.003	0.003	0.002	0.009	0.003
HCRC011	44	45	0.012		0.006	<0.001	0.002	<0.001	0.002	<0.001
HCRC011	45	46	0.010		0.006	<0.001	0.005	<0.001	0.002	<0.001
HCRC011	46	47	0.007		0.006	<0.001	0.002	<0.001	0.002	<0.001
HCRC011	47	48	0.037		0.008	0.003	0.015	0.002	0.004	0.003
HCRC011	48	49	0.018		0.024	0.006	0.018	<0.001	0.008	0.068
HCRC011	49	50	0.009		0.006	<0.001	0.003	<0.001	0.006	0.006
HCRC011	50	51	0.020		0.006	0.003	0.005	0.004	0.006	0.005
HCRC011	51	52	0.010		0.006	0.002	0.003	<0.001	0.003	<0.001
HCRC011	52	53	0.677		0.019	0.009	0.006	0.003	0.010	0.007
HCRC011	53	54	0.062		0.011	0.003	0.003	0.002	0.012	0.003
HCRC011	54	55	0.548		0.012	0.011	0.009	0.003	0.009	0.009
HCRC011	55	56	1.391		0.017	0.030	0.032	<0.001	0.035	0.006
HCRC011	56	57	0.066		0.016	0.001	0.002	0.004	0.005	<0.001
HCRC011	57	58	0.028		0.013	0.001	0.002	<0.001	0.004	0.002
HCRC011	58	59	0.013		0.008	0.001	0.003	<0.001	0.005	0.002
HCRC011	59	60	0.016		0.002	0.001	0.002	<0.001	0.004	<0.001
HCRC011	60	61	0.019		0.003	0.001	0.004	0.003	0.003	0.001
HCRC011	61	62	0.092		0.054	0.043	0.017	<0.001	0.005	0.046
HCRC011	62	63	0.305		0.378	0.086	0.069	0.003	0.009	0.176
HCRC011	63	64	0.752		0.186	0.013	0.101	<0.001	0.031	0.129
HCRC011	64	65	0.111		0.024	0.006	0.014	<0.001	0.010	0.019
HCRC011	65	66	0.022		0.003	0.003	0.003	<0.001	0.006	0.004
HCRC011	66	67	0.015		0.011	0.008	0.003	<0.001	0.006	0.006
HCRC011	67	68	0.123		0.075	0.010	0.007	<0.001	0.008	0.025
HCRC011	68	69	0.045		0.083	0.005	0.006	0.001	0.008	0.031
HCRC011	69	70	0.187		0.145	0.007	0.008	0.001	0.007	0.053
HCRC011	70	71	0.207		0.155	0.017	0.009	<0.001	0.006	0.060
HCRC011	71	72	0.091		0.727	0.011	0.072	<0.001	0.017	0.223

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC011	72	73	0.098		0.350	0.006	0.022	<0.001	0.012	0.115
HCRC011	73	74	0.066		3.297	0.010	0.245	<0.001	0.037	0.939
HCRC011	74	75	0.009		0.027	<0.001	0.004	<0.001	0.006	0.007
HCRC011	75	76	0.010		0.039	0.001	0.005	<0.001	0.013	0.009
HCRC011	76	77	0.240		0.026	0.010	0.010	0.006	0.010	0.013
HCRC011	77	78	0.025		0.129	0.002	0.013	<0.001	0.010	0.043
HCRC011	78	79	0.195		0.015	0.008	0.007	<0.001	0.012	0.016
HCRC011	79	80	0.010		0.015	0.003	0.003	<0.001	0.003	0.006
HCRC011	80	81	0.010		0.011	0.008	0.003	<0.001	<0.001	0.008
HCRC011	81	82	0.010		0.011	0.004	0.003	<0.001	0.007	0.003
HCRC011	82	83	0.009		0.014	0.002	0.004	<0.001	0.006	0.002
HCRC011	83	84	0.011		0.009	<0.001	0.002	0.001	0.005	0.002
HCRC011	84	85	0.055		0.014	0.005	0.002	<0.001	0.005	0.005
HCRC011	85	86	0.080		0.019	0.008	0.008	<0.001	0.003	0.020
HCRC011	86	87	0.038		1.622	0.006	0.017	0.001	0.036	0.483
HCRC011	87	88	0.689		1.090	0.008	0.025	<0.001	0.024	0.332
HCRC011	88	89	0.056		0.355	0.004	0.014	<0.001	0.009	0.130
HCRC011	89	90	0.036		0.477	0.005	0.015	<0.001	0.011	0.162
HCRC011	90	91	0.024		0.191	0.003	0.008	0.006	0.007	0.061
HCRC011	91	92	0.012		0.019	0.001	0.003	<0.001	0.007	0.004
HCRC011	92	93	0.010		0.008	0.002	0.004	<0.001	0.009	0.003
HCRC011	93	94	0.024		0.023	0.001	0.006	<0.001	0.013	0.003
HCRC011	94	95	0.018		0.011	0.001	0.003	<0.001	0.006	<0.001
HCRC011	95	96	0.020		0.030	0.001	0.004	<0.001	0.007	<0.001
HCRC011	96	97	0.040		0.049	0.002	0.007	0.002	0.008	0.002
HCRC011	97	98	0.208		0.028	0.004	0.006	<0.001	0.009	<0.001
HCRC011	98	99	0.035		0.130	0.001	0.007	0.004	0.009	0.033
HCRC011	99	100	0.037		0.529	0.005	0.013	<0.001	0.006	0.160
HCRC012	0	1	No Sample							
HCRC012	1	2	0.031		0.020	<0.001	0.005	<0.001	0.005	0.007
HCRC012	2	3	0.031		0.019	0.005	0.014	0.006	0.014	0.024
HCRC012	3	4	0.035		0.032	0.003	0.006	0.002	0.006	0.016
HCRC012	4	5	0.038		0.047	0.001	0.013	<0.001	0.004	0.009
HCRC012	5	6	0.038		0.047	<0.001	0.003	0.003	0.006	0.013
HCRC012	6	7	0.031		0.031	<0.001	0.003	0.005	0.002	0.009
HCRC012	7	8	0.029		0.038	<0.001	0.006	0.005	0.004	0.010
HCRC012	8	9	0.032		0.041	0.001	0.010	0.005	0.003	0.008
HCRC012	9	10	0.011		0.030	<0.001	0.005	<0.001	0.003	0.002
HCRC012	10	11	0.007		0.023	0.001	0.015	<0.001	0.006	<0.001
HCRC012	11	12	0.008		0.019	<0.001	0.006	<0.001	0.006	<0.001
HCRC012	12	13	0.027		0.033	0.007	0.030	<0.001	0.005	0.001
HCRC012	13	14	0.024		0.024	0.003	0.007	0.006	0.005	<0.001
HCRC012	14	15	0.023		0.022	0.004	0.004	0.004	0.009	<0.001
HCRC012	15	16	0.019		0.029	0.003	0.003	0.003	0.006	0.002
HCRC012	16	17	0.014		0.054	0.003	0.003	0.005	0.008	0.004
HCRC012	17	18	0.042		0.088	0.003	0.004	<0.001	0.008	0.011
HCRC012	18	19	0.024		0.036	<0.001	0.006	0.002	0.005	0.010
HCRC012	19	20	0.047		0.160	0.008	0.006	<0.001	0.010	0.011
HCRC012	20	21	0.079		0.084	0.010	0.018	<0.001	0.011	0.006
HCRC012	21	22	0.046		0.257	0.012	0.007	<0.001	0.020	0.008
HCRC012	22	23	0.346		0.077	0.008	0.011	0.005	0.017	0.003
HCRC012	23	24	No Sample							
HCRC012	24	25	0.054		0.024	0.003	0.008	0.004	0.020	0.001

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC012	25	26	0.046		0.010	0.003	0.126	<0.001	0.010	<0.001
HCRC012	26	27	0.060		0.009	0.001	0.019	0.005	0.014	<0.001
HCRC012	27	28	0.434		0.015	0.004	0.005	<0.001	0.009	<0.001
HCRC012	28	29	0.056		0.016	0.001	0.004	<0.001	0.007	0.001
HCRC012	29	30	0.022		0.015	0.001	0.004	0.004	0.007	0.001
HCRC012	30	31	0.024		0.011	0.003	0.029	0.002	0.007	<0.001
HCRC012	31	32	0.021		0.018	0.002	0.010	0.007	0.009	<0.001
HCRC012	32	33	0.020		0.016	0.002	0.005	0.001	0.008	<0.001
HCRC012	33	34	0.063		0.054	0.006	0.011	0.004	0.002	<0.001
HCRC012	34	35	0.015		0.009	0.002	0.007	<0.001	0.003	<0.001
HCRC012	35	36	0.012		0.035	0.001	0.003	0.002	0.006	<0.001
HCRC012	36	37	0.034		0.030	<0.001	0.004	0.003	0.007	0.005
HCRC012	37	38	0.012		0.015	<0.001	0.002	<0.001	0.003	<0.001
HCRC012	38	39	0.017		0.018	0.001	0.002	<0.001	0.002	<0.001
HCRC012	39	40	0.013		0.010	0.002	0.003	0.009	0.002	<0.001
HCRC012	40	41	0.015		0.008	0.003	0.003	0.001	0.002	0.002
HCRC012	41	42	0.111		0.009	0.007	0.003	0.002	0.003	0.004
HCRC012	42	43	0.014		0.024	0.003	0.004	<0.001	0.006	0.015
HCRC012	43	44	0.070		1.865	0.012	0.099	0.004	0.019	0.536
HCRC012	44	45	0.039		2.332	0.015	0.150	0.006	0.030	0.679
HCRC012	45	46	0.064		1.605	0.013	0.150	<0.001	0.026	0.484
HCRC012	46	47	0.059		0.798	0.012	0.132	0.002	0.016	0.268
HCRC012	47	48	0.028		0.114	0.017	0.043	<0.001	0.007	0.055
HCRC012	48	49	0.016		0.005	0.007	0.002	<0.001	0.009	0.002
HCRC012	49	50	0.014		0.007	0.007	0.002	0.004	0.009	0.005
HCRC012	50	51	0.013		0.005	0.006	0.002	<0.001	0.003	0.003
HCRC012	51	52	0.006		0.005	0.006	0.002	<0.001	0.003	<0.001
HCRC012	52	53	0.010		0.010	0.007	0.002	0.002	0.007	0.011
HCRC012	53	54	0.014		0.012	0.002	0.002	0.004	0.004	0.007
HCRC012	54	55	0.009		0.007	0.003	0.002	0.007	0.002	0.002
HCRC012	55	56	0.014		0.010	0.007	0.003	<0.001	0.006	0.009
HCRC012	56	57	0.008		0.005	0.004	0.002	<0.001	0.002	0.002
HCRC012	57	58	0.008		0.009	0.002	0.001	0.004	0.004	0.001
HCRC012	58	59	0.011		0.067	0.002	0.003	<0.001	0.003	0.021
HCRC012	59	60	0.018		1.685	0.011	0.062	0.005	<0.001	0.477
HCRC012	60	61	0.019		0.138	0.001	0.008	0.008	<0.001	0.040
HCRC012	61	62	0.024		0.015	0.001	0.003	0.003	0.006	0.005
HCRC012	62	63	0.438		0.010	0.010	0.004	<0.001	0.013	0.008
HCRC012	63	64	0.060		0.009	0.002	0.002	0.005	0.017	0.004
HCRC012	64	65	0.015		0.004	0.003	0.001	0.004	0.009	0.002
HCRC012	65	66	0.094		0.313	0.004	0.014	<0.001	0.011	0.104
HCRC012	66	67	0.028		0.121	0.006	0.005	<0.001	0.007	0.045
HCRC012	67	68	0.015		0.206	0.004	0.008	0.005	0.011	0.065
HCRC012	68	69	0.013		0.206	0.003	0.007	0.003	0.013	0.064
HCRC012	69	70	0.023		0.347	0.006	0.014	<0.001	0.015	0.117
HCRC012	70	71	0.031		0.264	0.004	0.013	0.003	0.012	0.098
HCRC012	71	72	0.017		1.273	0.008	0.045	0.007	0.020	0.385
HCRC012	72	73	0.219		0.916	0.009	0.096	0.002	0.017	0.306
HCRC012	73	74	0.021		0.528	0.003	0.032	0.005	0.014	0.176
HCRC012	74	75	0.448		0.426	0.009	0.026	0.005	0.018	0.157
HCRC012	75	76	0.123		0.657	0.008	0.012	0.002	0.023	0.226
HCRC012	76	77	0.023		0.256	0.003	0.007	0.004	0.013	0.090
HCRC012	77	78	0.020		0.223	0.006	0.010	0.007	0.013	0.072

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC012	78	79	0.016		0.263	0.007	0.006	<0.001	0.015	0.083
HCRC012	79	80	0.198		0.382	0.004	0.009	0.003	0.013	0.113
HCRC012	80	81	0.021		0.081	0.002	0.003	<0.001	0.010	0.026
HCRC012	81	82	0.015		0.012	0.001	0.003	0.001	0.010	0.006
HCRC012	82	83	0.013		0.008	<0.001	0.002	0.001	0.009	0.003
HCRC012	83	84	0.023		0.007	<0.001	0.002	0.003	0.014	0.002
HCRC012	84	85	0.027		0.006	0.001	0.002	0.001	0.014	0.001
HCRC012	85	86	0.010		0.007	0.002	0.002	0.004	0.011	0.002
HCRC012	86	87	0.010		0.005	<0.001	0.002	<0.001	0.013	0.004
HCRC012	87	88	0.044		0.010	0.006	0.007	0.002	0.011	0.012
HCRC012	88	89	0.015		0.006	0.001	0.009	<0.001	0.007	0.003
HCRC012	89	90	0.008		0.005	0.003	0.002	0.011	0.012	0.001
HCRC012	90	91	0.029		0.024	0.006	0.003	<0.001	0.008	0.012
HCRC012	91	92	0.020		0.034	0.010	0.004	0.002	0.011	0.019
HCRC012	92	93	0.035		0.121	0.010	0.008	<0.001	0.011	0.054
HCRC012	93	94	0.047		0.546	0.019	0.025	0.007	0.020	0.175
HCRC012	94	95	0.071		0.312	0.013	0.014	0.003	0.016	0.104
HCRC012	95	96	0.054		0.373	0.017	0.028	<0.001	0.015	0.127
HCRC012	96	97	0.392		0.111	0.023	0.018	0.006	0.011	0.056
HCRC012	97	98	0.579		0.124	0.104	0.027	<0.001	0.007	0.119
HCRC012	98	99	0.086		0.170	0.020	0.012	<0.001	0.013	0.080
HCRC012	99	100	0.055		0.237	0.010	0.009	0.004	0.018	0.094
HCRC013	0	1	0.066		0.046	0.001	0.003	0.002	0.009	0.003
HCRC013	1	2	0.026		0.019	0.002	0.004	0.002	0.009	0.005
HCRC013	2	3	0.028		0.029	<0.001	0.002	<0.001	0.009	0.002
HCRC013	3	4	0.016		0.081	<0.001	0.003	<0.001	0.002	0.003
HCRC013	4	5	0.028		0.111	<0.001	0.003	0.003	0.002	<0.001
HCRC013	5	6	0.025		0.098	0.001	0.007	<0.001	0.006	0.001
HCRC013	6	7	0.094		0.084	0.001	0.006	0.002	0.005	0.002
HCRC013	7	8	0.055		0.077	<0.001	0.006	<0.001	0.005	0.001
HCRC013	8	9	0.115		0.033	0.001	0.009	<0.001	0.007	0.002
HCRC013	9	10	0.048		0.040	0.001	0.009	0.002	0.007	0.002
HCRC013	10	11	0.061		0.021	0.001	0.026	<0.001	0.007	0.001
HCRC013	11	12	0.087		0.041	0.002	0.051	<0.001	0.006	0.002
HCRC013	12	13	0.215		0.031	0.003	0.014	<0.001	0.009	<0.001
HCRC013	13	14	0.287		0.023	0.001	0.019	0.006	0.008	0.003
HCRC013	14	15	0.061		0.051	<0.001	0.014	<0.001	0.006	<0.001
HCRC013	15	16	0.228		0.113	0.001	0.013	<0.001	0.008	0.002
HCRC013	16	17	0.035		0.169	<0.001	0.009	<0.001	0.003	0.012
HCRC013	17	18	0.018		0.156	0.002	0.010	<0.001	0.009	0.006
HCRC013	18	19	0.040		0.121	0.001	0.009	<0.001	0.009	0.003
HCRC013	19	20	0.024		0.129	<0.001	0.014	<0.001	0.005	0.002
HCRC013	20	21	0.013		0.051	<0.001	0.004	0.003	0.002	<0.001
HCRC013	21	22	0.010		0.038	<0.001	0.003	0.005	0.002	<0.001
HCRC013	22	23	0.010		0.042	0.001	0.004	<0.001	0.003	<0.001
HCRC013	23	24	0.009		0.041	0.003	0.003	<0.001	0.005	<0.001
HCRC013	24	25	0.017		0.048	0.002	0.004	0.001	0.003	<0.001
HCRC013	25	26	0.021		0.088	0.001	0.010	<0.001	0.009	<0.001
HCRC013	26	27	0.046		0.012	<0.001	0.013	<0.001	0.007	<0.001
HCRC013	27	28	0.013		0.012	0.001	0.010	<0.001	0.003	<0.001
HCRC013	28	29	0.011		0.014	<0.001	0.018	<0.001	0.012	<0.001
HCRC013	29	30	0.012		0.017	0.001	0.022	<0.001	0.008	<0.001
HCRC013	30	31	0.015		0.018	<0.001	0.009	0.001	0.007	<0.001

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC013	31	32	0.008		0.017	0.001	0.007	<0.001	0.011	<0.001
HCRC013	32	33	0.009		0.016	0.003	0.010	0.004	0.007	<0.001
HCRC013	33	34	0.006		0.014	<0.001	0.003	<0.001	0.008	<0.001
HCRC013	34	35	0.006		0.008	<0.001	0.012	<0.001	0.006	<0.001
HCRC013	35	36	0.008		0.005	<0.001	0.008	<0.001	0.005	<0.001
HCRC013	36	37	0.011		0.003	<0.001	0.004	<0.001	0.005	<0.001
HCRC013	37	38	0.009		0.003	<0.001	0.003	<0.001	0.002	<0.001
HCRC013	38	39	0.028		0.005	0.002	0.009	0.002	0.006	<0.001
HCRC013	39	40	0.022		0.010	0.003	0.014	<0.001	0.006	<0.001
HCRC013	40	41	0.019		0.009	0.001	0.008	<0.001	0.006	<0.001
HCRC013	41	42	0.046		0.010	0.001	0.016	<0.001	0.008	0.001
HCRC013	42	43	0.015		0.033	0.002	0.008	0.002	0.006	<0.001
HCRC013	43	44	0.027		0.045	0.005	0.010	0.003	0.020	<0.001
HCRC013	44	45	0.031		0.051	0.002	0.009	0.001	0.009	0.001
HCRC013	45	46	0.073		0.030	0.001	0.003	<0.001	0.012	0.002
HCRC013	46	47	0.028		0.010	0.001	0.003	<0.001	0.006	0.002
HCRC013	47	48	0.013		0.003	<0.001	0.008	<0.001	0.004	0.003
HCRC013	48	49	0.027		0.003	0.001	0.003	<0.001	0.006	0.002
HCRC013	49	50	0.016		0.082	0.003	0.007	<0.001	0.008	0.029
HCRC013	50	51	0.015		0.039	<0.001	0.007	<0.001	0.005	0.018
HCRC013	51	52	0.008		0.046	0.003	0.005	<0.001	0.006	0.018
HCRC013	52	53	0.007		0.008	0.001	0.006	<0.001	0.002	0.005
HCRC013	53	54	0.006		0.033	0.002	0.007	<0.001	0.005	0.014
HCRC013	54	55	0.011		0.031	0.001	0.005	<0.001	0.004	0.014
HCRC013	55	56	0.398		0.121	0.007	0.013	<0.001	0.009	0.037
HCRC013	56	57	0.133		0.274	0.004	0.028	<0.001	0.013	0.069
HCRC013	57	58	0.238		0.109	0.006	0.151	0.002	0.009	0.027
HCRC013	58	59	2.868		0.084	0.010	0.144	<0.001	0.007	0.007
HCRC013	59	60	0.617		0.144	0.006	0.049	0.003	0.008	0.006
HCRC013	60	61	0.148		0.102	0.005	0.007	<0.001	0.012	0.010
HCRC013	61	62	0.078		0.142	0.005	0.030	0.005	0.014	0.034
HCRC013	62	63	0.053		0.048	0.005	0.004	<0.001	0.006	<0.001
HCRC013	63	64	0.215		0.028	0.009	0.092	0.001	0.008	0.008
HCRC013	64	65	0.030		0.054	0.003	0.005	0.001	0.006	0.011
HCRC013	65	66	0.097		0.215	0.007	0.021	<0.001	0.013	0.057
HCRC013	66	67	0.029		0.418	0.004	0.022	<0.001	0.010	0.098
HCRC013	67	68	0.034		0.078	0.002	0.005	<0.001	0.007	0.015
HCRC013	68	69	0.205		0.053	0.031	0.006	0.001	0.006	0.032
HCRC013	69	70	0.139		0.064	0.004	0.020	0.001	0.014	0.014
HCRC013	70	71	0.121		0.032	0.011	0.005	<0.001	0.009	0.014
HCRC013	71	72	0.076		0.011	0.003	0.003	<0.001	0.010	0.009
HCRC013	72	73	0.008		0.014	0.005	0.004	<0.001	0.006	0.009
HCRC013	73	74	0.009		0.012	0.003	0.002	0.001	0.004	0.005
HCRC013	74	75	0.010		0.232	0.003	0.020	<0.001	0.005	0.074
HCRC013	75	76	0.015		0.028	<0.001	0.003	<0.001	0.006	0.009
HCRC013	76	77	0.772		0.014	0.020	0.007	<0.001	0.009	0.018
HCRC013	77	78	0.042		0.012	0.002	0.010	<0.001	0.008	0.004
HCRC013	78	79	0.938		0.017	0.027	0.007	0.002	0.005	0.016
HCRC013	79	80	0.148		0.121	0.007	0.014	<0.001	0.012	0.053
HCRC013	80	81	0.042		0.232	0.009	0.015	0.001	0.011	0.113
HCRC013	81	82	0.049		0.050	0.007	0.005	<0.001	0.006	0.029
HCRC013	82	83	0.032		0.084	0.028	0.005	<0.001	0.013	0.063
HCRC013	83	84	0.017		0.171	0.004	0.011	<0.001	0.016	0.116

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC013	84	85	0.142		0.087	0.008	0.011	0.005	0.015	0.059
HCRC013	85	86	0.190		0.040	0.019	0.007	<0.001	0.009	0.056
HCRC013	86	87	0.119		0.094	0.007	0.004	0.004	0.010	0.108
HCRC013	87	88	0.062		0.092	0.032	0.015	<0.001	0.013	0.095
HCRC013	88	89	0.073		0.262	0.008	0.010	0.001	0.014	0.243
HCRC013	89	90	0.285		0.121	0.005	0.010	<0.001	0.008	0.129
HCRC013	90	91	0.037		0.054	<0.001	0.006	0.002	0.005	0.061
HCRC013	91	92	0.044		0.198	0.003	0.015	<0.001	0.012	0.186
HCRC013	92	93	0.094		0.140	0.002	0.022	0.001	0.015	0.146
HCRC013	93	94	0.037		0.174	0.007	0.028	<0.001	0.014	0.199
HCRC013	94	95	0.102		0.122	0.007	0.014	<0.001	0.010	0.147
HCRC013	95	96	0.117		0.197	0.012	0.012	<0.001	0.011	0.223
HCRC013	96	97	0.068		0.166	0.026	0.014	0.002	0.011	0.145
HCRC013	97	98	0.048		0.094	0.014	0.009	<0.001	0.015	0.066
HCRC013	98	99	0.237		0.265	0.012	0.020	<0.001	0.012	0.118
HCRC013	99	100	0.034		0.095	0.004	0.004	<0.001	0.016	0.038
HCRC013	100	101	0.018		0.061	0.002	0.006	0.002	0.012	0.029
HCRC013	101	102	0.040		0.225	0.008	0.014	0.004	0.015	0.078
HCRC013	102	103	0.060		0.265	0.005	0.017	<0.001	0.014	0.084
HCRC013	103	104	0.030		0.121	0.001	0.009	0.003	0.011	0.040
HCRC013	104	105	0.138		0.022	0.008	0.006	0.001	0.012	0.010
HCRC013	105	106	0.113		0.006	0.005	0.004	<0.001	0.007	0.002
HCRC013	106	107	0.018		0.008	<0.001	0.002	0.002	0.007	0.002
HCRC013	107	108	0.010		0.010	0.002	0.002	<0.001	0.008	0.003
HCRC013	108	109	0.012		0.019	0.002	0.003	<0.001	0.014	0.005
HCRC013	109	110	0.007		0.011	0.001	0.001	<0.001	0.006	0.003
HCRC013	110	111	0.014		0.007	<0.001	0.001	<0.001	0.005	0.003
HCRC013	111	112	0.147		0.008	0.002	0.002	<0.001	0.006	0.003
HCRC013	112	113	0.027		0.226	0.006	0.009	0.004	0.013	0.081
HCRC013	113	114	0.025		0.263	0.010	0.016	<0.001	0.011	0.087
HCRC013	114	115	1.982		0.381	0.044	0.027	0.002	0.008	0.160
HCRC013	115	116	0.558		0.781	0.055	0.031	<0.001	0.014	0.272
HCRC013	116	117	0.057		0.092	0.007	0.007	<0.001	0.010	0.050
HCRC013	117	118	0.040		0.011	0.004	0.004	<0.001	0.012	0.003
HCRC013	118	119	0.020		0.023	0.003	0.003	<0.001	0.015	0.001
HCRC013	119	120	0.015		0.018	0.003	0.003	<0.001	0.005	0.001
HCRC014	0	1	0.023		0.004	0.007	0.006	0.005	0.002	0.006
HCRC014	1	2	0.213		0.035	0.003	0.010	<0.001	0.007	0.011
HCRC014	2	3	0.082		0.022	<0.001	0.005	0.005	0.005	0.002
HCRC014	3	4	0.108		0.017	<0.001	0.003	0.004	0.006	<0.001
HCRC014	4	5	0.028		0.065	0.001	0.002	<0.001	0.002	0.017
HCRC014	5	6	0.018		0.047	<0.001	0.003	0.006	0.002	0.007
HCRC014	6	7	0.016		0.066	<0.001	0.002	<0.001	0.002	<0.001
HCRC014	7	8	0.016		0.064	0.002	0.003	0.005	<0.001	<0.001
HCRC014	8	9	0.018		0.040	0.001	0.007	0.005	0.006	<0.001
HCRC014	9	10	0.019		0.037	0.002	0.011	<0.001	0.005	<0.001
HCRC014	10	11	0.013		0.045	0.002	0.013	0.002	0.004	<0.001
HCRC014	11	12	0.023		0.039	0.007	0.008	0.002	0.009	0.002
HCRC014	12	13	0.012		0.051	0.005	0.004	0.006	0.002	<0.001
HCRC014	13	14	0.011		0.050	0.003	0.004	0.003	0.002	<0.001
HCRC014	14	15	0.010		0.039	0.001	0.003	<0.001	0.004	0.001
HCRC014	15	16	0.012		0.047	0.001	0.005	0.004	0.002	<0.001
HCRC014	16	17	0.011		0.052	<0.001	0.003	<0.001	0.004	<0.001

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC014	17	18	0.008		0.042	<0.001	0.008	0.004	0.002	<0.001
HCRC014	18	19	0.005		0.031	<0.001	0.003	0.006	0.008	<0.001
HCRC014	19	20	0.008		0.037	<0.001	0.002	0.002	0.004	<0.001
HCRC014	20	21	0.010		0.032	0.003	0.001	<0.001	<0.001	<0.001
HCRC014	21	22	0.008		0.023	0.001	0.002	<0.001	0.002	<0.001
HCRC014	22	23	0.005		0.012	<0.001	0.001	<0.001	0.006	<0.001
HCRC014	23	24	0.007		0.004	0.001	0.002	0.001	0.004	<0.001
HCRC014	24	25	0.006		0.002	<0.001	0.002	<0.001	0.003	<0.001
HCRC014	25	26	0.008		0.003	0.003	0.002	<0.001	0.002	<0.001
HCRC014	26	27	0.066		0.013	0.003	0.002	<0.001	0.006	<0.001
HCRC014	27	28	0.043		0.031	0.007	0.004	0.002	0.005	<0.001
HCRC014	28	29	0.060		0.027	0.003	0.002	<0.001	0.005	<0.001
HCRC014	29	30	0.178		0.032	0.004	0.009	<0.001	0.002	<0.001
HCRC014	30	31	0.022		0.039	0.002	0.003	0.002	0.005	<0.001
HCRC014	31	32	0.026		0.079	0.003	0.012	<0.001	0.009	<0.001
HCRC014	32	33	0.055		0.097	0.005	0.013	<0.001	0.006	<0.001
HCRC014	33	34	0.132		0.046	0.006	0.055	<0.001	0.006	<0.001
HCRC014	34	35	0.089		0.056	0.005	0.030	<0.001	0.004	<0.001
HCRC014	35	36	0.057		0.094	0.003	0.014	0.004	0.010	<0.001
HCRC014	36	37	0.500		0.105	0.005	0.013	0.003	0.009	<0.001
HCRC014	37	38	0.061		0.085	0.003	0.011	<0.001	0.004	<0.001
HCRC014	38	39	0.018		0.104	0.004	0.003	<0.001	0.004	<0.001
HCRC014	39	40	0.021		0.052	0.005	0.003	<0.001	0.006	<0.001
HCRC014	40	41	0.018		0.008	0.004	0.001	<0.001	0.004	<0.001
HCRC014	41	42	0.141		0.005	0.003	0.003	<0.001	<0.001	<0.001
HCRC014	42	43	0.078		0.010	0.005	0.002	<0.001	0.002	<0.001
HCRC014	43	44	0.016		0.077	0.005	0.003	0.003	0.003	<0.001
HCRC014	44	45	0.008		0.030	<0.001	0.002	0.004	0.002	<0.001
HCRC014	45	46	0.008		0.009	0.001	0.003	<0.001	0.007	0.002
HCRC014	46	47	0.014		0.004	0.003	0.011	<0.001	0.003	0.003
HCRC014	47	48	0.023		0.003	0.004	0.062	<0.001	0.007	0.004
HCRC014	48	49	0.017		0.015	0.003	0.026	0.001	0.010	0.003
HCRC014	49	50	0.020		0.103	0.004	0.012	<0.001	0.011	0.001
HCRC014	50	51	0.010		0.015	<0.001	0.006	<0.001	0.003	0.002
HCRC014	51	52	0.009		0.010	0.001	0.028	<0.001	0.005	0.006
HCRC014	52	53	0.016		0.008	0.002	0.024	0.002	0.005	0.007
HCRC014	53	54	0.023		0.010	0.002	0.008	<0.001	0.002	0.004
HCRC014	54	55	0.038		0.016	0.002	0.025	<0.001	0.007	0.005
HCRC014	55	56	0.034		0.006	<0.001	0.037	<0.001	0.008	0.004
HCRC014	56	57	0.045		0.009	0.001	0.040	<0.001	0.008	0.003
HCRC014	57	58	0.015		0.007	0.003	0.019	<0.001	0.002	0.003
HCRC014	58	59	0.015		0.009	0.001	0.017	0.007	0.010	0.002
HCRC014	59	60	0.025		0.009	0.002	0.009	0.001	0.003	0.002
HCRC014	60	61	0.088		0.020	0.005	0.024	<0.001	0.009	0.012
HCRC014	61	62	0.018		0.057	0.002	0.011	<0.001	0.010	0.023
HCRC014	62	63	0.015		0.042	0.003	0.005	<0.001	0.003	0.016
HCRC014	63	64	0.138		0.067	0.005	0.005	<0.001	0.003	0.026
HCRC014	64	65	0.718		0.217	0.003	0.008	0.002	0.006	0.071
HCRC014	65	66	0.388		0.144	0.005	0.009	<0.001	0.006	0.055
HCRC014	66	67	0.062		0.084	0.003	0.008	<0.001	0.004	0.032
HCRC014	67	68	0.016		0.109	0.003	0.006	<0.001	0.006	0.035
HCRC014	68	69	0.025		0.102	0.002	0.008	<0.001	0.004	0.032
HCRC014	69	70	0.147		0.899	0.007	0.058	0.004	0.003	0.251

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC014	70	71	0.242		0.420	0.005	0.026	<0.001	0.007	0.129
HCRC014	71	72	0.142		0.191	0.002	0.011	0.003	0.006	0.067
HCRC014	72	73	0.027		0.209	0.002	0.013	<0.001	0.006	0.067
HCRC014	73	74	0.141		0.143	0.002	0.012	0.003	0.002	0.043
HCRC014	74	75	0.031		0.179	0.011	0.014	<0.001	0.008	0.061
HCRC014	75	76	0.011		0.023	0.003	0.004	<0.001	0.006	0.009
HCRC014	76	77	0.008		0.004	0.003	0.002	0.006	0.005	0.013
HCRC014	77	78	0.006		0.018	0.005	0.009	<0.001	<0.001	0.012
HCRC014	78	79	0.007		0.027	0.001	0.007	<0.001	0.006	0.014
HCRC014	79	80	0.014		0.024	0.003	0.005	<0.001	0.004	0.015
HCRC014	80	81	0.035		0.121	<0.001	0.006	<0.001	0.007	0.041
HCRC014	81	82	0.096		0.097	0.012	0.012	<0.001	0.008	0.047
HCRC014	82	83	0.018		0.025	0.003	0.006	<0.001	0.005	0.015
HCRC014	83	84	0.010		0.006	0.001	0.003	0.001	0.005	0.004
HCRC014	84	85	0.128		0.003	0.003	0.004	<0.001	0.003	0.004
HCRC014	85	86	0.099		0.039	0.002	0.004	0.002	0.009	0.017
HCRC014	86	87	0.448		0.023	0.009	0.007	<0.001	0.010	0.011
HCRC014	87	88	0.104		0.150	0.054	0.005	0.001	0.011	0.097
HCRC014	88	89	0.321		0.289	0.042	0.016	0.005	0.014	0.151
HCRC014	89	90	0.388		0.236	0.011	0.027	<0.001	0.009	0.103
HCRC014	90	91	0.615		0.137	0.006	0.016	0.003	0.011	0.055
HCRC014	91	92	0.089		0.046	0.002	0.014	<0.001	0.009	0.022
HCRC014	92	93	1.507		0.079	0.019	0.021	0.005	0.012	0.045
HCRC014	93	94	0.220		0.008	0.006	0.006	0.004	0.005	0.009
HCRC014	94	95	0.096		0.004	0.003	0.003	<0.001	0.008	0.004
HCRC014	95	96	0.528		0.008	0.013	0.005	0.004	0.010	0.008
HCRC014	96	97	0.285		0.164	0.025	0.013	0.010	0.013	0.091
HCRC014	97	98	0.198		0.305	0.062	0.017	0.005	0.011	0.189
HCRC014	98	99	0.061		0.048	0.012	0.007	0.003	0.009	0.027
HCRC014	99	100	0.333		0.069	0.005	0.068	<0.001	0.010	0.038
HCRC014	100	101	0.036		0.015	0.005	0.006	0.001	0.012	0.005
HCRC014	101	102	0.023		0.010	0.003	0.004	<0.001	0.011	0.005
HCRC014	102	103	0.020		0.009	0.003	0.002	0.004	0.014	0.038
HCRC014	103	104	0.095		0.046	0.087	0.003	<0.001	0.011	0.096
HCRC014	104	105	0.071		0.076	0.023	0.004	<0.001	0.010	0.054
HCRC014	105	106	0.106		0.164	0.012	0.020	<0.001	0.011	0.078
HCRC014	106	107	0.494		0.693	0.026	0.156	0.003	0.010	0.289
HCRC014	107	108	0.160		0.094	0.006	0.026	<0.001	0.009	0.039
HCRC014	108	109	0.051		0.042	0.003	0.008	<0.001	0.009	0.020
HCRC014	109	110	0.973		0.433	0.014	0.006	<0.001	0.015	0.186
HCRC014	110	111	0.228		0.072	0.005	0.002	0.005	0.008	0.033
HCRC014	111	112	0.061		0.050	0.014	0.006	<0.001	0.009	0.038
HCRC014	112	113	2.380		0.031	0.220	0.003	0.004	0.009	0.177
HCRC014	113	114	1.056		0.110	0.199	0.003	<0.001	0.006	0.225
HCRC014	114	115	0.199		0.101	0.116	0.012	0.002	0.014	0.194
HCRC014	115	116	0.101		0.083	0.024	0.018	<0.001	0.013	0.096
HCRC014	116	117	0.035		0.025	0.006	0.006	<0.001	0.009	0.028
HCRC014	117	118	0.048		0.085	0.023	0.007	<0.001	0.009	0.086
HCRC014	118	119	0.038		0.048	0.006	0.008	<0.001	0.011	0.034
HCRC014	119	120	0.087		0.027	0.010	0.004	<0.001	0.010	0.023
HCRC015	0	1	0.019		0.006	<0.001	0.002	<0.001	0.007	<0.001
HCRC015	1	2	0.019		0.019	<0.001	0.002	0.001	0.007	0.006
HCRC015	2	3	0.011		0.017	<0.001	0.002	0.002	0.006	0.014

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC015	3	4	0.008		0.017	<0.001	<0.001	<0.001	0.009	0.005
HCRC015	4	5	0.025		0.011	<0.001	0.001	<0.001	0.004	0.005
HCRC015	5	6	0.040		0.015	0.003	0.002	<0.001	0.014	<0.001
HCRC015	6	7	0.014		0.019	<0.001	0.001	<0.001	0.005	0.006
HCRC015	7	8	0.043		0.011	0.001	0.004	<0.001	0.024	0.005
HCRC015	8	9	0.021		0.008	<0.001	0.002	<0.001	0.011	0.001
HCRC015	9	10	0.024		0.007	<0.001	0.003	<0.001	0.011	0.002
HCRC015	10	11	0.026		0.010	<0.001	0.001	<0.001	0.011	<0.001
HCRC015	11	12	0.034		0.009	<0.001	0.004	<0.001	0.006	0.001
HCRC015	12	13	0.036		0.012	<0.001	0.004	0.002	0.005	0.003
HCRC015	13	14	0.023		0.010	<0.001	0.003	<0.001	0.011	0.002
HCRC015	14	15	0.021		0.013	<0.001	0.002	<0.001	0.008	<0.001
HCRC015	15	16	0.035		0.013	<0.001	0.004	<0.001	0.008	<0.001
HCRC015	16	17	0.023		0.011	<0.001	0.002	<0.001	0.006	<0.001
HCRC015	17	18	0.023		0.017	<0.001	0.002	0.004	0.002	<0.001
HCRC015	18	19	0.028		0.016	<0.001	0.002	0.003	0.007	<0.001
HCRC015	19	20	0.034		0.022	<0.001	0.001	<0.001	0.008	<0.001
HCRC015	20	21	0.038		0.022	<0.001	0.003	<0.001	0.008	<0.001
HCRC015	21	22	0.108		0.034	<0.001	0.004	<0.001	0.008	0.002
HCRC015	22	23	0.094		0.029	0.002	0.004	<0.001	0.010	<0.001
HCRC015	23	24	0.163		0.013	<0.001	0.007	<0.001	0.010	<0.001
HCRC015	24	25	0.244		0.013	0.002	0.008	<0.001	0.004	<0.001
HCRC015	25	26	0.085		0.023	<0.001	0.008	<0.001	0.010	<0.001
HCRC015	26	27	0.134		0.030	0.001	0.007	<0.001	0.087	<0.001
HCRC015	27	28	0.030		0.012	0.001	0.011	<0.001	0.005	<0.001
HCRC015	28	29	0.027		0.010	<0.001	0.002	0.004	0.007	<0.001
HCRC015	29	30	0.856		0.011	0.010	0.006	<0.001	0.006	0.004
HCRC015	30	31	1.345		0.011	0.008	0.004	<0.001	0.010	0.005
HCRC015	31	32	0.217		0.007	0.003	0.003	<0.001	0.006	0.004
HCRC015	32	33	0.021		0.007	<0.001	0.003	<0.001	0.009	0.006
HCRC015	33	34	0.032		0.005	0.001	0.002	<0.001	0.006	0.004
HCRC015	34	35	0.013		0.007	<0.001	0.002	0.006	0.003	0.002
HCRC015	35	36	0.022		0.005	<0.001	0.003	0.001	0.002	0.005
HCRC015	36	37	0.033		0.005	0.001	0.003	<0.001	0.009	0.008
HCRC015	37	38	0.013		0.004	<0.001	0.002	<0.001	0.005	0.002
HCRC015	38	39	0.016		0.007	0.002	0.001	<0.001	0.008	<0.001
HCRC015	39	40	0.024		0.002	<0.001	0.002	<0.001	0.007	<0.001
HCRC015	40	41	0.023		0.011	<0.001	0.002	<0.001	0.005	<0.001
HCRC015	41	42	0.028		0.004	<0.001	0.003	0.003	0.005	<0.001
HCRC015	42	43	0.017		0.006	<0.001	0.016	<0.001	0.005	<0.001
HCRC015	43	44	0.026		0.018	<0.001	0.004	<0.001	0.004	<0.001
HCRC015	44	45	0.040		0.022	<0.001	0.003	0.002	0.010	<0.001
HCRC015	45	46	0.013		0.004	<0.001	0.002	<0.001	0.004	<0.001
HCRC015	46	47	0.012		0.007	<0.001	0.001	<0.001	0.007	<0.001
HCRC015	47	48	0.013		0.004	<0.001	<0.001	<0.001	0.005	<0.001
HCRC015	48	49	0.011		0.003	<0.001	0.002	0.001	0.005	<0.001
HCRC015	49	50	0.008		0.002	<0.001	0.002	<0.001	0.005	<0.001
HCRC015	50	51	0.017		0.008	<0.001	0.003	<0.001	0.005	<0.001
HCRC015	51	52	0.028		0.006	<0.001	0.002	<0.001	0.006	<0.001
HCRC015	52	53	0.025		0.011	<0.001	0.003	<0.001	0.005	<0.001
HCRC015	53	54	0.023		0.008	<0.001	0.003	<0.001	0.002	<0.001
HCRC015	54	55	0.023		0.008	<0.001	0.004	<0.001	0.005	<0.001
HCRC015	55	56	0.010		0.007	<0.001	0.003	<0.001	0.003	<0.001

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC015	56	57	0.040		0.003	<0.001	0.002	<0.001	0.006	<0.001
HCRC015	57	58	0.012		0.002	<0.001	0.001	0.002	0.004	<0.001
HCRC015	58	59	0.006		0.002	<0.001	<0.001	<0.001	0.003	<0.001
HCRC015	59	60	0.042		0.003	<0.001	0.003	<0.001	0.004	0.001
HCRC015	60	61	0.018		0.003	<0.001	0.003	<0.001	0.004	0.002
HCRC015	61	62	0.008		0.003	<0.001	0.002	<0.001	0.002	0.001
HCRC015	62	63	0.006		0.002	<0.001	0.001	<0.001	0.004	0.001
HCRC015	63	64	0.016		0.011	<0.001	0.003	0.005	0.010	<0.001
HCRC015	64	65	0.009		0.004	0.001	0.002	<0.001	0.003	0.001
HCRC015	65	66	0.007		0.002	<0.001	0.002	<0.001	0.006	<0.001
HCRC015	66	67	0.012		0.006	<0.001	0.001	<0.001	0.002	0.003
HCRC015	67	68	0.011		0.005	<0.001	0.002	<0.001	0.017	<0.001
HCRC015	68	69	0.009		0.002	<0.001	0.001	<0.001	0.004	<0.001
HCRC015	69	70	0.016		0.003	<0.001	0.001	<0.001	0.002	<0.001
HCRC015	70	71	0.006		<0.001	<0.001	0.003	0.004	0.003	<0.001
HCRC015	71	72	0.006		0.002	<0.001	0.001	<0.001	0.002	<0.001
HCRC015	72	73	0.011		0.010	<0.001	0.001	0.002	0.009	<0.001
HCRC015	73	74	0.009		0.005	<0.001	0.002	<0.001	0.005	<0.001
HCRC015	74	75	0.023		0.011	<0.001	0.032	<0.001	0.008	<0.001
HCRC015	75	76	0.017		0.005	<0.001	0.022	<0.001	0.013	<0.001
HCRC015	76	77	0.041		0.015	<0.001	0.027	<0.001	0.011	<0.001
HCRC015	77	78	0.067		0.016	<0.001	0.024	<0.001	0.010	<0.001
HCRC015	78	79	0.020		0.008	<0.001	0.006	<0.001	0.005	<0.001
HCRC015	79	80	0.016		0.004	<0.001	0.002	0.003	0.002	<0.001
HCRC015	80	81	0.028		0.011	<0.001	0.002	<0.001	0.003	<0.001
HCRC015	81	82	0.014		0.008	<0.001	0.001	<0.001	<0.001	<0.001
HCRC015	82	83	0.015		0.011	<0.001	0.007	0.003	0.006	<0.001
HCRC015	83	84	0.018		0.019	<0.001	0.004	<0.001	0.021	<0.001
HCRC015	84	85	0.008		<0.001	<0.001	0.002	0.001	0.005	<0.001
HCRC015	85	86	0.005		0.002	<0.001	0.001	0.002	0.003	<0.001
HCRC015	86	87	0.009		<0.001	<0.001	0.002	<0.001	0.004	<0.001
HCRC015	87	88	0.006		0.006	<0.001	0.004	<0.001	<0.001	<0.001
HCRC015	88	89	0.008		0.056	<0.001	0.002	<0.001	<0.001	<0.001
HCRC015	89	90	0.009		0.035	<0.001	0.002	<0.001	0.003	<0.001
HCRC015	90	91	0.026		0.034	<0.001	0.004	0.001	0.003	0.008
HCRC015	91	92	0.011		0.038	<0.001	0.002	0.003	0.004	<0.001
HCRC015	92	93	0.018		0.028	<0.001	0.003	0.002	0.005	<0.001
HCRC015	93	94	0.011		0.041	<0.001	0.016	0.002	0.009	<0.001
HCRC015	94	95	0.009		0.012	<0.001	0.014	0.003	0.005	<0.001
HCRC015	95	96	0.009		0.005	<0.001	0.011	<0.001	0.002	<0.001
HCRC015	96	97	0.009		0.003	<0.001	0.006	<0.001	0.002	<0.001
HCRC015	97	98	0.024		0.003	<0.001	0.004	<0.001	0.002	<0.001
HCRC015	98	99	0.011		0.004	<0.001	0.008	<0.001	0.006	0.003
HCRC015	99	100	0.009		0.007	<0.001	0.004	<0.001	0.006	0.001
HCRC015	100	101	0.021		0.003	0.001	0.001	<0.001	0.007	<0.001
HCRC015	101	102	0.006		0.005	<0.001	<0.001	<0.001	0.004	0.001
HCRC015	102	103	0.006		0.008	<0.001	<0.001	0.003	0.004	<0.001
HCRC015	103	104	0.010		0.005	<0.001	0.002	<0.001	0.010	<0.001
HCRC015	104	105	0.005		0.007	<0.001	<0.001	<0.001	0.009	<0.001
HCRC015	105	106	0.006		0.007	<0.001	0.001	0.001	0.008	<0.001
HCRC015	106	107	0.007		0.003	<0.001	0.003	<0.001	0.009	<0.001
HCRC015	107	108	0.008		0.008	<0.001	0.002	<0.001	0.009	<0.001
HCRC015	108	109	0.010		0.006	<0.001	0.003	<0.001	0.006	<0.001

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC015	109	110	0.005		<0.001	<0.001	<0.001	0.002	0.002	<0.001
HCRC015	110	111	0.010		0.006	<0.001	0.004	<0.001	0.002	0.001
HCRC015	111	112	0.010		0.002	<0.001	0.001	<0.001	0.006	<0.001
HCRC015	112	113	0.010		0.004	<0.001	0.003	<0.001	0.004	<0.001
HCRC015	113	114	0.005		0.002	<0.001	0.001	<0.001	0.003	<0.001
HCRC015	114	115	0.007		0.007	<0.001	0.003	<0.001	0.006	0.004
HCRC015	115	116	0.011		0.006	0.001	0.003	0.004	0.006	0.001
HCRC015	116	117	0.005		0.003	<0.001	0.002	0.002	0.006	<0.001
HCRC015	117	118	0.014		0.002	<0.001	<0.001	0.002	0.004	<0.001
HCRC015	118	119	0.007		0.003	<0.001	0.001	0.001	0.005	<0.001
HCRC015	119	120	0.003		0.003	<0.001	0.001	<0.001	0.004	<0.001
HCRC016	0	1	No Sample							
HCRC016	1	2	0.012		0.005	<0.001	0.002	<0.001	0.007	<0.001
HCRC016	2	3	0.013		0.007	<0.001	0.001	0.004	0.007	0.015
HCRC016	3	4	0.011		0.005	<0.001	0.002	0.005	0.005	0.008
HCRC016	4	5	0.008		0.005	<0.001	0.001	<0.001	0.003	<0.001
HCRC016	5	6	0.010		0.007	<0.001	0.001	0.001	0.006	<0.001
HCRC016	6	7	0.006		0.003	<0.001	0.002	<0.001	0.005	<0.001
HCRC016	7	8	0.011		0.007	<0.001	0.004	<0.001	0.006	<0.001
HCRC016	8	9	0.010		0.009	<0.001	0.003	0.002	0.003	<0.001
HCRC016	9	10	0.009		0.006	<0.001	0.002	<0.001	0.005	<0.001
HCRC016	10	11	0.009		0.003	<0.001	0.002	<0.001	0.003	<0.001
HCRC016	11	12	0.009		0.005	<0.001	0.001	0.004	0.002	<0.001
HCRC016	12	13	0.007		0.003	<0.001	0.002	<0.001	0.002	<0.001
HCRC016	13	14	0.011		0.005	<0.001	0.002	<0.001	0.005	<0.001
HCRC016	14	15	0.012		0.009	<0.001	0.004	0.003	0.003	<0.001
HCRC016	15	16	0.018		0.013	<0.001	0.003	<0.001	0.003	<0.001
HCRC016	16	17	0.013		0.008	<0.001	0.003	<0.001	0.005	<0.001
HCRC016	17	18	0.011		0.008	<0.001	0.003	<0.001	0.003	<0.001
HCRC016	18	19	0.011		0.008	<0.001	0.003	<0.001	0.003	<0.001
HCRC016	19	20	0.023		0.007	<0.001	0.002	<0.001	0.006	<0.001
HCRC016	20	21	0.008		0.003	<0.001	0.002	<0.001	0.005	<0.001
HCRC016	21	22	0.012		0.004	<0.001	0.004	<0.001	0.005	<0.001
HCRC016	22	23	0.008		0.001	<0.001	0.001	<0.001	0.002	<0.001
HCRC016	23	24	0.006		<0.001	<0.001	0.003	0.002	0.006	<0.001
HCRC016	24	25	0.007		0.002	<0.001	0.001	<0.001	0.010	<0.001
HCRC016	25	26	0.008		0.003	<0.001	<0.001	<0.001	0.003	<0.001
HCRC016	26	27	0.008		0.007	<0.001	0.002	<0.001	0.005	<0.001
HCRC016	27	28	0.008		0.005	<0.001	0.002	<0.001	0.005	<0.001
HCRC016	28	29	0.007		0.007	<0.001	0.001	<0.001	0.003	<0.001
HCRC016	29	30	0.015		0.008	<0.001	0.002	0.004	0.003	<0.001
HCRC016	30	31	0.015		0.010	<0.001	0.004	0.004	0.003	<0.001
HCRC016	31	32	0.007		0.004	<0.001	<0.001	<0.001	0.006	<0.001
HCRC016	32	33	0.011		0.001	<0.001	0.002	0.006	0.005	<0.001
HCRC016	33	34	0.006		0.007	<0.001	0.002	<0.001	0.003	<0.001
HCRC016	34	35	0.010		0.021	<0.001	0.004	<0.001	0.002	<0.001
HCRC016	35	36	0.006		0.005	<0.001	0.002	0.002	0.002	<0.001
HCRC016	36	37	0.010		0.013	<0.001	0.003	<0.001	0.002	<0.001
HCRC016	37	38	0.011		0.013	<0.001	0.002	<0.001	<0.001	<0.001
HCRC016	38	39	0.006		0.010	<0.001	0.002	0.004	0.006	<0.001
HCRC016	39	40	0.007		0.005	<0.001	<0.001	0.002	0.006	<0.001
HCRC016	40	41	<0.001		0.005	<0.001	<0.001	<0.001	0.005	<0.001
HCRC016	41	42	0.006		0.007	<0.001	0.003	0.004	0.006	<0.001

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC016	42	43	0.006		0.005	<0.001	0.002	0.006	0.005	<0.001
HCRC016	43	44	0.007		0.008	<0.001	0.002	0.008	0.003	<0.001
HCRC016	44	45	0.009		0.016	<0.001	0.002	0.003	0.004	<0.001
HCRC016	45	46	0.007		0.014	<0.001	0.002	<0.001	0.003	<0.001
HCRC016	46	47	0.006		0.014	<0.001	<0.001	<0.001	0.007	<0.001
HCRC016	47	48	0.007		0.001	<0.001	0.003	<0.001	0.006	<0.001
HCRC016	48	49	0.005		0.003	<0.001	0.001	<0.001	<0.001	<0.001
HCRC016	49	50	0.007		0.004	<0.001	0.002	<0.001	0.008	<0.001
HCRC016	50	51	0.008		0.005	<0.001	0.002	<0.001	0.008	<0.001
HCRC016	51	52	0.007		<0.001	<0.001	0.001	<0.001	0.006	<0.001
HCRC016	52	53	0.009		0.010	<0.001	0.003	0.010	0.007	<0.001
HCRC016	53	54	0.006		0.006	<0.001	0.001	<0.001	0.005	<0.001
HCRC016	54	55	0.007		0.008	<0.001	0.009	<0.001	0.004	<0.001
HCRC016	55	56	0.007		0.007	<0.001	0.007	0.006	0.005	<0.001
HCRC016	56	57	0.006		0.008	<0.001	<0.001	<0.001	0.003	<0.001
HCRC016	57	58	0.007		0.012	<0.001	0.002	0.005	0.003	<0.001
HCRC016	58	59	0.007		0.006	<0.001	0.003	0.002	0.002	<0.001
HCRC016	59	60	0.005		0.007	<0.001	<0.001	<0.001	<0.001	<0.001
HCRC016	60	61	0.005		0.009	<0.001	0.002	<0.001	0.002	<0.001
HCRC016	61	62	0.006		0.005	<0.001	0.016	0.002	0.002	<0.001
HCRC016	62	63	0.011		0.013	<0.001	0.037	0.003	0.007	<0.001
HCRC016	63	64	0.008		0.011	<0.001	0.053	<0.001	<0.001	<0.001
HCRC016	64	65	0.018		0.025	<0.001	0.146	0.003	0.006	<0.001
HCRC016	65	66	0.018		0.021	<0.001	0.028	0.002	0.006	<0.001
HCRC016	66	67	0.008		0.013	<0.001	0.012	0.001	0.003	<0.001
HCRC016	67	68	0.005		0.010	<0.001	0.001	<0.001	<0.001	<0.001
HCRC016	68	69	0.009		0.010	<0.001	0.004	0.005	0.002	<0.001
HCRC016	69	70	0.010		0.012	<0.001	0.018	0.006	0.006	<0.001
HCRC016	70	71	0.313		0.009	0.001	0.004	<0.001	0.002	<0.001
HCRC016	71	72	0.028		0.011	<0.001	0.004	0.002	<0.001	<0.001
HCRC016	72	73	0.010		0.011	<0.001	0.004	<0.001	0.005	<0.001
HCRC016	73	74	0.006		0.009	<0.001	0.003	<0.001	0.004	<0.001
HCRC016	74	75	0.010		0.009	<0.001	0.009	<0.001	0.004	<0.001
HCRC016	75	76	0.009		0.013	<0.001	0.023	0.004	0.006	0.001
HCRC016	76	77	0.015		0.005	<0.001	0.008	<0.001	0.006	<0.001
HCRC016	77	78	0.010		0.012	<0.001	0.013	<0.001	0.003	<0.001
HCRC016	78	79	0.009		0.009	0.001	0.022	<0.001	0.005	0.003
HCRC016	79	80	0.005		<0.001	<0.001	0.004	<0.001	0.003	<0.001
HCRC016	80	81	0.017		0.004	<0.001	0.009	0.004	0.004	<0.001
HCRC016	81	82	0.123		0.003	<0.001	0.012	<0.001	0.007	<0.001
HCRC016	82	83	1.257		0.006	<0.001	0.010	<0.001	<0.001	<0.001
HCRC016	83	84	0.073		0.004	<0.001	0.008	<0.001	0.002	<0.001
HCRC016	84	85	0.022		0.008	<0.001	<0.001	<0.001	0.004	<0.001
HCRC016	85	86	0.009		<0.001	<0.001	0.002	<0.001	0.004	<0.001
HCRC016	86	87	3.533		0.006	0.027	0.008	<0.001	0.010	0.001
HCRC016	87	88	0.118		0.010	<0.001	0.002	0.001	0.010	<0.001
HCRC016	88	89	0.019		0.010	0.001	0.004	<0.001	0.009	<0.001
HCRC016	89	90	0.020		0.011	<0.001	0.002	<0.001	0.009	<0.001
HCRC016	90	91	0.030		0.008	0.010	0.005	0.005	0.010	<0.001
HCRC016	91	92	0.019		0.012	<0.001	0.004	<0.001	0.009	<0.001
HCRC016	92	93	0.076		0.008	0.008	0.009	<0.001	0.015	0.001
HCRC016	93	94	0.018		0.013	<0.001	0.003	<0.001	0.008	<0.001
HCRC016	94	95	0.010		0.005	<0.001	0.003	0.001	0.006	<0.001

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC016	95	96	0.013		0.005	<0.001	0.002	<0.001	0.005	<0.001
HCRC016	96	97	0.007		<0.001	<0.001	<0.001	0.003	0.004	<0.001
HCRC016	97	98	0.008		0.005	<0.001	<0.001	0.001	0.007	<0.001
HCRC016	98	99	0.009		0.004	<0.001	<0.001	0.004	0.002	<0.001
HCRC016	99	100	0.009		0.007	<0.001	<0.001	<0.001	0.005	<0.001
HCRC016	100	101	0.013		0.011	<0.001	0.003	<0.001	0.004	<0.001
HCRC016	101	102	0.016		0.009	<0.001	0.002	<0.001	0.006	<0.001
HCRC016	102	103	0.016		0.008	<0.001	0.003	<0.001	0.008	<0.001
HCRC016	103	104	0.009		0.004	<0.001	0.003	<0.001	0.006	<0.001
HCRC016	104	105	0.006		0.002	<0.001	0.003	<0.001	0.002	<0.001
HCRC016	105	106	0.021		0.013	<0.001	0.003	<0.001	0.006	<0.001
HCRC016	106	107	0.008		0.012	<0.001	0.004	<0.001	0.003	<0.001
HCRC016	107	108	0.005		0.008	<0.001	0.004	0.004	0.003	<0.001
HCRC016	108	109	0.005		0.007	<0.001	0.002	<0.001	0.006	0.001
HCRC016	109	110	0.006		0.010	<0.001	0.002	0.003	0.006	<0.001
HCRC016	110	111	0.005		0.008	<0.001	0.002	0.004	0.002	0.001
HCRC016	111	112	0.006		0.005	<0.001	0.002	0.002	<0.001	0.001
HCRC016	112	113	0.005		0.009	<0.001	0.002	<0.001	0.002	<0.001
HCRC016	113	114	0.007		0.005	<0.001	0.004	<0.001	0.006	<0.001
HCRC016	114	115	0.041		0.011	0.001	0.017	<0.001	0.005	<0.001
HCRC016	115	116	0.009		0.016	<0.001	0.014	0.001	0.006	<0.001
HCRC016	116	117	0.009		0.010	<0.001	0.008	0.001	0.008	<0.001
HCRC016	117	118	0.007		0.008	<0.001	0.002	0.004	0.005	<0.001
HCRC016	118	119	0.006		0.007	<0.001	0.002	0.003	0.003	<0.001
HCRC016	119	120	0.016		0.005	<0.001	0.002	<0.001	0.003	0.002
HCRC016	120	121	0.005		0.003	<0.001	0.002	<0.001	0.003	0.002
HCRC016	121	122	0.006		0.001	<0.001	0.003	<0.001	0.004	0.002
HCRC016	122	123	0.004		<0.001	<0.001	0.002	0.008	0.005	0.001
HCRC016	123	124	0.004		0.001	<0.001	0.001	<0.001	0.002	0.002
HCRC016	124	125	0.014		0.002	<0.001	0.002	<0.001	0.005	<0.001
HCRC016	125	126	0.014		0.005	<0.001	0.005	0.006	0.004	<0.001
HCRC016	126	127	0.107		0.082	<0.001	0.005	<0.001	0.004	0.026
HCRC016	127	128	3.145		0.048	0.014	0.009	<0.001	0.035	0.021
HCRC016	128	129	0.421		0.017	0.003	0.006	0.002	0.012	0.007
HCRC016	129	130	0.025		0.007	0.001	0.003	<0.001	0.010	0.001
HCRC016	130	131	0.013		0.005	<0.001	0.011	0.004	0.005	0.001
HCRC016	131	132	0.216		0.006	0.002	0.016	0.003	0.006	0.001
HCRC016	132	133	0.022		0.004	<0.001	0.008	<0.001	0.006	<0.001
HCRC016	133	134	0.007		0.007	<0.001	0.015	0.002	0.010	0.001
HCRC016	134	135	0.006		0.004	<0.001	0.005	<0.001	0.008	0.003
HCRC016	135	136	0.011		0.005	<0.001	0.016	<0.001	0.009	0.002
HCRC016	136	137	0.008		0.093	<0.001	0.008	<0.001	0.005	0.028
HCRC016	137	138	0.005		0.003	<0.001	0.006	0.001	0.002	<0.001
HCRC016	138	139	0.011		0.004	<0.001	0.066	<0.001	0.009	0.001
HCRC016	139	140	0.345		0.079	0.012	0.009	<0.001	0.006	0.029
HCRC016	140	141	0.029		0.341	0.003	0.007	<0.001	0.007	0.098
HCRC016	141	142	0.008		0.004	<0.001	0.012	<0.001	0.003	0.002
HCRC016	142	143	0.016		0.006	<0.001	0.005	0.002	0.007	0.002
HCRC016	143	144	0.386		0.003	0.011	0.009	<0.001	0.006	0.005
HCRC016	144	145	0.020		<0.001	<0.001	0.005	0.003	0.002	<0.001
HCRC016	145	146	0.005		0.004	<0.001	0.004	0.003	0.007	0.002
HCRC016	146	147	0.007		0.001	<0.001	0.002	<0.001	0.006	<0.001
HCRC016	147	148	0.007		0.003	<0.001	0.002	<0.001	0.003	<0.001

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC016	148	149	0.003		<0.001	<0.001	0.003	<0.001	0.004	<0.001
HCRC016	149	150	0.005		0.002	<0.001	0.003	<0.001	0.010	<0.001
HCRC017	0	1	No Sample							
HCRC017	1	2	0.041		0.024	0.001	0.001	<0.001	0.005	<0.001
HCRC017	2	3	0.012		0.034	<0.001	0.001	<0.001	<0.001	0.016
HCRC017	3	4	0.021		0.038	0.002	0.002	0.001	0.002	0.003
HCRC017	4	5	0.016		0.041	<0.001	0.002	<0.001	0.006	0.001
HCRC017	5	6	0.026		0.022	<0.001	0.009	0.002	0.004	<0.001
HCRC017	6	7	0.733		0.254	0.004	0.006	<0.001	0.011	0.007
HCRC017	7	8	0.089		0.310	0.003	0.015	0.001	0.018	0.017
HCRC017	8	9	0.035		0.130	0.001	0.005	<0.001	0.013	0.003
HCRC017	9	10	0.035		0.086	0.002	0.003	0.004	0.006	<0.001
HCRC017	10	11	0.016		0.035	0.001	0.002	<0.001	0.007	<0.001
HCRC017	11	12	0.027		0.029	0.003	0.004	0.006	0.013	<0.001
HCRC017	12	13	0.015		0.016	0.002	0.003	<0.001	0.009	<0.001
HCRC017	13	14	0.010		0.016	0.002	0.002	0.001	0.006	<0.001
HCRC017	14	15	0.011		0.013	<0.001	0.002	<0.001	0.006	0.001
HCRC017	15	16	0.012		0.014	<0.001	0.003	<0.001	0.004	<0.001
HCRC017	16	17	0.021		0.027	0.001	0.002	<0.001	0.006	<0.001
HCRC017	17	18	0.014		0.025	0.001	0.003	0.003	0.010	<0.001
HCRC017	18	19	0.011		0.018	0.001	0.003	<0.001	0.006	<0.001
HCRC017	19	20	0.012		0.032	<0.001	0.002	<0.001	0.010	<0.001
HCRC017	20	21	0.029		0.059	0.003	0.007	<0.001	0.021	<0.001
HCRC017	21	22	0.053		0.097	0.003	0.013	<0.001	0.007	<0.001
HCRC017	22	23	0.021		0.058	0.003	0.003	<0.001	0.009	<0.001
HCRC017	23	24	0.016		0.039	0.003	0.003	0.005	0.009	<0.001
HCRC017	24	25	0.014		0.011	<0.001	0.002	0.003	0.006	<0.001
HCRC017	25	26	0.012		0.011	0.003	0.012	<0.001	0.007	<0.001
HCRC017	26	27	0.011		0.035	0.003	0.004	<0.001	0.006	<0.001
HCRC017	27	28	0.006		0.013	<0.001	0.006	<0.001	0.007	<0.001
HCRC017	28	29	0.008		0.006	<0.001	0.003	0.002	0.004	<0.001
HCRC017	29	30	0.007		0.004	<0.001	<0.001	<0.001	0.006	<0.001
HCRC017	30	31	0.018		0.009	0.001	0.003	<0.001	0.007	<0.001
HCRC017	31	32	0.023		0.010	<0.001	0.007	<0.001	0.008	<0.001
HCRC017	32	33	0.012		0.006	<0.001	0.003	<0.001	0.007	<0.001
HCRC017	33	34	0.025		0.008	0.003	0.005	<0.001	0.008	<0.001
HCRC017	34	35	0.018		0.015	0.001	0.002	<0.001	0.007	<0.001
HCRC017	35	36	0.015		0.022	0.002	0.004	<0.001	0.010	<0.001
HCRC017	36	37	0.022		0.017	0.001	0.020	<0.001	0.010	<0.001
HCRC017	37	38	0.030		0.021	<0.001	0.007	0.004	0.008	<0.001
HCRC017	38	39	0.058		0.119	0.002	0.011	<0.001	0.009	0.025
HCRC017	39	40	0.084		0.157	0.005	0.011	<0.001	0.009	0.046
HCRC017	40	41	0.028		0.149	0.007	0.007	<0.001	0.005	0.056
HCRC017	41	42	0.017		0.118	0.011	0.006	<0.001	0.007	0.046
HCRC017	42	43	0.015		0.153	0.003	0.004	<0.001	0.012	0.059
HCRC017	43	44	0.031		0.333	0.007	0.011	0.004	0.011	0.110
HCRC017	44	45	0.038		0.055	0.014	0.005	<0.001	0.007	0.032
HCRC017	45	46	0.025		0.038	0.009	0.005	0.003	0.006	0.017
HCRC017	46	47	0.013		0.070	0.015	0.005	0.004	0.004	0.024
HCRC017	47	48	0.009		0.074	0.007	0.005	<0.001	0.006	0.023
HCRC017	48	49	0.018		0.104	0.006	0.005	<0.001	0.004	0.032
HCRC017	49	50	0.021		0.052	0.005	0.004	<0.001	0.010	0.017
HCRC017	50	51	0.034		0.010	0.005	0.010	0.003	0.010	0.007

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC017	51	52	0.027		0.002	0.006	0.006	<0.001	0.007	0.001
HCRC017	52	53	0.063		0.018	0.009	0.009	<0.001	0.011	0.010
HCRC017	53	54	No Sample							
HCRC017	54	55	0.184		0.193	0.048	0.027	<0.001	0.010	0.153
HCRC017	55	56	0.237		0.182	0.078	0.030	<0.001	0.010	0.166
HCRC017	56	57	0.172		0.163	0.075	0.039	<0.001	0.008	0.152
HCRC017	57	58	0.374		0.179	0.174	0.055	0.006	0.014	0.237
HCRC017	58	59	0.689		0.170	0.123	0.050	0.002	0.012	0.163
HCRC017	59	60	0.066		0.229	0.017	0.014	<0.001	0.015	0.083
HCRC017	60	61	0.066		0.856	0.017	0.038	0.004	0.021	0.295
HCRC017	61	62	0.035		1.141	0.046	0.052	<0.001	0.017	0.334
HCRC017	62	63	0.042		0.937	0.028	0.042	<0.001	0.013	0.278
HCRC017	63	64	0.031		0.559	0.013	0.028	0.003	0.014	0.180
HCRC017	64	65	0.020		0.145	0.020	0.015	<0.001	0.015	0.057
HCRC017	65	66	0.016		0.388	0.019	0.016	0.002	0.018	0.127
HCRC017	66	67	0.012		0.037	0.010	0.013	<0.001	0.005	0.067
HCRC017	67	68	0.006		0.026	0.015	0.005	<0.001	0.005	0.023
HCRC017	68	69	0.004		0.012	0.003	0.003	0.001	0.004	0.009
HCRC017	69	70	0.014		0.214	0.007	0.011	<0.001	0.017	0.068
HCRC017	70	71	0.019		0.091	0.007	0.008	0.002	0.008	0.031
HCRC017	71	72	0.014		0.029	0.009	0.011	<0.001	0.007	0.013
HCRC017	72	73	0.036		0.060	0.005	0.004	<0.001	0.007	0.027
HCRC017	73	74	0.135		0.049	0.012	0.008	<0.001	0.008	0.034
HCRC017	74	75	0.021		0.016	0.004	0.006	<0.001	0.006	0.011
HCRC017	75	76	0.013		0.012	0.003	0.003	<0.001	0.008	0.005
HCRC017	76	77	0.011		0.006	0.001	0.003	<0.001	0.005	0.005
HCRC017	77	78	0.012		0.006	0.003	0.003	<0.001	0.009	0.004
HCRC017	78	79	0.011		0.007	0.005	0.003	<0.001	0.006	0.014
HCRC017	79	80	0.010		0.011	0.003	0.003	<0.001	0.008	0.008
HCRC017	80	81	0.007		0.002	0.003	0.007	0.001	0.008	0.006
HCRC017	81	82	0.008		0.005	0.005	0.008	<0.001	0.005	0.004
HCRC017	82	83	0.009		0.010	0.003	0.010	<0.001	0.003	0.003
HCRC017	83	84	0.008		0.006	0.001	0.041	0.002	0.006	0.004
HCRC017	84	85	0.018		0.007	0.006	0.011	0.002	0.007	0.033
HCRC017	85	86	0.007		0.003	0.003	0.001	<0.001	0.007	0.022
HCRC017	86	87	0.144		0.007	0.011	0.003	<0.001	0.022	0.012
HCRC017	87	88	0.021		0.003	0.002	0.003	<0.001	0.007	0.005
HCRC017	88	89	0.011		0.005	0.003	0.003	<0.001	0.006	0.003
HCRC017	89	90	0.009		0.007	0.004	0.010	<0.001	0.005	0.007
HCRC017	90	91	0.016		0.008	0.005	0.003	0.005	0.006	0.026
HCRC017	91	92	0.015		0.003	0.004	0.003	<0.001	0.005	0.017
HCRC017	92	93	0.447		0.003	0.063	0.011	<0.001	0.004	0.016
HCRC017	93	94	0.052		0.002	0.009	0.013	<0.001	0.008	0.009
HCRC017	94	95	0.019		0.003	0.003	0.018	<0.001	0.004	0.004
HCRC017	95	96	0.014		0.002	0.004	0.003	<0.001	0.005	0.001
HCRC017	96	97	0.014		0.007	0.005	0.004	0.001	0.006	0.022
HCRC017	97	98	0.014		0.007	0.003	0.004	<0.001	0.006	0.007
HCRC017	98	99	0.007		0.013	0.003	0.002	<0.001	0.004	0.009
HCRC017	99	100	0.010		0.013	0.003	0.005	0.004	0.009	0.024
HCRC018	0	1	No Sample							
HCRC018	1	2	0.044		0.064	0.002	0.002	<0.001	0.006	0.026
HCRC018	2	3	0.036		0.052	0.001	0.002	0.004	0.007	0.006
HCRC018	3	4	0.041		0.054	<0.001	0.002	0.002	0.011	0.003

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC018	4	5	0.043		0.054	<0.001	<0.001	0.006	0.013	0.002
HCRC018	5	6	0.047		0.068	<0.001	0.002	0.005	0.007	0.001
HCRC018	6	7	0.029		0.057	<0.001	0.002	<0.001	0.009	0.002
HCRC018	7	8	0.022		0.060	<0.001	0.001	<0.001	<0.001	0.001
HCRC018	8	9	0.020		0.047	0.001	0.003	0.002	<0.001	0.005
HCRC018	9	10	0.015		0.046	<0.001	0.002	0.001	<0.001	0.001
HCRC018	10	11	0.015		0.051	<0.001	0.003	<0.001	0.003	0.001
HCRC018	11	12	0.018		0.059	<0.001	0.001	<0.001	0.002	<0.001
HCRC018	12	13	0.018		0.051	<0.001	0.001	<0.001	0.006	<0.001
HCRC018	13	14	0.013		0.073	<0.001	0.001	<0.001	0.002	<0.001
HCRC018	14	15	0.010		0.041	<0.001	0.002	<0.001	0.002	<0.001
HCRC018	15	16	0.017		0.047	<0.001	0.002	<0.001	0.007	<0.001
HCRC018	16	17	0.012		0.044	<0.001	0.001	0.004	0.002	<0.001
HCRC018	17	18	0.012		0.052	<0.001	0.002	0.004	<0.001	<0.001
HCRC018	18	19	0.012		0.070	<0.001	0.001	<0.001	0.002	<0.001
HCRC018	19	20	0.013		0.078	0.001	0.001	0.007	0.002	<0.001
HCRC018	20	21	0.017		0.072	<0.001	<0.001	<0.001	0.002	<0.001
HCRC018	21	22	0.016		0.116	<0.001	0.001	0.004	0.004	<0.001
HCRC018	22	23	0.048		0.082	0.001	0.004	0.003	0.006	0.001
HCRC018	23	24	0.043		0.118	<0.001	0.004	<0.001	0.003	0.001
HCRC018	24	25	0.052		0.176	<0.001	0.010	<0.001	0.007	0.006
HCRC018	25	26	0.042		0.350	0.001	0.007	<0.001	0.004	0.005
HCRC018	26	27	0.061		0.203	0.001	0.007	0.001	0.007	0.003
HCRC018	27	28	0.067		0.127	0.002	0.004	0.004	0.009	<0.001
HCRC018	28	29	0.073		0.168	<0.001	0.002	0.002	0.009	<0.001
HCRC018	29	30	0.055		0.144	0.001	0.001	<0.001	0.008	<0.001
HCRC018	30	31	0.032		0.134	<0.001	0.002	0.002	0.011	0.001
HCRC018	31	32	0.044		0.148	0.001	0.003	0.001	0.059	<0.001
HCRC018	32	33	0.036		0.120	0.003	0.003	0.002	0.014	<0.001
HCRC018	33	34	0.045		0.221	0.002	0.002	0.005	0.054	<0.001
HCRC018	34	35	0.027		0.164	<0.001	0.002	0.004	0.021	<0.001
HCRC018	35	36	0.043		0.207	0.003	0.004	<0.001	0.030	<0.001
HCRC018	36	37	0.042		0.142	<0.001	0.002	0.004	0.016	0.001
HCRC018	37	38	0.041		0.120	<0.001	0.002	0.002	0.012	<0.001
HCRC018	38	39	0.020		0.047	<0.001	<0.001	<0.001	0.011	<0.001
HCRC018	39	40	0.031		0.054	0.001	0.003	<0.001	0.004	<0.001
HCRC018	40	41	0.027		0.057	<0.001	0.004	<0.001	0.009	<0.001
HCRC018	41	42	0.018		0.060	<0.001	0.003	0.002	0.005	<0.001
HCRC018	42	43	0.065		0.067	0.004	0.006	<0.001	0.009	0.002
HCRC018	43	44	0.077		0.067	0.004	0.008	<0.001	0.003	0.002
HCRC018	44	45	0.032		0.063	<0.001	0.005	<0.001	0.002	0.002
HCRC018	45	46	0.023		0.030	<0.001	0.002	<0.001	0.003	<0.001
HCRC018	46	47	0.011		0.023	0.002	0.003	0.001	0.006	<0.001
HCRC018	47	48	0.007		0.013	0.002	0.001	<0.001	<0.001	0.003
HCRC018	48	49	0.006		0.015	<0.001	0.001	<0.001	0.003	0.005
HCRC018	49	50	0.005		0.009	0.002	<0.001	<0.001	0.003	0.010
HCRC018	50	51	0.005		0.033	<0.001	<0.001	<0.001	0.002	0.009
HCRC018	51	52	0.009		0.033	<0.001	0.002	<0.001	0.004	0.004
HCRC018	52	53	0.011		0.009	0.003	0.002	0.003	<0.001	0.011
HCRC018	53	54	0.022		0.010	0.005	0.005	<0.001	0.002	0.028
HCRC018	54	55	0.013		0.013	0.001	0.002	0.003	0.002	0.010
HCRC018	55	56	0.005		0.011	<0.001	0.003	<0.001	0.005	0.002
HCRC018	56	57	0.008		0.009	<0.001	0.007	<0.001	0.005	0.008

Hole#	From (m)	To (m)	WO3 (%)	Au (g/t)	Cu (%)	Mo (%)	Bi (%)	Sb (%)	Sn (%)	S (%)
HCRC018	57	58	0.011		0.014	<0.001	0.002	0.002	<0.001	0.005
HCRC018	58	59	0.006		0.013	<0.001	0.001	0.003	0.004	<0.001
HCRC018	59	60	0.007		0.010	<0.001	0.001	<0.001	0.006	<0.001
HCRC018	60	61	0.015		0.013	<0.001	0.001	<0.001	0.008	<0.001
HCRC018	61	62	0.015		0.015	<0.001	0.002	<0.001	0.004	<0.001
HCRC018	62	63	0.008		0.008	<0.001	0.001	<0.001	0.003	<0.001
HCRC018	63	64	0.038		0.007	0.001	0.002	<0.001	0.004	0.001
HCRC018	64	65	0.018		0.007	0.003	0.002	0.010	0.003	0.016
HCRC018	65	66	0.731		0.006	0.015	0.023	<0.001	0.024	0.024
HCRC018	66	67	0.416		0.157	0.012	0.004	<0.001	0.010	0.060
HCRC018	67	68	0.031		0.180	0.003	0.001	0.003	0.006	0.059
HCRC018	68	69	0.028		0.034	0.001	0.002	0.001	0.004	0.026
HCRC018	69	70	0.010		0.072	0.003	0.001	0.001	0.002	0.028
HCRC018	70	71	0.011		0.017	0.008	0.002	0.003	<0.001	0.014
HCRC018	71	72	0.008		0.055	0.002	<0.001	0.005	<0.001	0.024
HCRC018	72	73	0.026		0.232	0.003	0.004	<0.001	0.006	0.097
HCRC018	73	74	0.012		0.092	0.001	0.002	<0.001	0.004	0.038
HCRC018	74	75	0.011		0.028	0.004	0.002	<0.001	0.004	0.009
HCRC018	75	76	0.007		0.003	<0.001	<0.001	0.003	0.002	<0.001
HCRC018	76	77	0.113		0.006	0.011	0.004	<0.001	0.004	0.125
HCRC018	77	78	0.020		0.008	0.004	0.003	<0.001	0.006	0.008
HCRC018	78	79	0.123		0.054	0.019	0.005	<0.001	0.006	0.043
HCRC018	79	80	0.019		0.018	0.015	<0.001	0.003	0.005	0.018
HCRC018	80	81	0.017		0.146	0.004	0.002	<0.001	0.003	0.057
HCRC018	81	82	0.013		0.070	0.009	0.003	<0.001	0.002	0.036
HCRC018	82	83	0.018		0.182	0.006	0.002	0.003	0.002	0.066
HCRC018	83	84	0.017		0.078	0.011	0.002	0.002	0.008	0.031
HCRC018	84	85	0.008		0.006	0.003	0.001	0.006	0.002	0.001
HCRC018	85	86	0.063		0.005	0.003	0.001	0.003	<0.001	<0.001
HCRC018	86	87	0.010		0.007	0.003	0.001	<0.001	0.004	<0.001
HCRC018	87	88	0.029		0.007	0.001	0.002	<0.001	0.003	0.001
HCRC018	88	89	0.008		0.007	0.003	0.002	<0.001	0.003	0.002
HCRC018	89	90	0.007		0.010	0.001	0.001	0.007	0.005	0.004
HCRC018	90	91	0.005		0.006	0.001	<0.001	<0.001	0.002	<0.001
HCRC018	91	92	0.008		0.012	0.002	0.003	0.001	0.006	0.003
HCRC018	92	93	0.006		0.006	0.001	<0.001	0.001	0.002	0.002
HCRC018	93	94	0.006		0.008	0.002	<0.001	<0.001	0.005	0.002
HCRC018	94	95	0.007		0.012	<0.001	0.002	0.003	0.006	<0.001
HCRC018	95	96	0.005		0.013	<0.001	<0.001	<0.001	0.002	0.002
HCRC018	96	97	0.004		0.007	0.003	<0.001	<0.001	0.002	0.005
HCRC018	97	98	0.003		0.011	<0.001	<0.001	0.007	0.002	<0.001
HCRC018	98	99	0.005		0.013	<0.001	<0.001	0.003	<0.001	<0.001
HCRC018	99	100	0.005		0.011	<0.001	0.001	0.002	0.005	<0.001